https://doi.org/10.22320/s0718221x/2024.13

ARTÍCULO

Time-moisture superposition principle in creep behavior of white oak with various earlywood vessel locations

Yuge Zhang[1] https://orcid.org/0000-0003-0819-069X
Junfeng Hou[1*] https://orcid.org/0000-0002-6337-9658♠
Haili Chen[1] https://orcid.org/0000-0002-1714-337X
Junjie Cen[1] https://orcid.org/0000-0001-8885-3988
Zhihong Jiang[1] https://orcid.org/0000-0003-2902-1991
Youming Yu[1*] https://orcid.org/0000-0002-2184-8890

[1]Zhejiang A&F University. College of Chemistry and Materials Engineering. Hangzhou, China.
[*]The author had seen the final accepted version.

♠Corresponding author: houjunfeng@zafu.edu.cn

Abstract:
Creep behavior of wood plays a fundamental role in precision processing of wood. In this work, experimental creep tests have been conducted to determine the influence of earlywood vessel location and moisture content on creep behavior of *Quercus alba* (white oak). Time-moisture superposition principle was applied to predict long-term creep behavior of white oak. Results revealed that both of instantaneous and 45-min strain of specimens increased with the increasing of moisture content and decreased with increasing distance between earlywood vessel belt and load-bearing surface significantly. Additionally, the time-moisture superposition principle was found to have feasibility to predict creep behavior of white oak with various earlywood vessel locations and moisture content ranges (6 % - 18 %). We believe that the proposed investigation was beneficial for the processing precision and civil engineering applications of wood.

PAPER ACEPTADO

Keywords: America white oak, creep behavior, earlywood, vessel element, *Quercus alba*, time-moisture superposition principle.

Received: 02.12.2022
Accepted: 19.09.2023

Introduction

Bending emerges as an important methodology towards the precision process of wooden furniture parts and it provokes a wide attention (Moosavi *et al*. 2016; Wang 2017, Báder *et al*. 2019, Gaff *et al*. 2019, Hou *et al*. 2021). The application of bending in the wooden furniture manufacturing brings about beautiful curves and conformable visual/tactile experience, making it warmly welcomed by consumers (Chen 2002).

However, wood bending processing has under-overcome disadvantages lying in high production cost, hyper rate of waste products, great springback rate of bending parts and low utilization rate of materials (Wang and Xu 2014, Wang 2017). Therefore, it is of great significance to understand the bending mechanism of wood to stabilize the quality of bended wood products. It also possesses notable importance for an up-coming green society by reducing the waste of wood.

It has been confirmed that bending property of hardwood was better than the softwoods (Sedighi Moghaddam *et al.* 2017, Gaff *et al*. 2019, Zhang *et al*. 2013, Báder *et al*. 2019). The stress-strain relation was obviously affected by wrinkle formed on cell wall of vessel in the tension and compression surface of elm and ash after pretreatment and compression along the grain, contributing to the realization of compression along the grain of hardwood (Song *et al.* 2003, Song 2008).

Besides, the effect of steam-grain compression on bending property of beech and sessile oak was explored by investigation of the polysaccharides and lignin by FTIR (Báder *et*

PAPER ACEPTADO

al. 2020). Another study revealed that a critical effect was generated to impact flexural strength (IBS) of summer oak and Norway spruce in different thermal modification temperature with corresponding critical temperature 160 ℃ (Gaff *et al*. 2019). Experiments have been conducted to investigate the creep behavior of white oak with various distributions of earlywood vessel, and it was found that instantaneous and 45-min strain of specimens would decrease with increasing distance between earlywood vessel belt and load-bearing surface obviously (Hou *et al*. 2021). The ring-porous wood exhibits obvious advantages in wood bending processing.

The bending and compression process of ring-porous wood is composed of a series of vessel elements under different stress state conditions, exerting a significant influence on the bending processing quality of wood (Song *et al.* 2005, Zhang *et al.* 2013). The stress state of vessel element in different locations is mainly divided into compression, tension and neutral layer in wood bending process (Chen and Zhu 2019). Hence, it is necessary to explore the effect of vessel element with various stress states on wood creep behaviors to reveal the mechanism of wood bending.

Creep behaviors play a critical role in the bending process of wood regardless of tree species, i.e., the hardwood (Hou *et al*. 2021, Yin *et al*. 2021, Song 2008) and softwood (Nakai *et al*. 2018, Wang *et al.* 2020). Many studies have been carried out to investigate the effects of moisture content (MC), temperature and grain orientations on wood static viscoelasticity systematically (Kutnar *et al*. 2021, Hsieh and Chang 2018, Nakai *et al*. 2018). A critical effect appeared on the bending creep of white oak under different temperature, and the corresponding temperature threshold was 50 ℃ (Yin *et al*. 2021).

PAPER ACEPTADO

Instantaneous and creep strain of beech after thermo-hydro-mechanically treatment were confirmed to increase with increasing loadings (Kutnar *et al*. 2021). Besides, the time-stress superposition principle (TSSP) and time-temperatures-stress superposition principle (TTSSP) were applied to simulate the bending creep response characteristics of high temperature treated Chinese fir, indicating that the temperature threshold of TSSP and TTSSP for the prediction of flexural creep behavior of Chinese fir after high temperature treatment was 180 ℃ (Wang *et al*. 2020).

However, little efforts have been poured onto analyzing the effect of earlywood vessel locations and MC on creep behavior of ring-porous wood and its long-term creep behavior prediction in accordance with time-temperatures-moisture superposition principle (TTMSP). For this reason, it is crucial to analyze and predict the creep behavior and the applicability of TTMSP on ring-porous wood.

In this study, the effect of earlywood vessel location and moisture content (MC) on creep behavior of white oak was systematically investigated to reveal the bending mechanism of wood from wood viscoelastic behavior. The applicability of time-moisture superposition principle (TMSP) to creep behavior of white oak with various earlywood vessel location and MC conditions was also studied. This work provides great scientific basis and technical support for processing precision and civil engineering applications of wood.

PAPER ACEPTADO

Materials and methods

Materials

America white oak (*Quercus alba* L.), earlywood and sapwood lumber were purchased from Nanxun Timber Market in Huzhou, China. Size of white oak specimens was 40 mm (Longitudinal: L) × 12 mm (Tangential: T) × 2,2 mm (Radial: R). Four types of specimens were prepared for creep behavior analysis of white oak. As can be seen in Figure 1, a bending loading along the radial direction in a double cantilever fixture was applied to specimen during creep test (Figure 1).

As depicted, Specimen A is the specimen with earlywood vessel in the compression layer, B is with earlywood vessel in the mesne layer, C is with earlywood vessel in the tensile layer and D is the control without earlywood vessel.

PAPER ACEPTADO

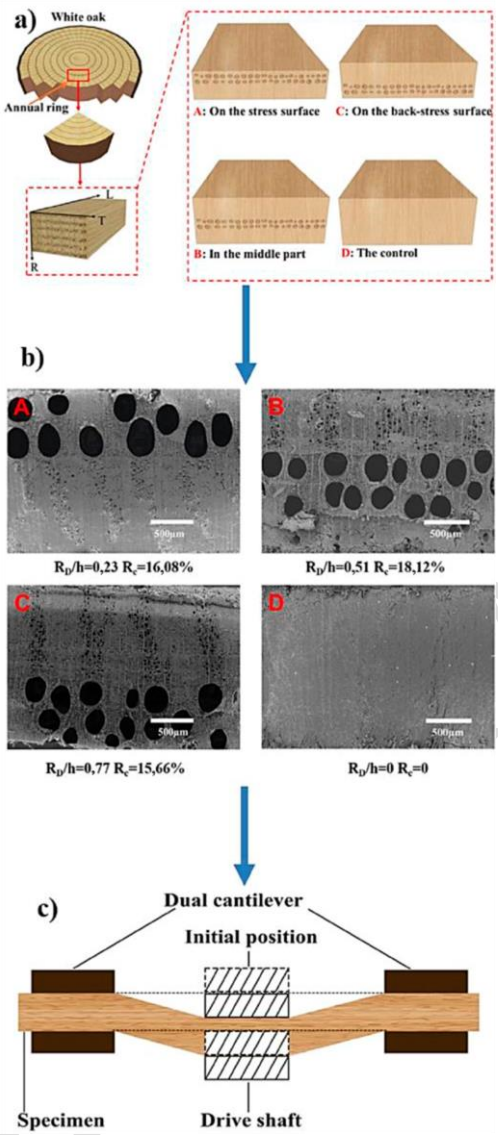


Figure 1: Preparation, numerical characterization and creep test of white oak specimens with various earlywood vessel locations: a) Sample preparation; b) Numerical characterization; c) Creep test.

PAPER ACEPTADO

Numerical characterization of earlywood vessel location

Numerical characterization process of earlywood vessel location characteristics by MATLAB 9.6 (2019a) software is presented in Figure 2. Distribution of earlywood

vessel element in the cross section of specimens was investigated by Scanning electron microscope (SEM, TM-3030, Hitachi Limited, and Tokyo, Japan).

Vessel area ratio (R_C) in the cross-section of specimens was calculated in accordance with the area of earlywood vessel elements and the total area of cross-section of specimens obtained by digital image using MATLAB 9.6 (2019a) software (Figure 2a). Besides, the distance between earlywood vessel belt and load-bearing surface (R_D) was determined by the distance between the central location of earlywood vessel belt and load-bearing surface according to Figure 2b.

Twenty replicated SEM images from three adjacent repeated specimens were applied to calculate R_C and R_D for each type of specimen, and the average R_C and R_D values were used for the subsequent analysis.

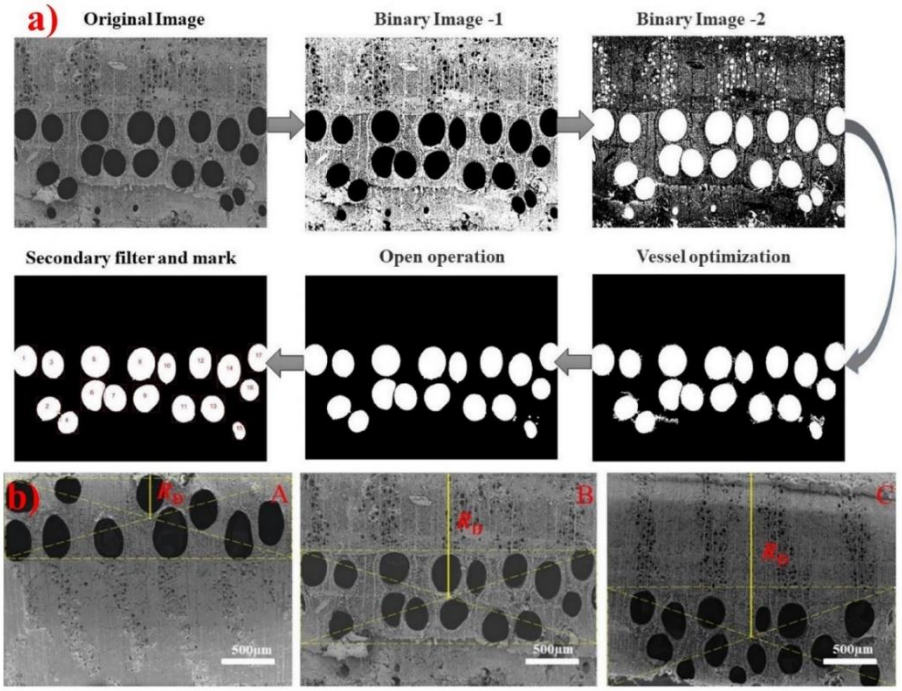


Figure 2: Numerical characterizations processes of earlywood vessel location parameters of specimens: a) Earlywood vessel area ratio (R_C); b) the distance between earlywood vessel and load-bearing surface (R_D).

ACEPTADO

Creep behavior analysis of white oak

The specimens were placed in a high-low humidity alternating test box (EL-10KA, Espec Corporation, USA) to adjust the corresponding moisture content (MC) to 6 %, 9 %, 12 %, 15 %, and 18 %, respectively. Creep behaviors were studied by a dynamic thermomechanical analyzer (DMA-Q800, TA instruments, New Castle, USA) with a bending loading along the radial direction in a double cantilever fixture (Figure 1c) (Hou *et al.* 2021).

In addition, the MC of specimen was controlled by a humidity accessory during creep test. Creep test of white oak specimens was performed at room temperature, and the corresponding RH was controlled to 30 %, 51 %, 71 %, 79 %, and 86 %. A constant stress of 5,0 MPa was applied to investigate bending creep behaviors of specimens as reported in the earlier studies (Wang *et al*. 2018, Yin *et al*. 2021, Hou *et al*. 2021). Besides, the holding time was set to 45 min during creep test. Data of bending creep behaviors was collected and recorded by a DMA procedure. Three repetitions for each type of specimens were prepared.

Results and discussion

PAPER ACEPTADO

Numerical characterization of earlywood vessel location in white oak specimens

Normality analysis (i.e., Gaussian distribution analysis) for earlywood vessel area ratio (R_C) and the distance between earlywood vessel and load-bearing surface (R_D) of specimens are presented in Figure 3 and Figure 4. As depicted in Figure 3, R_C of specimens followed a normal distribution. It indicated that R_C in the cross section of specimens with various earlywood vessel locations was almost the same. Therefore, the number and distribution state of earlywood vessel elements in specimens were consistent, providing basis for the investigation of creep behavior of white oak.

Besides, R_D of specimens with various earlywood vessel distributions followed a normal distribution as illustrated in Figure 4. It indicated that R_D of Specimen A, B, and C were 0,50 ± 0,03 mm, 1,12 mm ± 0,04 mm and 1,70 mm ± 0,02 mm. The obtained data for R_D was then applied to analyze the effect of earlywood vessel locations on creep behavior of white oak. The same conclusion was obtained for the normality test result of R_C and R_D of specimens as shown in Table 1.

PAPER ACEPTADO

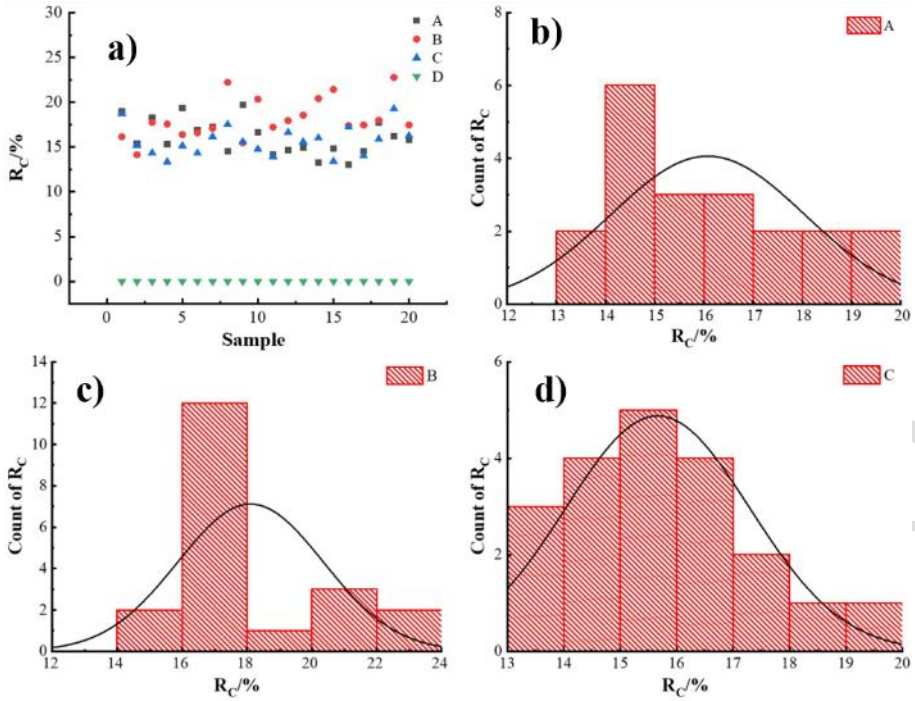


Figure 3: Normality analysis for vessel area ratio in specimens: a) Earlywood vessel area ratio of tested specimens; b) Normality analysis of Specimen A; c) Normality analysis of Specimen B; d) Normality analysis of Specimen C.

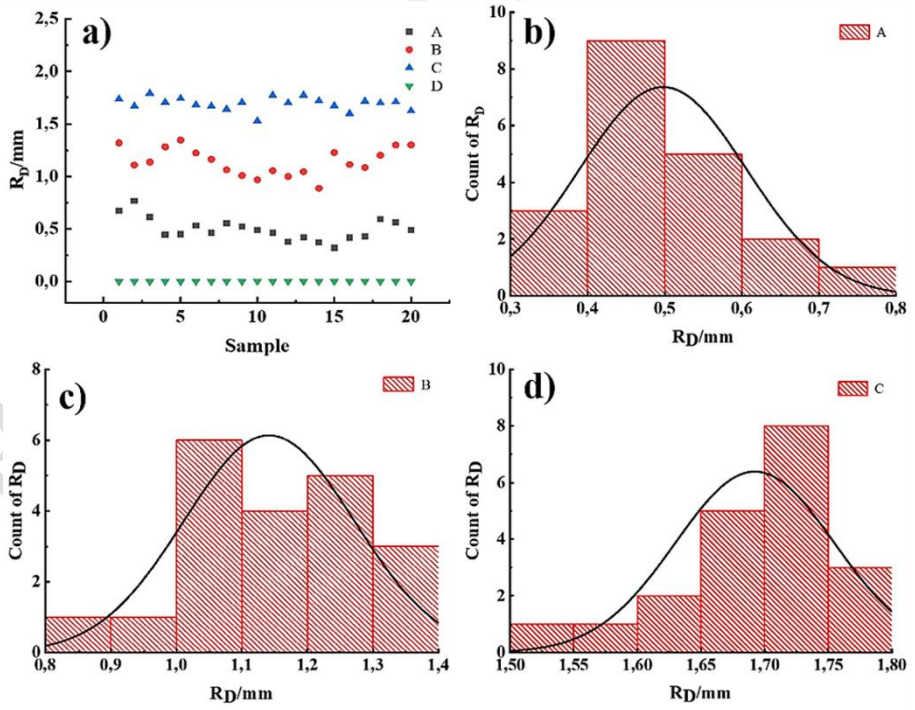


Figure 4: Normality analysis for the distance between earlywood vessel belt and load-bearing surface (R_D) of specimens: a) R_D of specimens; b) Normality analysis of Specimen A; c) Normality analysis of Specimen B; d) Normality analysis of Specimen C.

Table 1: Normality test result of vessel area ratio (R_C) and the distance between vessel and load-bearing surface (R_D) of specimens.

Parameter	A	B	C	D
R_C (Mean[a]±SD, %)	16,08±0,44	18,12±0,50	15,66±0,37	0±0
DF	20	20	20	20
Statistic	0,95	0,92	0,96	-
Prob<W	0,41	0,12	0,45	-
R_D (Mean[a]±SD, mm)	0,50±0,03	1,12±0,04	1,70±0,02	0±0
DF	15	15	15	15
Statistic	0,97	0,95	0,91	-
Prob<W	0,58	0,86	0,14	-

[a] Mean is for repeated specimens. SD is standard deviation.

PAPER ACEPTADO

Earlywood Vessel location-dependent creep behavior of white oak

Figure 5 and Figure 6 presents the creep strain curves of white oak. As depicted in Figure 5, a gradual decrease was observed in creep strain of specimens and the decrement was increased with increasing R_D. The same conclusion was obtained to instantaneous and 45-min strain of specimens. Compared with the control, increment in instantaneous strain of specimens was 24,19 %, 12,89 % and 4,01 % with the increase of R_D from 0, 50 mm to 1,70 mm at the MC of 12 % (Figure 6).

The same result was found in instantaneous strain and 45-min strain of specimens under different MC conditions. An obvious increment of creep strain was observed in Specimen A in comparison with that of Specimen B, C and D. It was also noted that the effect of vessel location on instantaneous strain and 45-min strain of specimens was

significantly at 0,05 levels. As described in the stress concentration problem of holes or circular holes in elasticity based on Lamé equation of elasticity, stress at the edge of holes is much higher than that without holes, and it will also be higher than the stress slightly away from the holes as an elastic body with small holes is subjected to external stress (Hou *et al*. 2021).

The effects of stress on circular hole or circular channel were decreased with the increase of the distance between the circular hole or circular channel and stress in accordance with the Saint-Venant's principle of elastic mechanics (Yin *et al*. 2021, Hou *et al*. 2021). The stress concentration phenomenon of earlywood vessel was more obvious with the increase of R_D as the specimens were subjected to an external stress. The similar conclusion was obtained from our previous study conducted to investigate the effect of temperature and earlywood vessel belt distribution on creep behavior of white oak (Hou *et al*. 2021).

PAPER ACEPTADO

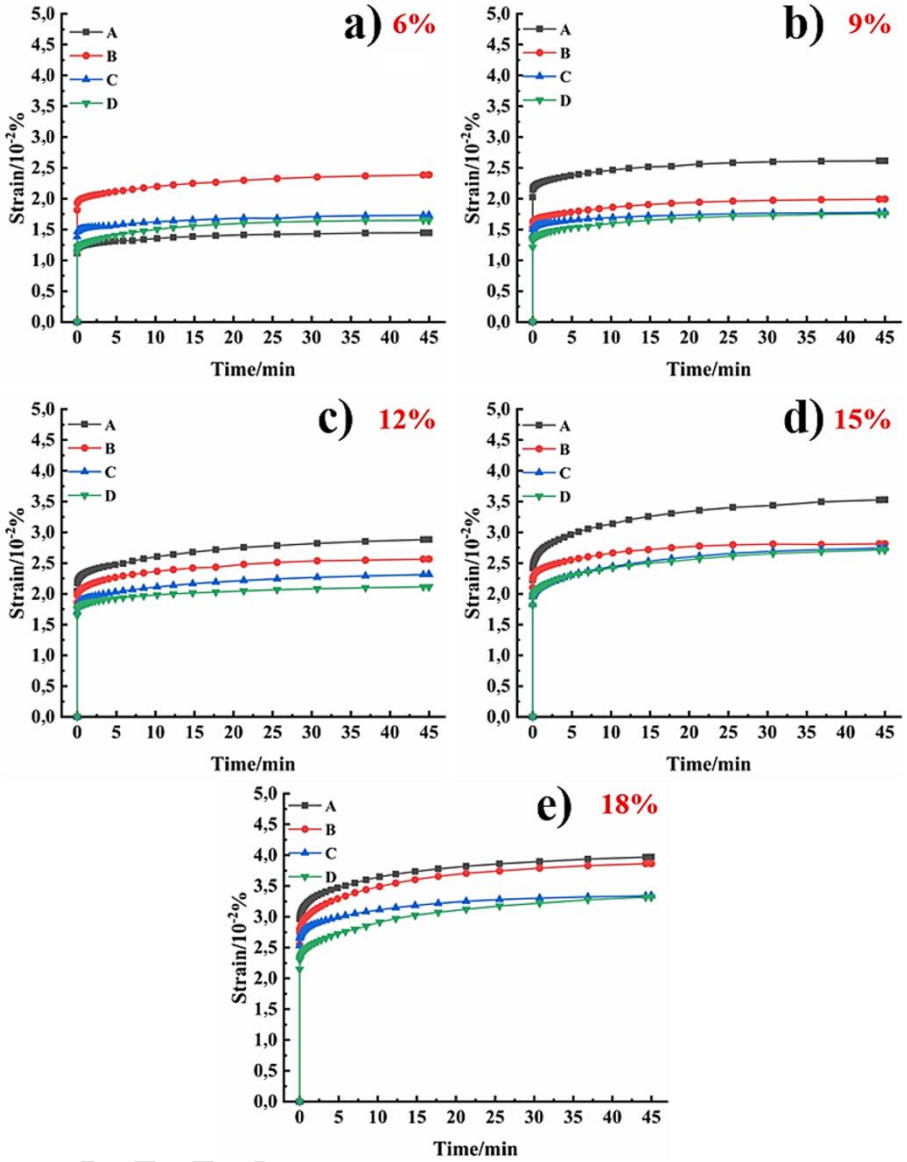


Figure 5: Creep curves of white oak specimens under different earlywood vessel location conditions: a) 6 %; b) 9 %; c) 12 %; d) 12% and e) 15 %.

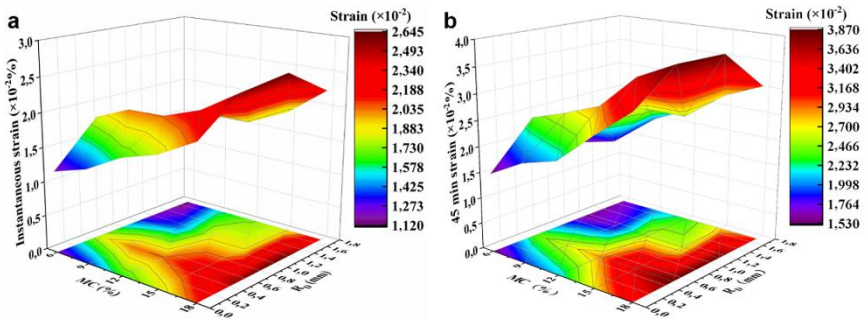


Figure 6: Instantaneous a) and 45-min strain b) of white oak under different MC and earlywood vessel location conditions.

Table 2: Values of variance analysis on instantaneous and 45-min strain of white oak under different MC and vessel location conditions.

Parameter	Source	SS	DF	MS	F	P-value
Instantaneous strain	Vessel location	$7{,}69\times10^{-5}$	3	$2{,}56\times10^{-5}$	14,33	$2{,}85\times10^{-4}$
	MC	$2{,}42\times10^{-4}$	4	$6{,}05\times10^{-5}$	33,83	$1{,}90\times10^{-6}$
	Error	$2{,}15\times10^{-5}$	12	$1{,}79\times10^{-6}$	-	-
	Sum	$3{,}40\times10^{-4}$	19			
45-min strain	Vessel location	$1{,}80\times10^{-5}$	3	$6{,}00\times10^{-5}$	14,85	$2{,}42\times10^{-4}$
	MC	$7{,}34\times10^{-4}$	4	$1{,}83\times10^{-4}$	45,34	$3{,}79\times10^{-7}$
	Error	$4{,}85\times10^{-5}$	12	$4{,}04\times10^{-6}$	-	-
	Sum	$9{,}62\times10^{-4}$	19	-	-	-

Moisture-dependent creep behavior of white oak

Creep strain curves of specimens as a function of time under different MC conditions are displayed in Figure 7. Results revealed that MC significantly affected the creep behavior of specimens (Table 2). As illustrated in Figure 7, creep strain of specimens gradually increased with increasing MC. A slightly increase was observed to creep strain of specimens with the increase of MC from 6 % to 12 %. A remarkable increase in creep strain was generated with further increasing MC to 15 %.

Additionally, increment of creep strain of specimens was increased with increasing MC. This may be attributed to the fact that the bound water exists in microcapillary system of wood with MC lower than fiber saturation point (Placet *et al*. 2007, Placet *et al*. 2012). Hydrogen bonding among the molecular chains in cell wall was weakened with the introduction of water molecules, leading to a decline of mechanical properties in

PAPER ACEPTADO

wood cell wall (Placet *et al*. 2007, Placet *et al*. 2012).

Additionally, obvious swelling is formed in wood cell wall with increasing MC, further resulting in the increase of the free volume and decrease of wood cell wall substance in accordance with free volume theory and an acceleration of molecular movement (Nimez *et al*. 2023). Relative slippage among microfibrils was also observed to increase with increasing MC due to the role of moisture as the plasticizer in wood (Salmén 2004, Navi and Stanzil-Tschegg 2008). Therefore, creep phenomenon of specimens became more and more obvious and increased with increasing MC as expected.

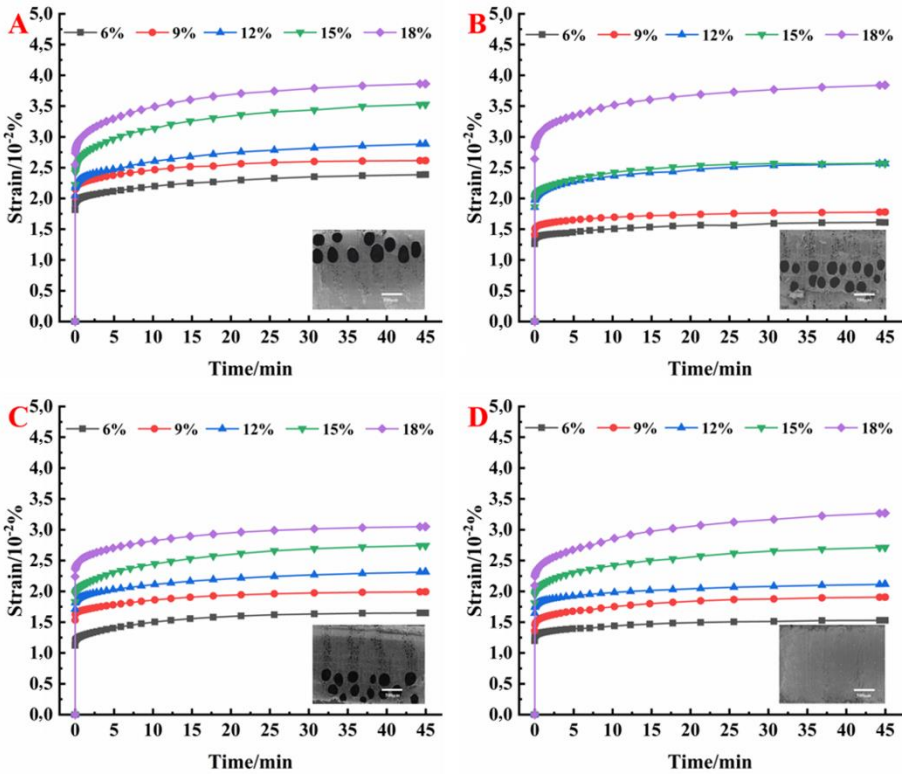


Figure 7: Creep curves of white oak under different MC conditions.

As can be seen in Figure 7, instantaneous and 45-min strain of specimens were increased with increasing MC. Compared with the control, increment of instantaneous

strain of Specimen A was 51,59 %, 48,97 %, 24,19 %, 22,80 % and 21,61 % with the increase of the MC from 6 % to 18 %. The same result was obtained to 45-min strain of Specimen A. Moreover, the corresponding increment in instantaneous and 45-min strain of Specimen B and C was obviously decreased in comparison with that of Specimen A.

Besides, both effects of MC and vessel location on instantaneous and 45-min strain of white oak were significantly at 0,05 levels (Table 2). The F value of MC was greater than that of vessel location, indicating that MC change gradient had a more significant effect on instantaneous and 45-min strain of white oak compared to vessel location. It can be attributed to the fact that moisture absorption capacity of microfibrils is weaker than the matrix (Kojima and Yamamoto 2005, Englund and Svensson 2011).

Therefore, the effect of MC on creep strain of wood was mainly determined by microfibril angle. When longitudinal swelling was occurred to the matrix, binding force on the matrix longitudinal swelling caused by microfibrils increased with the decrease of microfibril angle, leading to a decline in the longitudinal creep deformation of wood cell wall finally (Lichtenegger *et al*. 1999, Hein and Liam 2012, de Borst *et al*. 2012, Thomas *et al*. 2014). The binding force on the matrix longitudinal swelling caused by microfibrils was also decreased with further increasing microfibril angle greater than 45°, and the longitudinal creep compliance of wood was obviously increased with increasing MC (Roszyk *et al*. 2012, Hein and Liam 2012, Kaboorani *et al*. 2013). Therefore, instantaneous and 45-min strain of white oak were increased with the increase of MC.

PAPER ACEPTADO

Time-moisture superposition principle (TMSP) in creep response of white oak

It was found that the increase of the MC and R_D had an inverse effect on the creep behavior of white oak in the creep test process (Figure 5 and Figure 7). However, little efforts have been poured onto predicting long-term creep behavior of ring-porous wood with various earlywood vessel locations. It is crucial to analyze and predict the long-term creep behavior of ring-porous wood for its future application in processing precision of wood. Williams-Land-Ferry (WLF) model has been widely used to predict the long-term viscoelasticity behavior of wood (Dlouhá *et al*. 2009, Peng *et al*. 2021, Wang *et al*. 2020).

The moisture dependence of strain can be expressed as Equation 1 according to WLF model.

$$Log(a_T) = \frac{-D_1 x\left(MC - MC_0\right)}{-D_2 - \left(MC - MC_0\right)} \qquad (1)$$

Where, $log(a_T)$ is shifting factor; MC is moisture content of specimen; MC_0 is the referenced moisture content of specimen; D_1 and D_2 is the constant.

45-min creep curves of specimen with various earlywood vessel locations and MCs (6 % - 18 %) were plotted as strain versus log time and shifted horizontally according to TMSP to build the master curves, as depicted in Figure 8. Creep test performed at 6 %

PAPER ACEPTADO

MC was selected as a reference in this study. As depicted, the short-term creep curves of specimens for 45 min can be processed by TMSP to obtain the long-term creep curves for $10^{7,16}$ s (Specimen A), $10^{8,27}$ s (Specimen B), $10^{8,81}$ s (Specimen C) and $10^{8,83}$ s (Specimen D).

It was concluded that TMSP was feasible to predict creep behavior of white oak wood with various earlywood vessel locations and MC ranges. Additionally, the time span of long-term creep curves was increased with increasing R_D, and smaller than that of the control. It can be attributed to the fact that the creep of specimen with earlywood vessel is greater than that of the control in accordance with the stress concentration problem of holes or circular holes in elasticity based on Lamet equation of elasticity (Hou *et al*. 2021).

Additionally, the effects of stress on circular hole or circular channel were decreased with increasing distance between the circular hole or circular channel and stress in accordance with the Saint-Venant's principle of elastic mechanics. The stress concentration phenomenon of earlywood vessel was more obvious with the increase of the distance between the stress and earlywood vessel as the specimens were subjected to an external stress.

Relationship between shift factors (log (a_T)) and MC of specimens is presented in Figure 9. It indicated that the curves between horizontal shift factor (log (a_T)) and MC of specimens met the requirements of WLF equation with *R*2 values ranged from 0,991 to 0,999. It was concluded that the WLF model would provide excellent agreement with the shift factor (log (a_T)) over the measured MC ranges (6 % - 18 %) of specimens with

PAPER ACEPTADO

various vessel locations. WLF equation can be used to effectively express the relationship between the MC and the time of bending creep of white oak wood, which provides the great scientific basis and technical support for processing precision and civil engineering applications of wood.

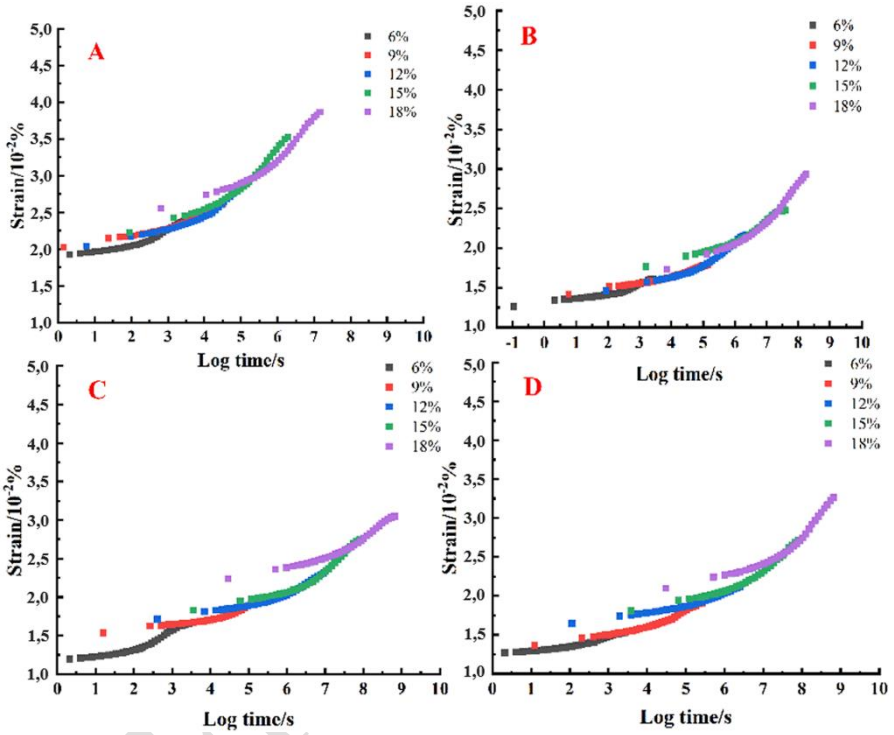


Figure 8: Master curve of creep behavior at different MCs at a referenced MC of 6 %.

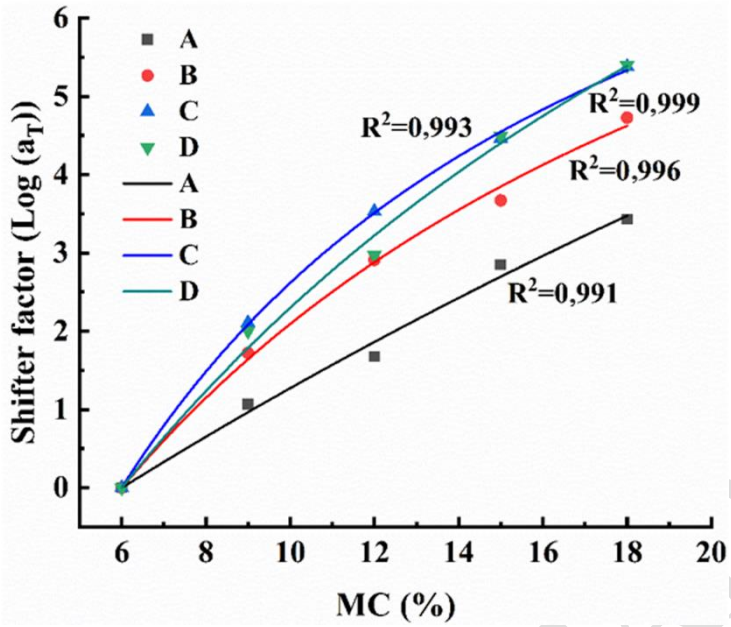


Figure 9: Relationship between shift factors (log (a_T)) and MC of specimens.

PAPER ACEPTADO

Conclusions

The effect of earlywood vessel location and MC on creep behavior of white oak was systemically investigated by DMA. Results revealed that the effect of earlywood vessel location and MC on creep strain of white oak was significantly. Both instantaneous and 45-min strain of specimens were obviously increased with increasing MC and remarkably decreased with the increase of R_D. The short-term creep curves of specimens for 45 min can be processed by TMSP to obtain the long-term creep curves from $10^{7,16}$ s to $10^{8,83}$ s. Furthermore, the relationship between time and MC of creep characteristics for white oak can be effectively described by WLF equation. Therefore,

we believe that the proposed investigation was beneficial for the processing precision and civil engineering applications of wood

Authorship contributions

Y. Z.: Investigation, methodology, data curation, writing-original draft. J. H.: Conceptualization, methodology, writing-review & editing，funding acquisition. H. C.: Investigation, writing-review & editing. J. C.: Investigation, data curation. Z. J.: Writing-review & editing，funding acquisition. Y. Y.: Conceptualization, writing-review & editing, supervision, project administration.

Acknowledgments

The authors thank the National Natural Science Foundation of China (32201492; 31670561) and Talent Startup Project of Scientific Research and Development Foundation of Zhejiang A & F University (2020FR020) for supporting this paper.

PAPER ACEPTADO

References:

Báder, M.; Németh, R.; Konnerth, J. 2019. Micromechanical properties of longitudinally compressed wood. *European Journal of Wood and Wood Products* 77(3): 341-351. https://doi.org/10.1007/s00107-019-01392-0

Báder, M.; Németh, R.; Sandak, J.; Sandak, A. 2020. FTIR analysis of chemical changes in wood induced by steaming and longitudinal compression. *Cellulose* 27(12): 6811-6829. https://doi.org/10.1007/s10570-020-03131-8

Chen, G.R. 2002. Elasticity. Hehai University Press, Nanjing, People's Republic of China.

Chen, Y.S.; Zhu, J. 2019. Study on bending characteristics of fast-growing Eucalyptus bookcase shelves by using burgers model. *Wood Research* 64(1): 137-144. http://www.woodresearch.sk/cms/study-on-bending-chracteristics-of-fast-growing-eucalyptus-bookcase-shelves-by-using-burgers-model/

Dlouhá, J.; Clair, B.; Arnould, O.; Horáček, P.; Gril, J. 2009. On the time-temperature equivalency in green wood: Characterization of viscoelastic properties in longitudinal direction. *Holzforschung* 63(3): 327-333. https://hal.archives-ouvertes.fr/hal-00437887

de Borst, K.; Bade, T.K.; Wikete, C. 2012. Microstructure-stiffness relationships of ten European and tropical hardwood species. *Journal of Structural Biology*

177(2):532-542. http://doi.org/10.1016/j.jsb.2011.10.010
Englund, E.T.; Svensson, S. 2011. Modeling time-dependent mechanical behavior of softwood using deformation kinetics. *Holzforschung* 65(2): 231-237. https://doi.org/10.1515/HF.2011.011
Gaff, M.; Kačík, F.; Gašparík, M. 2019. Impact of thermal modification on the chemical changes and impact bending strength of European oak and Norway spruce wood. *Composite Structures* 216: 80-88. https://doi.org/10.1016/j.compstruct.2019.02.091
Hein, P.R.G.; Lima, J.T. 2012. Relationships between microfibril angle, modulus of elasticity and compressive strength Eucalyptus wood. *Maderas. Ciencia y Tecnología* 14(3): 267-274. https://doi.org/10.4067/S0718-221X2012005000002
Hou, J.F.; Jiang, Y.Q.; Yin, Y.Q.; Zhang, W.G.; Chen, H.L.; Yu, Y.M.; Jiang, Z.H. 2021. Experimental study and comparative numerical modeling of creep behavior of white oak wood with various distributions of earlywood vessel belt. *Journal of Wood Science* 67(1): e57. https://doi.org/10.1186/s10086-021-01989-1
Hsieh, T.Y.; Chang, F.C. 2018. Effects of moisture content and temperature on wood creep. *Holzforschung* 72(12): 1071-1078. https://doi.org/10.1515/hf-2018-0056
Kaboorani, A.; Blanchet, P.; Laghdir, A. 2013. A rapid method to assess viscoelastic and mechanosorptive creep in wood. *Wood and Fiber Science* 45: 370-382. https://wfs.swst.org/index.php/wfs/article/view/61
Kojima, Y.; Yamamoto, H. 2005. Effect of moisture content on the longitudinal tensile creep behavior of wood. *Journal of Wood Science* 51(5): 462-467. https://doi.org/10.1007/s10086-004-0676-5
Kutnar, A.; O'Dell, J.; Hunt, C.; Frihart, C.; Kamke, F.; Schwarzkopf, M. 2021. Viscoelastic properties of thermo-hydro-mechanically treated beech (*Fagus sylvatica* L.) determined using dynamic mechanical analysis. *European Journal of Wood and Wood Products* 79(2): 263-271. https://doi.org/10.1007/s00107-020-01629-3
Lichtenegger, L.; Reiterer, A.; Stanzl-Tschegg, S.E.; Fratzl, P. 1999. Variation of cellulose microfibril angles in softwoods and hardwoods-A possible strategy of mechanical optimization. *Journal of Structural Biology* 128(3): 257-269. https://doi.org/10.1006/jsbi.1999.4194
MATLAB 9.7 2019. MathWorks. INC: Natick City, Massachusetts, United States.
Moosavi, V.; Eslam, H.K.; Bazyar, B.; Najafi, A.; Talaeepoor, M. 2016. Bending creep behavior of Hornbeam wood. *Drvna Industrija* 67(4): 341-350. https://doi.org/10.5552/drind.2016.1609
Nakai, T.; Toba, K.; Yamamoto, H. 2018. Creep and stress relaxation behavior for natural cellulose crystal of wood cell wall under uniaxial tensile stress in the fiber direction. *Journal of Wood Science* 64(6): 745-750. https://doi.org/10.1007/s10086-018-1767-z
Navi, P.; Stanzil-Tschegg, S. 2008. Micromechanics of creep and relaxation of wood. A review COST Action E35 2004-2008: Wood machining-micromechanics and fracture. *Holzforschung* 63(2):186-195. https://doi.org/10.1515/HF.2009.013
Nimez, P.; Teischinger, A.; Sandberg, D. 2023. Springer handbook of wood science and technology. *Springer Handbook of Wood Science and Technology.*

https://doi.org/10.1007/978-3-030-81315-4
Peng, H.; Zhang, T.Y.; Jiang, J.L.; Zhang, Y.L.; Cao, J.Z.; Lu. J.X. 2021. Comparison of the time-moisture and time-temperature equivalences in the creep properties of Chinese fir. *Wood Material Science & Engineering* 17(6): 911-917. https://doi.org/10.1080/17480272.2021.1976273
Placet, V.; Passard, J.; Perré, P. 2007. Viscoelastic properties of green wood across the grain measured by harmonic tests in the range 0 ºC - 95 ºC: Hardwood vs. softwood and normal wood vs. reaction wood. *Holzforschung* 61(5): 548-557. https://doi.org/10.1515/HF.2007.093
Placet, V.; Cisse, O.; Boubakar, M.L. 2012. Influence of environmental relative humidity on the tensile and rotational behavior of hemp fibers. *Journal of Materials Science* 47(7): 3435-3446. https://doi.org/10.1007/s10853-011-6191-3
Roszyk, E.; Mania, P.; MoliŃski, W. 2012. The influence of microfibril angle on creep Scotch pine wood under tensile stress along the grains. *Wood Reseach* 57(3): 347-358. http://www.woodresearch.sk/wr/201203/01.pdf
Salmén, L. 2004. Micromechanical understanding of the cell-wall structure. *Comptes Rendus Biologies* 327(9-10): 873-880. https://doi.org/10.1016/j.crvi.2004.03.010
Sedighi Moghaddam, M.; Van den Bulcke, J.; Wålinder, M.E.P.; Claesson, P.M.; Van Acker, J.; Swerin, A. 2017. Microstructure of chemically modified wood using X-ray computed tomography in relation to wetting properties. *Holzforschung* 71(2): 119-128. https://doi.org/10.1515/hf-2015-0227
Song, K. Y. 2003. The technology of wood compressing and multi-direction bending, Master thesis. Ha'erbin, Northeast Forestry University, People's Republic of China.
Song, K.Y. 2008. Study on the technology of longitudinal compressing and multi-dimensional bending of wood, Ph.D. thesis. Ha'erbin, Northeast Forestry University, People's Republic of China.
Song, K.Y.; Wang, F.H.; Song, Y.H. 2005. The techniques of F. MandhuRica, Longitudinal compression and bending. *Furniture* 5: 18-23. https://link.cnki.net/doi/10.16610/j.cnki.jiaju.2005.03.010
Thomas, L.H.; Forsyth, V.T.; Martel, A.; Grillo, I.; Altaner, C.M.; Jarvis, M.C. 2014. Structure and spacing of cellulose microfibrils in woody cell walls of dicots. *Cellulose* 21(6): 3887-3895. http://doi.org/10.1007/s10570-014-0431-z
Wang, C.; Wu, Q.; Lin, P.; Yang, D.; Yu, Y.M. 2018. Orthotropic creep performance of small flawless oak board. *Scientia Silvae Sinicae* 54(4): 79-86. https://doi.org/10.11707/j.1001-7488.20180409
Wang, J.F.; Wang, X.; He, Q.; Zhang, Y.L.; Zhan, T.Y. 2020. Time-temperature-stress equivalence in compressive creep response of Chinese fir at high-temperature range. *Construction and Building Materials* 235: e117809. https://doi.org/10.1016/j.conbuildmat.2019.117809
Wang, J.; Xu, W. 2014. Research status and development trend of the techniques of solid wood longitudinal compressing and bending. *Furniture* 35(5): 15-19. https://doi.org/10.16610/j.cnki.jiaju.2014.05.001
Wang, S.L. 2017. Research and application of Michael Thonet's wood bending techniques. *Furniture & Interiors* 5:16-17. https://link.cnki.net/doi/10.16771/j.cn43-
PAPER ACCEPTED

1247/ts.2017.05.003
Yin, Y.Q.; Hou, J.F.; Jiang, Z.H.; Yu, Y.M. 2021. Effect of earlywood vessel distribution on creep characteristics of ring-porous oak wood. *Journal of Forestry Engineering* 6(3): 54-60. https://doi.org/10.13360/j.issn.2096-1359.202009045
Zhang, Y.; Tong, D.; Song, K.Y. 2013. Stress-strain constitutive relation of longitudinal compressed *Fraxinus mandshurica* Rupr. with hydrothermal-microwave treatment. *Journal of Nanjing Forestry University (Natural Sciences Edition)* 56(4): 105-109. http://nldxb.njfu.edu.cn/CN/10.3969/j.issn.1000-2006.2013.04.020

PAPER ACEPTADO