

Production of Cellulose From Different Species of Banana (*Musa Paradisiaca*) Mid Rib Waste: A Sustainable Raw Material for Industrial Applications

Nelly Ndukwe

ndukwe.nelly@yahoo.com

Mountain Top University

Ilesanmi Nathanael

Mountain Top University

Olusegun O. Ezekiel

Mountain Top University

Research Article

Keywords: Banana Mid Rib, Cellulose Production, *Musa paradisiaca*, Pulping Process, Holocellulose

Posted Date: July 17th, 2026

DOI: <https://doi.org/10.21203/rs.3.rs-10384026/v1>

License: © ⓘ This work is licensed under a Creative Commons Attribution 4.0 International License. [Read Full License](#)

Additional Declarations: The authors declare no competing interests.

Abstract

Wood fibre has been the primary sources of raw materials for the production of cellulose for pulp and paper, bio-energy development and other industrial applications and this has not only encouraged deforestation but led to high cost of cellulose. This study examined the potential of generating cellulose pulp from four different species of banana (*Musa paradisiaca*) mid rib wastes commonly known in Nigeria as Ibo banana, Saro, Paranta, and Ogede omini via alkaline sulphite pulping process using 1: 1 ratio of NaOH and NaHSO₃. The results gave the percentage yield of cellulose of 30% to 40% with the highest cellulose of 40% being produced from *Musa paradisiaca* (Paranta), the same amount of 35% cellulose yield were obtained from *Musa paradisiaca* (Ogede omini) and *Musa paradisiaca* (Ibo banana) respectively while the lowest cellulose was produced by *Musa paradisiaca* (Saro). Holocellulose range of 80% to 71% was recorded while the alpha cellulose and hemicellulose were calculated respectively. The FTIR characterization of the cellulose from each banana mid rib species confirmed their chemical identity. The Fiber Length, Fiber Diameter, Lumen Width, Cell Wall Thickness, Runkel, Flexibility, Slenderness ratios and Coefficient of rigidity indicated that the mid rib cellulose from each of the banana species have suitable long fibers and good tensile strength properties for industrial cellulose applications and morphological properties of the fibers shown by the (SEM) analysis also confirmed the alignment of the cellulose fibers, thus making the various banana mid rib wastes a viable potential for cellulose production.

Introduction

Wood cellulose has been a traditional source of raw materials for paper industry and increasing demand for pulp and paper products due to rapid technological advancement has further worsened the global environmental impact arising from deforestation. Currently, there has been a continuous effort into finding viable and sustainable sources of cellulose fibers [1]. Furthermore, the emission of greenhouse gases from the combustion of fossil fuels has generated public concern and has shifted research focus to the use of agricultural wastes as alternative and sustainable feedstocks for biogeny development [2]

The generation of biomass wastes emanating from agricultural residues have continued to gain increasing attention recently especially in developing countries where poor waste management practices are dominant, thereby raising environmental and health concerns. Across the globe, 140 Gt of agricultural wastes are produced every year and about 517 million tons of these biomaterials are unutilized. Over 60% of agricultural residues generated in the world have been evaluated to come from low-income countries like Nigeria, again Nigeria is one of the major producers of banana fruit crop [3]

Banana as an abundant agricultural resource is overly cultivated amongst the tropical nations of the world such as Nigeria. Banana fruit is believed to be the eighth most essential plant globally and one of the world's most crucial agricultural food and staple crops, from 135 countries, 148 million tons were produced; It has been evaluated as a necessary requirement to achieving food security and it served as a staple food for over 400 million people across the world [4]. The crop has lots of economic benefits ranging from affordable sources of raw materials for industrial uses to finished products. On the other hand, these vast chains of industrial processes produce large volume of waste amounting to 200 tons on daily basis [5]. These abundant bio-resources can be potentially harnessed into various industrial applications such as organic fertilizers, biochemicals, animal feedstuff and bioenergy development [6, 7]. Several studies and investigations have been carried out on banana pseudo-stem, FAO. [8]

The banana pseudo-stem has been used in the generation cellulose pulp fibers for textiles, pulp and paper industries, in the production of confectionaries, liquid fertilizer and vermin-compost [9, 10, 11]. Recently, the banana pseudo-stem has been employed as a potential alternative cheap feed raw material [12].

Furthermore, the studies have shown that over 353,443 tons of banana peel, empty banana bunch, the rejected banana fruit generated annually can be effectively utilized in the production animal feed and some other medicinal uses [13].

It has been reported that the use of banana wastes facilitates the rate of bioremediation of crude oil polluted soil by enhancing soil aeration and increasing the water holding capacity of the soil material [14]. investigation into the use of banana peels as a low-cost adsorbent for the removal of heavy metals such as zinc (Zn), copper (Cu), and manganese (Mn) in synthetic water and its adsorption capacity has been conducted [15]. While, the study in the development of industrial adsorbent using banana peel activated carbon for treatment of water contaminated with various heavy metals like Mn, Pb, Zn and Fe has also been documented [16]. However, current study on the potential cellulose sources from different species of banana leaf mid rib abundant in Nigeria is still under investigated.

Materials And Methods

The chemicals and reagents used in the sample characterization and analyses were of analytical grades obtained from Sigma Aldrich UK, while the 97% grade sodium hydrogen sulphite (NaHSO_3) and sodium hydroxide (NaOH) used for the pulping investigation was manufactured by JHY CHEM, Tianjin Jiahengyuan Chemicals Co., Ltd.

Sample Collection and Preparation

The four different species of the banana mid rib waste investigated were sourced from Mountain Top University farmland at Km 12, Lagos/Ibadan Expressway, Ogun State, Nigeria (Geographical location – 6.7292° N, 3.4126° E). The banana mid rib was carefully separated from their parent leaves and was cut into smaller suitable sizes of 0.05 m diameter in accordance with TAPPI T257 test method.

Pulping Investigation

Each of the mid rib species of 250 g mass were subjected to alkaline sulfite chemical pulping. The white liquor used in pulping was prepared by dissolving NaOH (25 g) and NaHSO_3 (25 g) in 500 mL of distilled water and the 250 g of each sample was weighed into 1 L Erlenmeyer flask containing the white liquor. The flasks were carefully sealed with cotton wool and later placed inside a stainless vertical autoclave with model: YX-280A England (18L), NO. E280AHK220355 and pressure 0.14MPa- 0.165MPa with working volt: AC220V 50 Hz 2.0 kw and G.W/N. W:16.5/15kg. The reaction was done for 90 min at a temperature of 16 °C and at the completion of pulping process, the cellulose pulp was separated from the black liquor, washed with deionized water and then air-dried for 24 h to give a bright fluffy pulp [17].

. Determination of Extractive Content

The extractive contents of the different samples were determined using Soxhlet extractor in accordance with standard Tappi T204 om-88 test method under a solvent mixture of ethanol and acetone in the ratio 1:2 using 4 g

each of the air-dried biomass of sample size 0.25 to 0.5 cm diameter and were put into the extraction thimble and covered with cotton wool. Reflux was carried out for 6 h with Soxhlet extraction apparatus and the solvent obtained at the end of each extraction process was evaporated at reduced pressure and the weight of the dried extractive content obtained [18].

Determination of Lignin Content

The lignin contents for each of the biomass waste samples were determined on the 1.00 g each of the extractive free the corn stalk, corn cob, corn husk and corn leaf was placed in a 50 mL beaker containing 15 mL of 72% H_2SO_4 at 25°C for 2 h after which the reaction medium was transferred into a 1000 mL Erlenmeyer flask. The acid was diluted by adding 575 mL of distilled water after which the contents of the flask was refluxed for 4 h, allowed to cool and filtered. The residue was washed free of acid, then oven-dried to constant weight at a temperature of 105°C [19].

Determination of Holocellulose

The holocellulose determination was conducted by weighing 3 g each of the mid rib sample oven-dried samples into a 250 ml flask with watch glass cover and 150ml of distilled water, at interval of an hour 0.2 ml of cold glacial acetic acid, and one gram of NaClO_2 was added for five hours and the flask was placed into a water bath at 70°C-80°C. The content of the flask was filtered off with Buchner funnel and washed free of ClO_2 with cold distilled water. The residue was then dried at 105°C in an oven and cooled in a desiccator and weighed repeatedly to obtain a consistent weight [20].

Determination of Alpha Cellulose

3g of oven-dried sample of the respective corn waste was weighed into a 250 ml Erlenmeyer containing 17.5 percent NaOH and 50 ml of distilled was placed in water bath at a temperature of 20°C and stirred for 30 min. The reaction medium was transferred into a Buchner funnel and filtered and the residue was cleaned with 40 ml of 10% acetic acid and 40 ml of 8.3% NaOH after which 1000 mL of hot tap water was employed for the removal of the acid from the acid from the residue. The residue was finally dried at 105° C in an oven at a constant weighed [20].

Hemicellulose Cellulose Determination

The amount of non-sugar monomer present in the four different waste samples was determined by subtracting the alpha cellulose content from the holocellulose content.

Fiber Morphological Characterization

The morphological determination of the cellulose pulp produced each of banana mid rib waste was carried out by macerating the samples in a solution of 1:1 HNO_3 and KClO_3 for 30 min and the macerated samples were measured using an optical digital microscope (Olympus CX23). 20 fibers of each sample were analyzed and the average reading was taken in accordance with ASTM D-1037-12 2020 and ASTM D-1413-61 2007 [21, 22].

Results And Discussion

The results obtained from the pulping investigation in Table 1 showed that *M. paradisiaca* (P) banana mid rib specie gave the highest cellulose pulp yield of 40.10%, equal amount of cellulose of 35.23% and 35.30% was produced by *M. paradisiaca* (I) and *M. paradisiaca* (O) banana species respectively while *M. paradisiaca* (S) produced lowest pulp yield of 30.20%. It was also observed that there was similarity in the amount of lignin and extractive contents of the four-banana mid rib and these results correlate with the yield of pulp lignin and extractive contents of Nigerian sawdust wood species [17].

Table 1

The mean percentage yield of cellulose pulp, lignin, extractive and ash contents obtained from the different species of Banana Mid-Rib Waste

Different Species of Banana Mid-Rib Waste	Common Nigeria Names	Mean Pulp Yield (Cellulose) (%)	Lignin (%)	Extractive Content (%)	Mean Moisture Content (%)	Mean Ash Content (%)
<i>M. paradisiaca</i> (S)	Saro	30.20 ± 1.20	12.00 ± 0.05	3.0 ± 0.45	10.01 ± 0.54	2.50 ± 0.05
<i>M. paradisiaca</i> (P)	Paranta	40.10 ± 1.05	13.80 ± 0.02	4.0 ± 0.47	12.00 ± 0.62	2.65 ± 0.03
<i>M. paradisiaca</i> (I)	Ibo banana	35.25 ± 1.00	14.05 ± 0.03	3.7 ± 0.50	10.23 ± 0.54	2.60 ± 0.04
<i>M. paradisiaca</i> (O)	Ogede Omini	35.30 ± 1.05	13.50 ± 0.03	3.5 ± 0.50	9.50 ± 0.60	2.70 ± 0.10

The alpha cellulose content (Table 2) of 30% obtained from the mid rib species implies that their utilization in pulp and paper products formation will impact favorably in tensile strength. The highest holocellulose content of 80% was produced from *M. paradisiaca* (P), while 79% and 78% was recoded from *M. paradisiaca* (I) and *M. paradisiaca* (O) with the lowest holocellulose content of 71% from *M. paradisiaca* (S). These results correlate with that of wheat straw and oil palm trunk making the banana mid rib waste suitable alternative sources of cellulose fibers [23].

Table 2

The percentage Alpha Cellulose, Hemi Cellulose and Holo Cellulose of different Species of Banana Mid-Rib Waste

Different Species of Banana Mid-Rib Waste	Common Nigeria Names	Alpha Cellulose (%)	Hemi Cellulose (%)	Holo Cellulose (%)
<i>Musa paradisiaca</i> (S)	Saro	28.01	43.00	71.01
<i>Musa paradisiaca</i> (P)	Paranta	30.00	50.00	80.00
<i>Musa paradisiaca</i> (I)	Ibo banana	30.00	49.00	79.00
<i>Musa paradisiaca</i> (O)	Ogede Omini	30.01	48.00	78.01

The measurement of 1% NaOH solubility, cold water and hot water solubility test carried on the different mid-rib banana species (Table 3) showed the potential of biomaterials for the generation of cellulose pulp for pulp and paper, bioenergy development and other industrial application

Table 3
The Analysis of 1% NaOH, Cold Water and Hot Water Solubility Test

Different Species of f Banana Mid-Rib Waste	Common Nigeria Names	Mean 1% NaOH Solubility	Mean % Cold Water Solubility	Mean % Hot Water Solubility
<i>M. paradisiaca</i> (S)	Saro	20.25 ± 1.02	12. ± 0.65	13.80 ± 1.02
<i>M. paradisiaca</i> (P)	Paranta	19.67 ± 1.03	10.66 ± 0.45	12.25 ± 1.03
<i>M. paradisiaca</i> (I)	Ibo banana	18.20 ± 1.05	11.85 ± 0.56	13.08 ± 1.04
<i>M. paradisiaca</i> (O)	Ogede Omini	17.84 ± 1.04	8.05 ± 0.55	10.25 ± 1.04

The mean values of the Fibre Length (FL), Fibre Diameter (FD), Lumen Width (LW) and Cell Wall Thickness (CWT), Runkel Ratio (RR), Flexibility Ratio (FR), Slenderness Ratio (S%) and Coefficient of Rigidity (CoR%) established from the morphological determination of the four banana mid rib species are (table 5) showed high fiber length of 2.86 mm, 2.42 mm, 2.15mm and 1.63 mm from *M. paradisiaca* (P). *M. paradisiaca* (I), *M. paradisiaca* (O), and *M. paradisiaca* (S) respectively and these values compared favorably with the fiber lengths of 1.05 mm–1.36 mm obtained from eighteen different Nigerian wood species. It was also observed that the fiber diameter of range of 19.13 µm to 21.51 µm obtained from the four species of the banana mid rib are higher than 15.22 µm (*M. Excelsa*). The lumen width of 12.52 µm, 11.90 µm, 10.62 µm and 10.05 µm from the corn wastes were better than smallest 8.89 µm was recorded for *M. Excelsa* wood. The average cell wall thickness of 4.76 µm, obtained from this study favours large scale industrial utilization compared that with 2.61 µm to 6.92 µm got from wood species [24]. Other parameters like Runkel, Flexibility, Slenderness ratios and coefficient of rigidity determined from the banana mid rib waste showed that these biomaterials can positively influence the important paper products quality such as the tensile strength, paper sheet formation, tear resistance, and breaking load strain, [25].

Table 4
The Mean Values from Fiber Characterization of different Species of Banana Mid-Rib Waste

Different Banana Mid- Rib Waste	Fiber Length (mm)	Fiber Diameter (µm)	Lumen Width (µm)	Cell Wall Thickness (µm)	Runkel Ratio (RR)	Flexibility Ratio (FR)	Slenderness Ratio (S %):	Coefficient of Rigidity (CoR%):
<i>M. paradisiaca</i> (S)	1.625	19.13	10.021	4.850	1000	24500	0.084	24000
<i>M. paradisiaca</i> (P)	2.864	21.510	12.641	5.216	1100	26000	0.1568	25000
<i>M. paradisiaca</i> (I)	2.425	20.210	11.524	4.932	1000	25033	0.098	24000
<i>M. paradisiaca</i> (O)	2.150	19.744	11.450	4.855	1000	2500	0.0956	24333

The FTIR analysis of different corn biomass waste; corn stalk, corn leaf, corn husk and corn cob indicated in Figs. 1–4 showed observable peaks at 3272.6 cm^{-1} , 2926.0 cm^{-1} , 1736.9 cm^{-1} of hydroxyl, methoxyl, carbonyl functional group confirm the presence of cellulose. The presence of similar peaks on the spectra of cellulose samples from corn stalk and corn cob were observed at $3450 - 3428\text{ cm}^{-1}$ *paradisiaca* (I) and *paradisiaca* (O) are characteristic the hydroxyl group stretching tendency in cellulose molecule while the peaks at wave number of 2915 cm^{-1} to 3000 cm^{-1} shown in *paradisiaca* (I) and *paradisiaca* (S) cellulose spectral correspond to C-H bonds in cellulose. The inter - and intra molecular hydrogen bond vibrations in cellulose were also dictated in the regions of 1686 cm^{-1} - 980 cm^{-1} in the cellulose produced from the mid rib waste [26].

Ibo banana specie

Figure 1: FTIR Analysis of the cellulose from mid-rib M. paradisiaca (I)

Saro banana specie

Figure 2: FTIR Analysis of the cellulose from mid-rib M. paradisiaca (S)

Ogede Omini specie

Figure 3: FTIR Analysis of the cellulose from mid-rib M. paradisiaca (O)

Paranta banana specie

Figure 4: FTIR Analysis of the cellulose from mid-rib M. paradisiaca (P)

The surface morphological characterization of the different four mid rib banana species using SEM (Fig. 5) showed suitable alignment of cellulose fibers and their conformity to pulp and paper development and various bioproduct applications.

Conclusion

This study has demonstrated the huge cellulose potential embedded in the four major species of banana mid rib waste cultivated massively in Nigeria, making them a variable alternative bioresources for the production of cellulose polysaccharides for various industrial application. The morphological and fiber characterization of the mid rib cellulose compared favorably with that of wood cellulose. Hence, the utilization of banana mid rib biomass waste for cellulose extraction will not only provide a sustainable and cheap bioresources for industrial application but will also reduce the environmental pollution from this waste.

Declarations

Conflict of interest

The authors hereby declare that there is no conflict of interest in this research, neither was there any funding received to carry this project.

References

1. Odejobi J, Ajala OO, Osuolale FN (2021) Review on potential of using agricultural, municipal solid and industrial wastes as substrates for biogas production in Nigeria. Springer-Verlag GmbH Germany, part of Springer Nature 2022 Proceedings of the Canadian Society of Civil Engineering Annual Conference (2021)
2. Narayanaperumal S, Suyambulingam I, Avudaiappan S, Ayrilmis N, Divakaran D, Senthamaraikannan P, Selvan A (2026) A Critical Review on Green Conversion Techniques of Biomass Waste to Value-Added Bioproducts: Advances, Challenges, and Future Technological Strategies. GCB Bioenergy 18(5):e70118. <https://doi.org/10.1111/gcbb.70118>
3. Giwa AL, Okoli IC, Obikaonu HO (2025) Valorization of Agricultural Biomass Wastes in Nigeria With Focus on Banana Pseudo-Stem, Empty Palm Bunch and Rice Husk. Asian J Res Rev Agric 7(1):260–275. <https://doi.org/10.56557/ajrra/2025/v7i1176>
4. Thangavelu R, Saraswathi MS, Uma S, Loganathan M, Backiyarani S, Durai P, Raj EE, Marimuthu N, Kannan G, Swennen R (2021) Fusarium wilt resistance in bananas. Sci Rep 11:3183. <https://doi.org/10.1038/s41598-021-82666-y>
5. Hassan HF, Hassan UF, Usher OA, Ibrahim AB (2018) Exploring the potentials of banana peels in feed formulation. Int J Adv Res Chem Sci 5:10–14. <https://doi.org/10.20431/2349-0403.0505003>
6. Nwogu CM, Nwogu RK, Okoli CI (2022) Feed grade ash from empty palm bunch and its effects on layer performance. ASRIC J Agricultural Sci 1:17–25 Available online at. <http://www.asric.org>
7. Obuka NSP, Onyechi PC, Okoli NC (2018) Palm oil biomass waste: A renewable energy resource for power generation. Saudi J Eng Technol 3(12):680–691. <https://doi.org/10.21276/sjeat.2018.3.12.2>
8. FAO (2023) Banana facts and figures. Food and Agricultural Organization, Rome
9. Subagyo A, Chafidz A (2020) Banana pseudo-stem fiber: Preparation, characteristics, and applications. IntechOpen. <https://doi.org/10.5772/intechopen.82204>
10. Arafat KMY, Nayeem J, Quadery AH, Quaiyyum MA, Jahan S, M (2018) Handmade paper from waste banana fibre. Bangladesh J Sci Industrial Res 53(2):83–88
11. Matos E, Silva NE, Lima HJD, Valentim JK, Tossué FJM, Bittencourt TM, Velarde JMD (2019) Banana leaf in the diet of laying hens in cage free system. Acta Scientiarum Anim Sci 41:e46908
12. Thiet G, Binh PV, Nhan NTH, Ngu NT (2022) Using banana leaf and pseudo-stem (*Musa spp.*) silage substituted rice bran in the diet of growing wild crossbred boar. *Livestock Research for Rural Development*, 34(7). Retrieved from <http://www.lrrd.org/lrrd34/7/3458nthi.html>
13. Rattanapan C, Ounsaneha W (2022) Value-added banana production waste under circular economy concept. *International Journal of Environmental Science*, 13, 92–96. *OLAWORE ; S. Asian Res. J. Nat. Prod.*, vol. 9, no. 1, pp. 147–158, 2026; Article no.SARJNP.152601 158; <https://doi.org/10.18178/ijesd.2022.13.3.1377>
14. Hatzikiseyan A (2017) Principles of bioremediation processes. *Trends in Bioremediation and Phytoremediation*
15. Mahlangu JM, Simate GS, de Beer M (2018) Adsorption of Mn²⁺ from acid mine drainage using banana peels. Int J Water Wastewater Treat 4(1). <https://doi.org/10.16966/2381-5299.153>
16. Khairiah K, Frida E, Sebayang K, Sinuhaji P, Humaidi S (2021) Data on characterization, model, and adsorption rate of banana peel activated carbon (*Musa acuminata*) for adsorbents of various heavy metals (Mn, Pb, Zn, Fe). Data Brief 39:107611. <https://doi.org/10.1016/j.dib.2021.107611>
17. Ndukwe NA, Okiei WO, Jenmi JO, Alo BI (2009) Comparative Study of Percentage Yield of Pulp from various Nigerian Wood Species using the Kraft Process. African Journal of Environmental Science and Technology, 3 (1), 21–25 (2009). <http://www.academicjournals.org/AJest> ISSN 1996 – 0786. USA

18. TAPPI (1988) Solvent Extractives of Wood and Pulp. T 204 om-88 Standard Methods of the Technical Association of the Pulp and Paper Industry, New York, USA
19. Ndukwe NA, Okiei WO, Jenmi JO, Alo BI (2012) The Correlates of the Yield of Chemical Pulp, the Lignin Content and the Extractive Materials of Tropical Hardwoods. *African Journal of Agricultural Research*, 7 (40), 5518–5524 (2012). <http://www.academicjournals.org/AJAR> 10.5897/AJAR12.1136 ISSN 1991-637X
20. Rabemanolontsoa H, Saka S (2012) Holocellulose Determination in Biomass. Zero-Carbon Energy Kyoto 2011. Springer, Tokyo. (Modified Procedure)
21. American Society for Testing and Materials ASTM (2020) Standard Test Methods for Evaluating Properties of Wood-Based Fibre and Particle Panel Materials. ASTM D103712, West Conshohocken. PA.
22. American Society for Testing and Materials, ASTM D1413-61- (2007) Preparation of decayed wood for microscopical examination. ASTM International, West Conshohocken, PA
23. Małachowska E, Dubowik M, Boruszewski P, Przybysz P (2021) Accelerated ageing of paper: effect of lignin content and humidity on tensile properties. *Herit Sci* 9(1):1–8
24. Sadiku NA, N. A., Micheal CM (2022) Fibre Sourcing for The Nigerian Pulp Mills: Evaluation of Suitability Indices of Selected Nigerian Rainforest Wood Fibres. *Indonesian Journal of Forestry Research* Vol. 9 No. 2, 135–146. (2022), ISSN: 2355–7079/E-ISSN: 2406–8195
25. Fatriani, Banjarbaru (2017) Fiber dimension and derivatives value of sugar palm frond in various positions. *Agric Forestry Fisheries* 6(2):66–68. doi://10.11648/j. aff.20170602.13
26. Feng X, Jianming Y, Tesso. T, Dowell F, Wang D (2013) Qualitative and quantitative analysis of lignocellulosic biomass using infrared techniques: A mini-review. *Appl Energy* 104:801–809. <https://doi.org/10.1016/j.apenergy.2012.12.019>

Figures

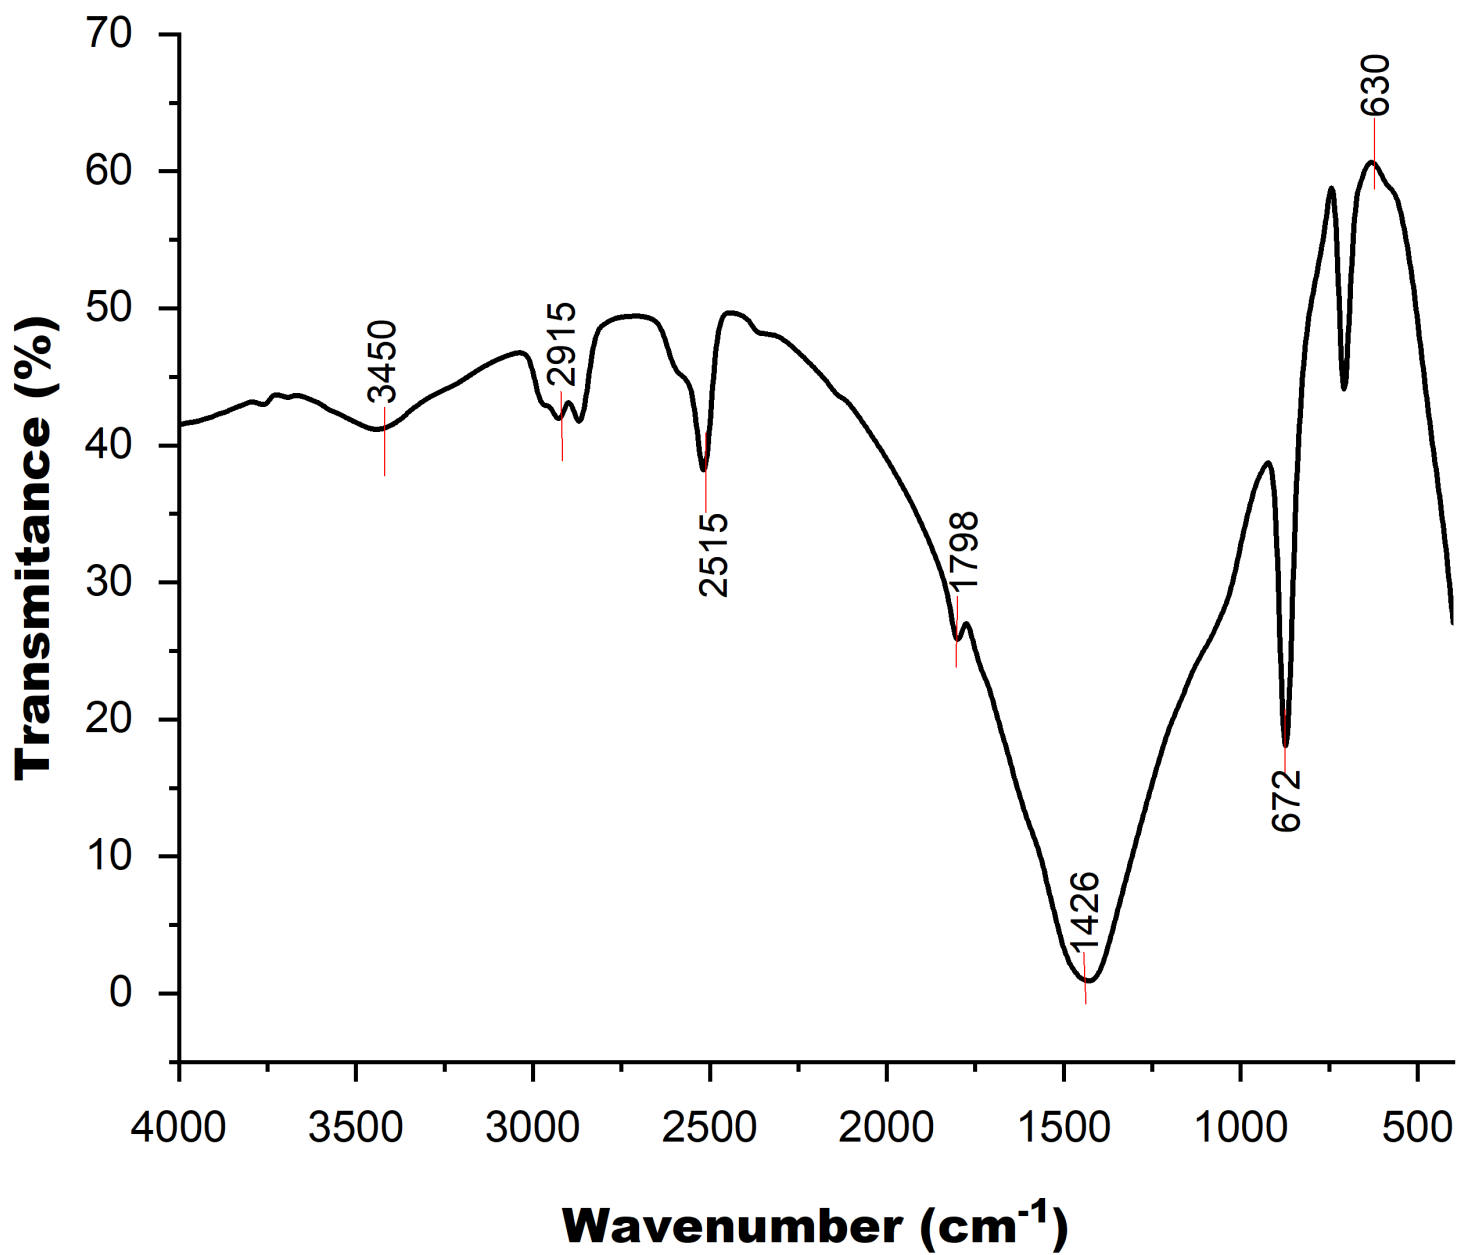


Figure 1

FTIR Analysis of the cellulose from mid-rib *M. paradisiaca* (I)

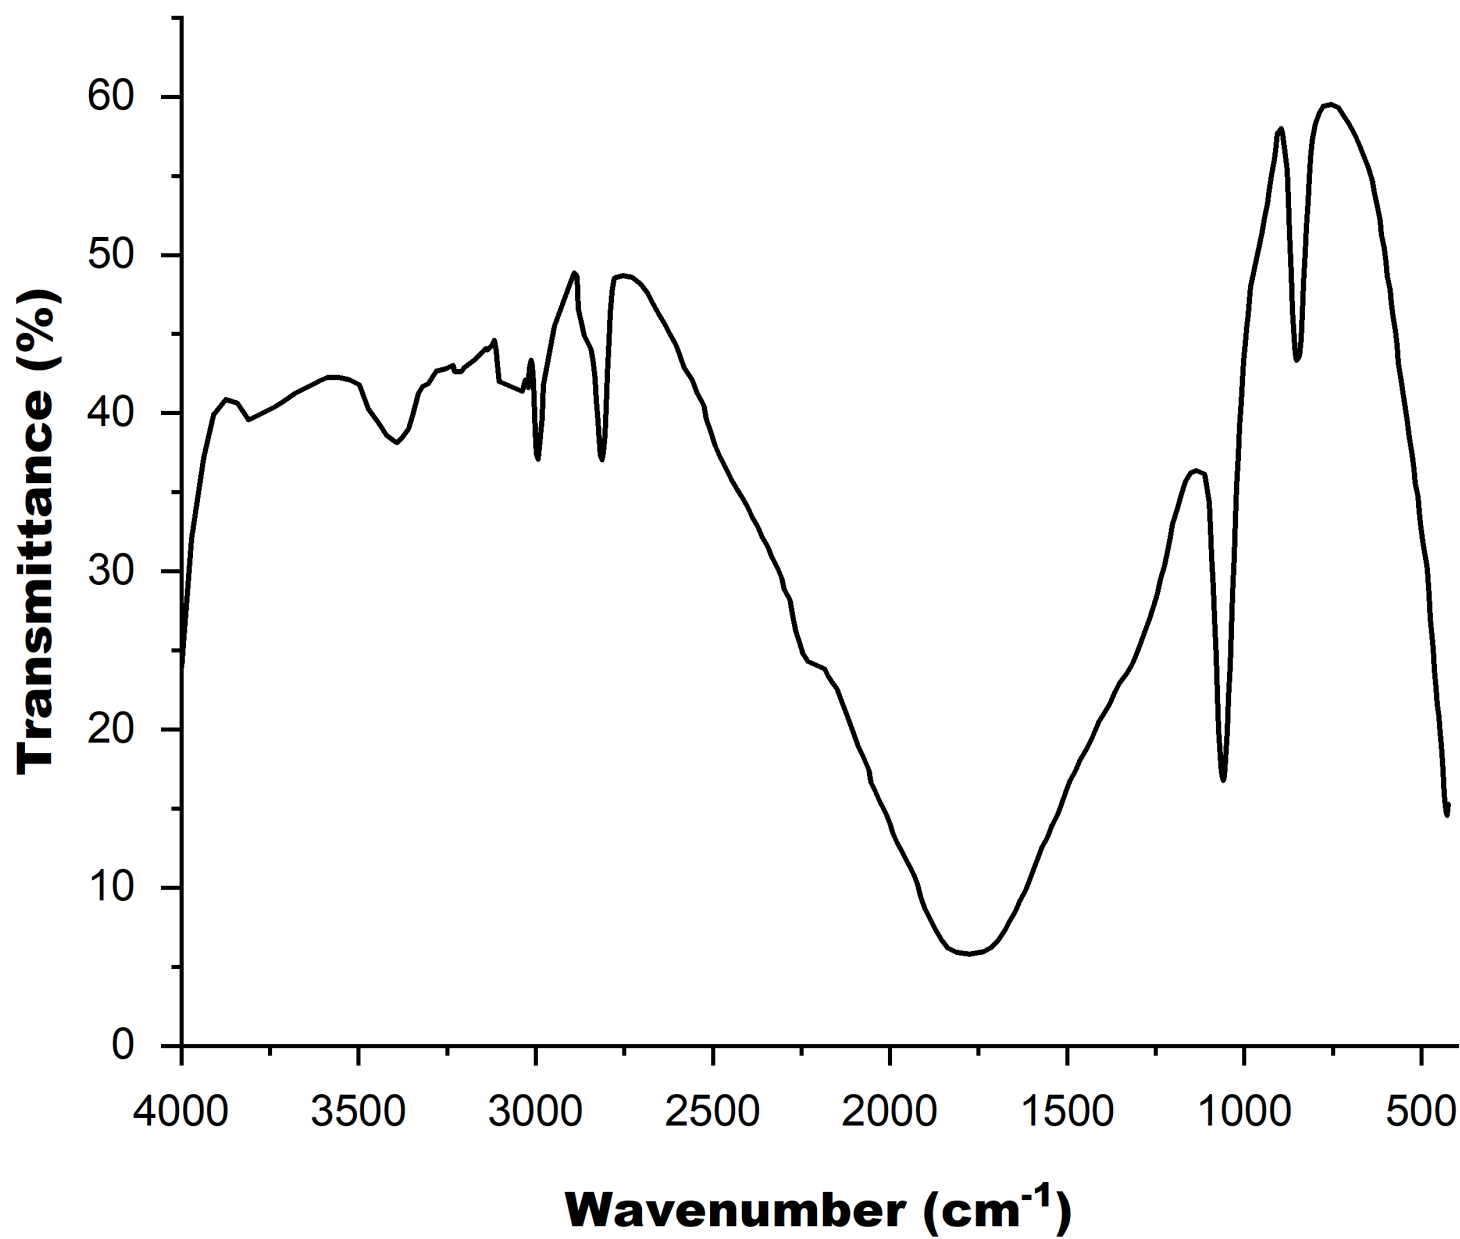


Figure 2

FTIR Analysis of the cellulose from mid-rib *M. paradisiaca* (S)

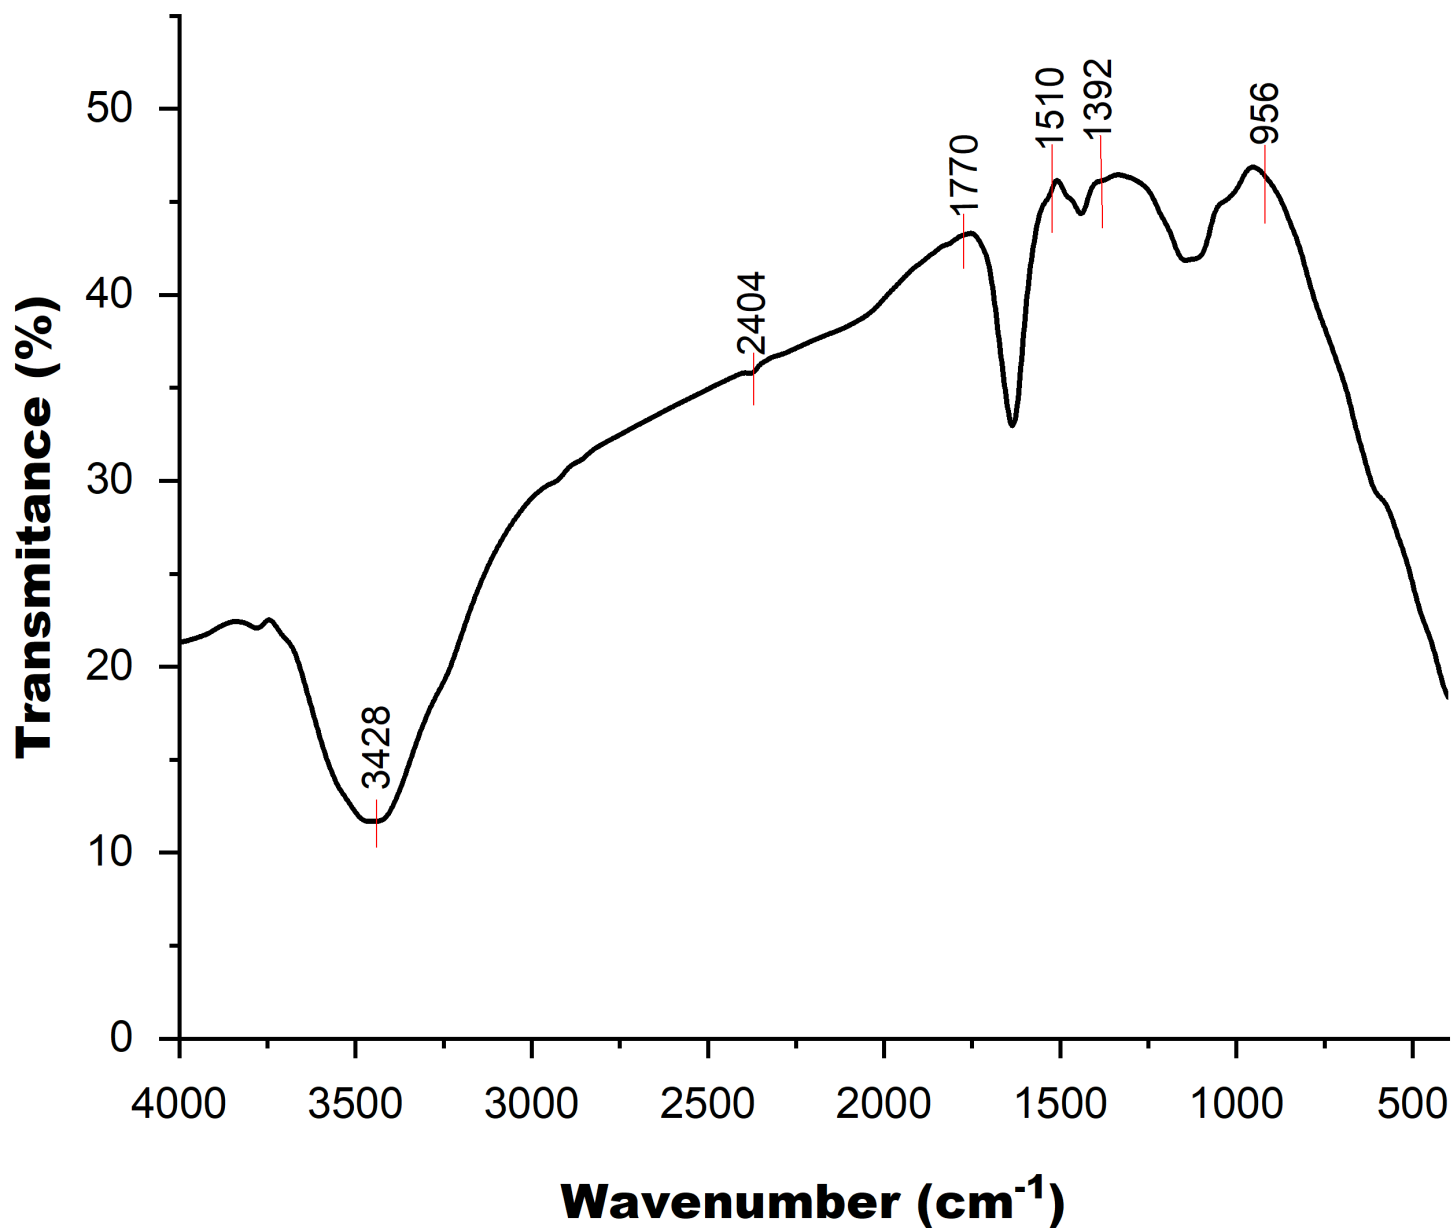


Figure 3

FTIR Analysis of the cellulose from mid-rib *M. paradisiaca* (O)

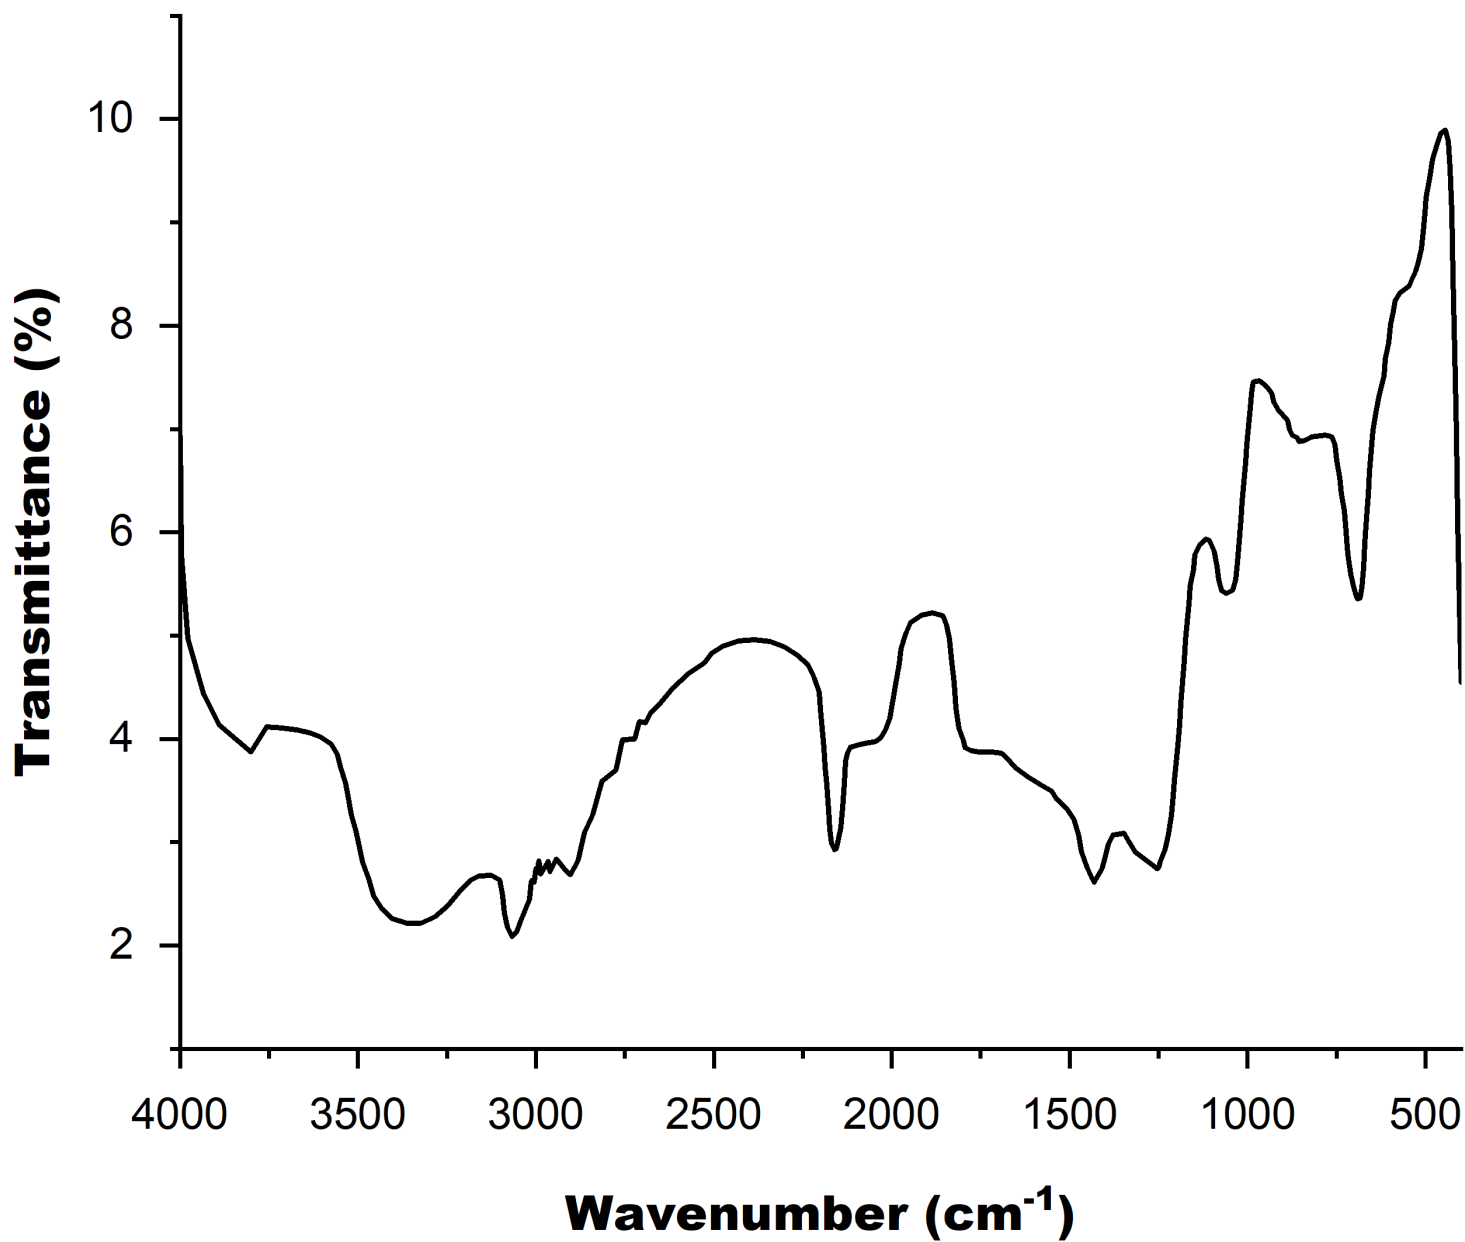


Figure 4

FTIR Analysis of the cellulose from mid-rib *M. paradisiaca* (P)

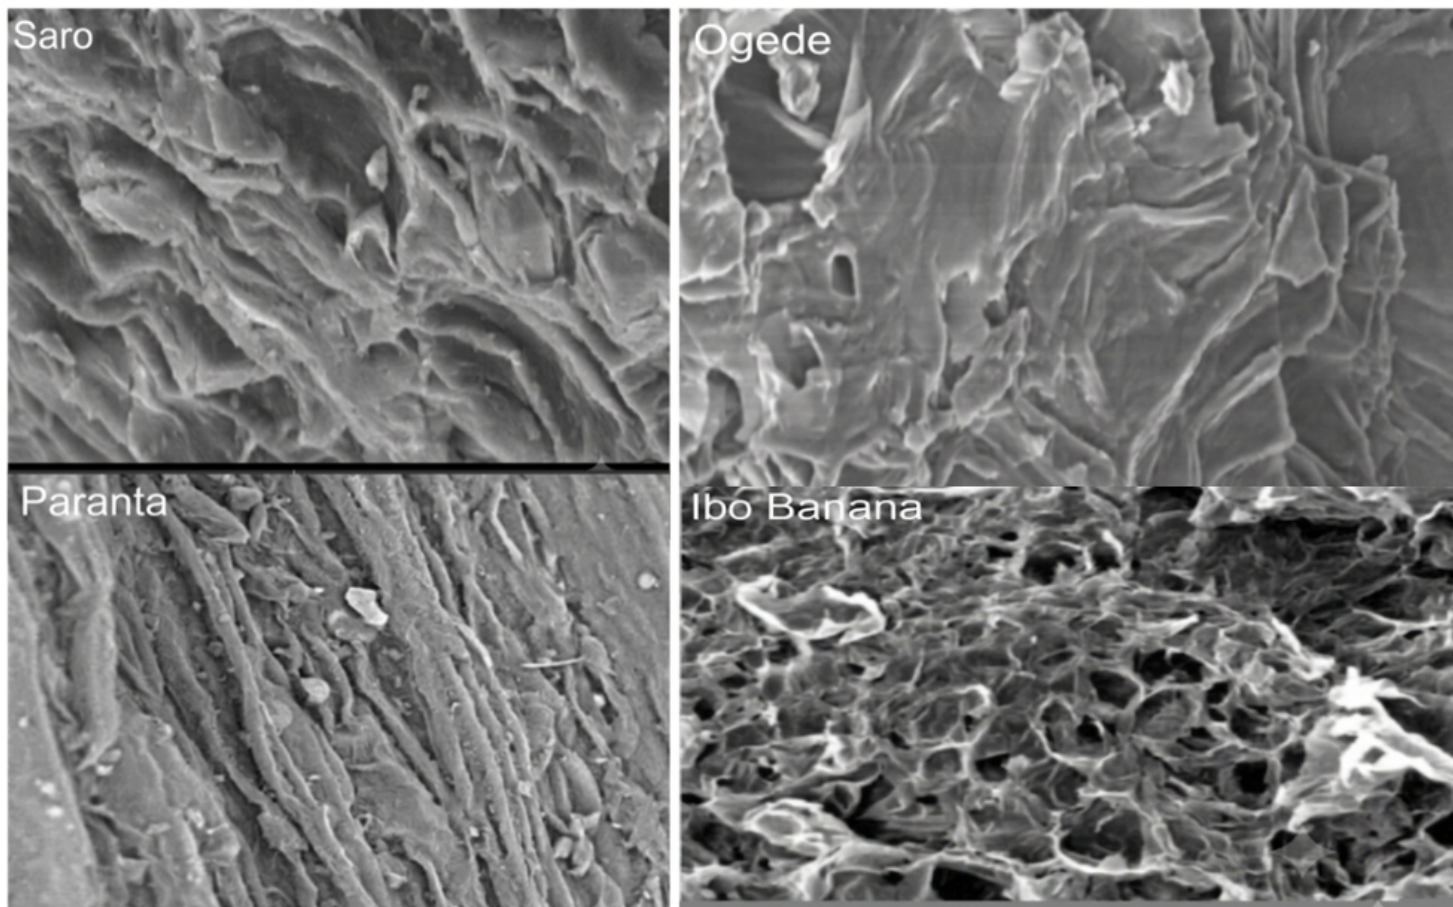


Figure 5

Surface morphology of the cellulose from the four different banana mid rib wastes at 10,000 magnifications, Hv of 20 Kv, HFW of 130 μ m and pressure of 70 Pa.