



Facile preparation of cobalt-oxide nanostructures with enriched cobalt(ii) ion surface using Solanum melongena for energy application

Abdul Jaleel Laghari, Umair Aftab, Muhammad Ishaque Abro, Aneela Tahira, Elmuez Dawi, Muhammad Ali Bhatti, Antonia Infantes-Molina, Melanie Emo, Brigitte Vigolo, Rafat Ibrahim, et al.

► To cite this version:

Abdul Jaleel Laghari, Umair Aftab, Muhammad Ishaque Abro, Aneela Tahira, Elmuez Dawi, et al.. Facile preparation of cobalt-oxide nanostructures with enriched cobalt(ii) ion surface using Solanum melongena for energy application. RSC Advances, In press, 15 (38), pp.31107-31121. <10.1039/D5RA02960K>. <hal-05241630>

HAL Id: hal-05241630

<https://hal.science/hal-05241630v1>

Submitted on 8 Dec 2025

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



HAL Authorization

Facile preparation of cobalt-oxide nanostructures with enrich Cobalt(II) ion surface using solanum-melongena for energy application

Abdul Jaleel Laghari^a, Umair Aftab^a, Muhammad Ishaque Abro^a, Aneela Tahira^f, Elmuez Dawi^g, Muhammad Ali Bhatti^e, Antonia Infantes-Molina^d, Melanie Emo^c, Brigitte Vigolo^c, Rafat M. Ibrahim^h, Zafar Hussain Ibupoto^b

^aDepartment of Metallurgy and Materials, Mehran University of Engineering and Technology, 76080 Jamshoro, Sindh, Pakistan.

^bInstitute of Chemistry, University of Sindh Jamshoro, 76080, Sindh, Pakistan.

^cUniversité de Lorraine, CNRS, IJL, F-54000 Nancy, France.

^dDepartment of Inorganic Chemistry, Crystallography and Mineralogy, Unidad Asociada al ICP-CSIC, Faculty of Sciences, University of Malaga, Campus de Teatinos, 29071, Malaga, Spain.

^eCentre for Environmental Sciences, University of Sindh Jamshoro, 76080, Sindh, Pakistan.

^fInstitute of Chemistry, Shah Abdul Latif University Khairpur Mirs, Sindh, Pakistan.

^gCollege of Humanities and Sciences, department of Mathematics and Sciences, Ajman University, P.O.Box 346, Ajman, United Arab Emirates.

^hPhysics Department, Faculty of Science, Taibah University, Al-Madaina Al Munawarah 42353, Saudi Arabia.

*Corresponding author(s):

Zafar Hussain Ibupoto, PhD, Email : zaffar.ibhupoto@usindh.edu.pk;

Muhammad Ishaque Abro, PhD, Email: ishaque.abro@faculty.muet.edu.pk

Abstract


The increasing demand for efficient energy conversion and storage systems necessitates the development of high-performance, cost-effective electrode materials. To address this challenge, we employed rotten Solanum melongena (eggplant) juice as a precursor for the fabrication of low-cost, earth-abundant, and active electrode materials based on cobalt oxide (Co₃O₄) nanostructures. Different volumes of rotten Solanum melongena juice (5 mL, 10 mL, 15 mL, and 20 mL) were utilized during the precipitation process to synthesize Co₃O₄ nanostructures. These nanostructures were characterized in terms of crystal quality, surface morphology, surface chemical composition, and electrochemical properties. Notably, the synthesis using 15 mL of rotten Solanum melongena juice resulted in a highly efficient electrode material for oxygen evolution reaction (OER) in 1 M KOH electrolytic solution, with an overpotential of 276 mV at 10 mA cm⁻². In addition to its electrocatalytic properties,

the Co_3O_4 electrode material was evaluated for supercapacitor applications, demonstrating a specific capacitance of 1303.13 F/g, an energy density of 28.96 Wh/kg at 1.25 A/g, and a 97% specific capacitance retention over 30,000 galvanic charge-discharge cycles.

Keywords: Co_3O_4 nanostructures, solanum melongena juice, oxygen evolution reaction, supercapacitor.

Graphical abstract

The solanum melongena juice shows the contributing role towards enhanced electrochemical performance of Co_3O_4 nanostructures during supercapacitor and OER applications.

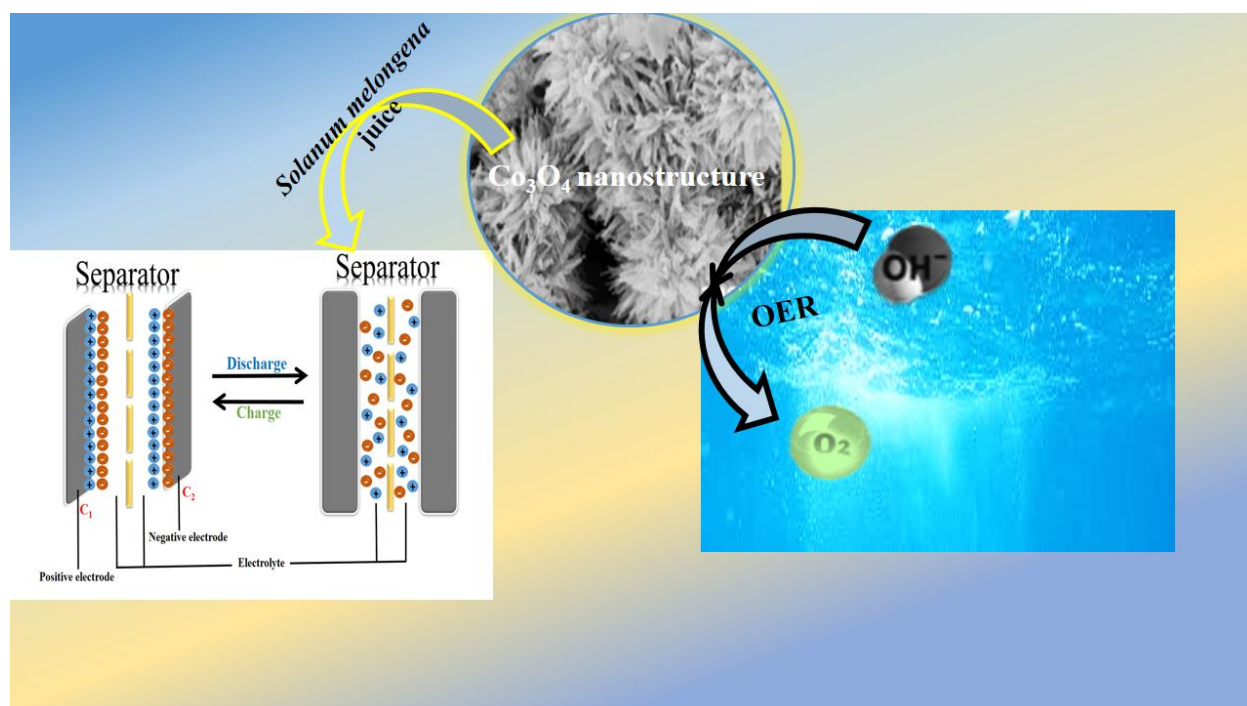

1. Introduction

A considerable amount of attention has been focused on renewable energy generation and energy storage to fulfill the global energy demand in the most efficient manner [1-9]. The current global situation is more concentrated on the remedy of environmental pollution and exhaustive aspects of fossil fuels; therefore it has been deeply realised to fabricate the sustainable energy conversion and storage systems to mitigate the energy shortage [1, 3, 6]. The supercapacitors are making the energy storage devices and have received a lot of focus in recent times [6]. The supercapacitors have been associated with high power density, long cycling operational time, and swift charge-discharge capacity compared to Li-ion batteries [6]. But the supercapacitors suffer from poor energy density, which is the main barrier to their

practical use. The electrocatalytic water splitting is one of the potential energy conversion systems and has been known as an efficient technology to develop a sustainable hydrogen generation source [7, 8]. The oxygen evolution reaction (OER) has a great impact on the performance of electrocatalytic water splitting; however, OER exhibits slow kinetics, thus resulting in large overpotentials [9]. The slow kinetics and high energy barrier of OER strongly limit the practical use of electrocatalytic water splitting for the efficient hydrogen generation [9].

Properties like high catalytic activity, better electrical conductivity, sufficient surface area and porosity, good stability/Durability and superior specific capacitance are required for the electrode material to perform well for water splitting and supercapacitor application [10-18]. Transition metals such as nickel, iron, zinc, and cobalt based oxides are highly promising and potential substitutes for the noble metal-based electrocatalysts in electrochemical water splitting and supercapacitor application [19-22]. Compared to CoO and Co₂O₃, Co₃O₄ is the most stable phase of cobalt oxide [23-24]. The Co₃O₄ based materials have been synthesized by variety of potential methods such as combustion process [25], hydrothermal [26], Pechiney [27], co-precipitation [28], green approach [29], electrospinning method [30], solvothermal [31], and sol gel process [32]. Green preparation of Co₃O₄ has demonstrated promising results in terms of influencing its surface properties, morphology, and stoichiometric variation. As a result, the electrochemical performance of Co₃O₄ is improved [33,34]. By utilizing green synthesis, a variety of natural reducing, capping, and stabilizing agents can be utilized to enhance the surface-active sites, charge transport, highly compatible surfaces, tunable electron transport pathways, and the stability of materials against harsh electrolytes [35,36]. Thus, different plant extracts have been used to synthesize a wide range of metal oxides nanostructures (ZnO, Fe₂O₃, AgO, CuO, Al₂O₃ etc) [37]. Previously, moringa oleifera extract was used to synthesize Co₃O₄, and the results were highly promising in the development of electrode materials for supercapacitors [38]. As a template, solanum tuberosum leaf extract was also used to prepare Co₃O₄ nanostructures, and the electrochemical and antibacterial properties of Co₃O₄ have been greatly enhanced as a result [39]. It has been discovered that several natural organic compounds act as catalysts during oxidation and reduction reactions as well as accelerating electron transport during oxidation of water [40]. The solanum melongena plant contains a variety of phenolic compounds and anthocyanins that possess reducing and oxidizing properties [41, 42]. To enhance the electrochemical performance of Co₃O₄ nanostructures, the hypothesis presented here

proposes that rotten solanum melongena extract can be used to tailor the sizes, shapes, and chemical compositions of the nanostructures. This could be possible through the exploitation of different phytochemicals of the solanum melongena extract owing to their reducing, capping, stabilizing, and structure-directing agent properties. These characteristics of solanum melongena extract during the synthesis of Co_3O_4 have not been investigated in the past; hence, this is the first kind of study. Therefore, the Co_3O_4 based material could be incorporated into the development of high-performance electrode materials for energy conversion and storage through the combined effect of various phytochemicals in solanum melongena. As a result of the variable properties of cobalt-based materials, OER half-cell water splitting may be enabled at a low overpotential due to the use of rotten solanum melongena juice. In light of these circumstances, the present study was carried out to synthesize Co_3O_4 based materials using different amounts of solanum melongena juice, and it has been successfully applied to the development of an electrode material for use in OER and supercapacitors.

2. Materials and Methods

2.1 Used chemicals

Cobalt chloride ($\text{CoCl}_2 \cdot 6\text{H}_2\text{O}$), urea ($\text{CH}_4\text{N}_2\text{O}$), 85% potassium hydroxide, silicon paper, alumina (Al_2O_3) 0.03 μm slurry, nickel foam, and 20% ethanol ($\text{C}_2\text{H}_5\text{OH}$) were purchased from Sigma Aldrich in Karachi Sindh Pakistan. The electrolyte solution and growth of materials were prepared using deionized water. The vegetable, solanum melongena, was purchased from a local market in Jamshoro, Sindh.

2.2 Green mediate preparation of Co_3O_4 based materials using rotten solanum melongena juice during precipitation method

A rotten solanum melongena sample was collected from a local market in Jamshoro and washed several times with deionized water prior to being used to synthesize the Co_3O_4 nanostructure. To prepare the juice, rotten solanum melongena (250gm) was put into the domestic juicer machine and filtered using filter paper. We collected approximately 150 mL of solanum melongena juice and stored it at 4°C in a refrigerator. Afterwards, Co_3O_4 nanostructures were prepared using the precipitation method with and without rotten solanum melongena juice. A variety of quantities of solanum melongena juice were used in order to better understand the effects of rotten solanum melongena juice on the structure and

functionality of Co_3O_4 . As a natural source of reducing, capping, and stabilizing agents, the juice of rotten solanum melongenas can result in variation in shape orientation, stoichiometric composition, and size of Co_3O_4 nanostructures. In a typical preparation, 250 mL of deionized water contains 0.1 M cobalt chloride hexahydrate (5.92 gm) and 0.1 M urea (1.5 gm). Five growth solutions were prepared, four of which contained rotten solanum melongena juice in amounts of 5 mL, 10 mL, 15 mL and 20 mL, as well as 0.1 M cobalt chloride hexahydrate (5.92 gm) and 0.1 M urea (1.5 gm). In addition, the fifth growth solution was prepared without rotten solanum melongena juice and contained only 0.1 M cobalt chloride hexahydrate and 0.1 M urea, as well as a label indicating that it was pure cobalt oxide. In the following steps, five beakers containing growth solutions were covered with aluminum sheets and placed in an electric oven preheated to 95 °C for five hours. After collecting the cobalt hydroxide product, it was washed several times with ethanol and deionized water, and then dried overnight at 60 °C. Following this, the product was thermally annealed for three hours at 500 °C. The heating rate of the furnace was 80C/min in the presence of an air atmosphere. Therefore, Co_3O_4 nanostructures obtained with and without rotten solanum melongena juice were characterized structurally and electrochemically. Co_3O_4 samples prepared from solanum melongena juice are referred to as cobalt oxide-solanum melongenas (CE) in the manuscript. Supplementary Scheme 1 illustrates the synthesis and interaction with the heterostructures.

2.3. The structure and compositional studies of green mediated Co_3O_4 nanostructure

The morphology of Co_3O_4 nanostructures was investigated through scanning electron microscopy (SEM) using a JEOL JSM-6480A operating at 20 kV. Additional structural analyses were conducted via transmission electron microscopy (TEM) and high-resolution transmission electron microscopy (HRTEM) using a JEOL JEM-ARM 200F Cold FEG microscope, operating at 200 kV and equipped with a probe corrector (Cs). X-ray diffraction (XRD) patterns, obtained using a Philips PANalytical diffractometer with $\text{CuK}\alpha$ radiation ($\lambda = 1.5418 \text{ \AA}$) at 45 kV and 45 mA, were analyzed via HighScore Plus software to assess purity and crystallinity [42]. Chemical states and surface composition were examined through X-ray photoelectron spectroscopy (XPS) using a monochromatic Al $\text{K}\alpha$ source (1486 eV) under ultra-high vacuum (10^{-10} mbar), with results analyzed at a resolution of 0.651 eV on the 7/2 line of full width at half maximum. Atomic structure was further analyzed using a JEOL JEM ARM 200F Cold FEG microscope equipped with spherical aberration (Cs). A phytochemical analysis of Solanum melongena juice was conducted at the University of Sindh, Jamshoro, employing various tests, including iodine, alkaloids, Molisch, Fehling's, Benedict's,

Barfoed's, Dragendorff's, Mayer's, Hager's, Wagner's, and tannic acid tests. Fourier-transform infrared (FTIR) spectroscopy was performed using a PerkinElmer Spectrum Two instrument across the range of 4000 to 400 cm^{-1} .

2.4 The fabrication of green mediated Co_3O_4 nanostructures-based electrode material for the energy conversion and storage applications

All electrochemical tests for OER characterization were conducted using a VERSASTAT 4-500 analytical potentiostat with various electrochemical modes, including linear sweep voltammetry (LSV), cyclic voltammetry (CV), electrochemical impedance spectroscopy (EIS), and chronopotentiometry in 1.0 M KOH aqueous solution. An electrochemical cell system with three electrodes was employed. A silver-silver chloride electrode (Ag/AgCl) filled with 3 M potassium chloride (KCl) electrolyte served as the reference electrode, a glassy carbon electrode (GCE) as the working electrode, and a graphite rod as the counter electrode. The catalytic material ink was prepared by mixing 10 mg of each Co_3O_4 nanostructure sample with 5 mL of deionized water and 0.3 mL of Nafion (5%) as a binder. The GCE had a diameter of approximately 3 mm (area: 0.071 cm^2). Catalyst ink (5 μL , loading mass: 0.02 mg) was sprayed onto the GCE and dried by blowing air. CV and LSV tests were conducted on 1 M KOH electrolyte to characterize the OER. Prior to LSV, CV was used at a scan rate of 10 mV/s to stabilize the electrode. The reference electrode experimental potential was converted to the reversible hydrogen electrode potential using the Nernst equation. Electrochemical impedance spectroscopy (EIS) was utilized to measure charge transfer resistance under conditions of 100 kHz to 0.1 Hz, with sinusoidal potentials of 5 mV and 1.4 V vs. RHE as OER onset potentials.

Z-view software was used to simulate the EIS data to determine the appropriate electric circuit for accurate estimation of charge transfer resistance. A durability experiment was then conducted at current densities of 20 and 40 mA/cm^2 for 15 and 30 hours, respectively. To calculate the electrochemical active surface area (ECSA), CV curves were measured at various scan rates in the non-Faradic region. For the conversion of experimental potentials measured against Ag/AgCl and the calculation of Tafel slopes, the following mathematical relations were applied.

$$E_{\text{RHE}} = E_{\text{Ag/AgCl}} + 0.059\text{pH} + E^{\circ}_{\text{Ag/AgCl}} \quad (1)$$

Whereas, $E^{\circ}_{\text{Ag/AgCl}}$ is 0.2412

$$\text{Overpotential } (\eta) = \text{Onset potential } (E_{RHE})_{(V)} - 1.23_{(V)} \quad (2)$$

Tafel equation was applied to LSV curves for the calculation of Tafel Slopes.

$$\eta = b \log j + a \quad (3)$$

Herein, b is Tafel slope, η overpotential and j is current density.

An electrode material based on Co_3O_4 nanostructure was also studied for electrochemical supercapacitor applications by dip coating Co_3O_4 nanostructure on nickel foam. The purpose of using nickel as an electrode substrate was to deposit electrode materials due to its high surface area and the possibility of depositing large amounts of material. A nickel foam sample measuring 2 cm^2 was dipped into Co_3O_4 ink that contained 5% Nafion as a binder, dried for five minutes, and then repeated several times. Material adhesion was enhanced by sintering at 65°C for one hour at low temperature. It was found that around 2 mg of electrode material was loaded onto the nickel foam. A Co_3O_4 nanostructure was deposited on nickel foam and used as a working electrode, a graphite rod as a counter electrode and (Ag/AgCl, filled with 3MKCl) as a counter electrode and a reference electrode. To characterize Co_3O_4 nanostructures prepared in 3.0M KOH, galvanostatic charge-discharge (GCD) and cyclic voltammetry (CV) were used. The concentration of 3.0 M KOH was chosen due to the fact that high amounts of hydroxide ions can be adsorption onto the electrode material in order to demonstrate the capacity of the material to store charge efficiently. Using repeatable GCD cycles, the percent specific capacitance retention and columbic efficiency of electrode materials were calculated for 30000 cycles to ensure durability and cyclic stability [43]. The formulae for specific capacitance retention and columbic efficiency are given in eq. S1 and eq. S2.

Results and discussion

3.1 Morphology, crystal quality and chemical composition characterization of as prepared Co_3O_4 materials

Using XRD analysis, we determined the phase and purity of pure Co_3O_4 and Co_3O_4 samples prepared with rotten Solanum melongena juice. Figure 1 illustrates the measured reflections of each sample. The diffraction peaks were observed to be located at two-theta angles starting at 31.40° , 37.02° , 38.80° , 44.95° , 55.61° , 59.46° , 65.32° , 77.21° , and 79.11° , and were

labeled as corresponding diffraction patterns (220), (311), (222), (422), (511), (440), (322), and (622). The measured diffraction patterns correspond to a cubic phase of Co_3O_4 nanostructure, according to the standard JCPDS (card no: 01-078-1970).

Using rotten *Solanum melongena* juice provided redox compounds that affected the relative intensity of Co_3O_4 peaks, resulting in slight differences between peak intensities using 5 mL (EC-5), 10 mL (EC-10), 15 mL (EC-15), and 20 mL (EC-20). According to the XRD analysis, the *Solanum melongena*-mediated preparation of Co_3O_4 was successful in the presence of *Solanum melongena* juice. *Solanum melongena* juice did not alter the Co_3O_4 phase, even at high concentrations, as compared to the synthesis process occurring without *Solanum melongena* juice (pristine Co_3O_4).

The magnified image (Figure 1) of the (311) and (400) planes reveal that the peak shifts to the left side as a result of the compressing effect induced by the phytochemicals in *Solanum melongena* juice. With increasing amounts of *Solanum melongena* juice, the intensity of the peaks decreased, indicating a decrease in the crystallinity of Co_3O_4 . The samples were found to be extremely pure and did not contain any other impurities. Information extracted from the XRD data is provided in Supplementary Table (S1), further confirms that the crystallinity index decreases while d-spacing and lattice parameter are increases by the addition of rotten *Solanum melongena* during synthesis. Table 1 lists the phytochemicals identified during the phytochemical analysis. These components of *Solanum melongena* juice play a dynamic role in affecting the structural, size, and surface properties of Co_3O_4 nanostructures. Phytochemical analysis revealed that phenolic compounds, alkaloids, tannins, and flavonoids can act as capping, reducing, stabilizing, and surface-modifying agents.

Table 1: Phytochemical analysis of rotten *solanum melongena* juice.

Flavonols	Flavones	Flavonoids	Phenolic acid	Alkaloids
+	+	+	+	+
Tannins	Saponins	Reducing sugar	Non-Reducing sugar	Ascorbic acid
+	+	+	+	+

+ Present

The method used for the phytochemical analysis is given in the supplementary section.

Figure 2 depicts typical SEM images of pure Co_3O_4 and Co_3O_4 nanostructures mediated by *solanum melongena* at different magnifications. The Co_3O_4 is typically arranged in an

elongated rod-like morphology composed of assembled nanoparticles glued together, with a length of a few microns and a diameter of 10-150 nm (Figures 2a and 2b). It has been observed that in all cases where solanum melongena juice is used in the interim, Co_3O_4 nanostructures mediated by solanum melongena appear as urchin-like structures with needles no larger than 10 nanometers in diameter. According to (Figure 2c-2j), these nanostructures will exhibit a superior surface compared to the thick pure Co_3O_4 material, which has a thin surface due to the self-assembling of nanoparticles into defected nanorods. When the rotten solanum melongena juice amount was increased from 5 mL, 10 mL, 15 mL during the synthesis process, an effect without a rigorous tendency was observed (Figures 2c and 2d, 2e and 2f, and 2g and 2h). It appears that the size of the urchins decreases from 500 nm⁻¹ nm for 5 mL and 10 mL to a majority of urchins falling below 300-500 nm for Co_3O_4 prepared with 15 mL of rotten solanum melongena juice. Additionally, some isolated particles are dispersed within the urchins. In the case of the highest quantity of solanum melongena juice, 20 mL, well-defined nanostructures became less difficult to detect and aggregated into a denser structure of solanum melongena juice, with variable surface morphology. As shown in Figure 2, the largest amount of rotten solanum melongena juice (Figures 2i and 2j) has completely changed its morphology into nanosheets decorated with nanoparticles.

As can be seen in Figure 2, 5 mL, 10 mL, and 15 mL of rotten solanum melongena juice summarized the thin nanorod into a flower shape. The transformation of morphology may be related to the use of phytochemicals from the juice of *Solanum melongena* during the growth process. Since phytochemicals, particularly phenolic compounds, have reducing properties and possess hydroxyl terminated groups in cyclic rings. The two aspects of solanum melongena juice phytochemicals influenced the reaction growth rate, resulting in a change in shape orientation from a rod to an urchin. *Solanum melongena* juice contains a wide range of phytochemicals with redox properties and also reducing properties for the surface modification of nanomaterials, in terms of size and shape variation. We propose that phytochemicals, particularly phenolic substances and reducing sugars, may play a role during the growth process by interfering with the Co ions by changing the growth kinetics and nucleation rate. According to the SEM studies shown in Figure 2, the overall morphology and size of nanostructures were significantly altered. In connection with the XRD studies, it has been shown that the two theta angle was slightly changed, which may have been as a consequence of phytochemicals altering the nucleation rate for crystal growth during synthesis. As shown in Figure 1, this shift in two-theta angle was observed.

SEM analysis revealed that solanum melongena juice's oxidation and reductive compounds were the main mediators and responsible for tuning the morphology of Co_3O_4 nanostructures. As a result of its ability to tailor surface and electron communication, solanum melongena juice could play a significant role in the final application of Co_3O_4 nanostructures [38,39].

TEM/HRTEM observations were conducted on the sample of Co_3O_4 prepared with 15 mL of rotten solanum melongena juice. Figure 3 provides a summary of the results. It was observed by SEM that the sample prepared with solanum melongena juice contained aggregated particles of various shapes, including small nanorods (Figure 3a) or small angular nanoparticles (Figure 3b), which are primarily of a few tens of nanometers in diameter within the 10-nanometer range for both nanorods and nanoparticles. As demonstrated by XRD measurements (Figure 1), HRTEM micrographs (Figures 3c-3d) using Fast Fourier Transform (FFT) (Figure 3e) reveal polycrystallinity. The d-spacing of 0.47 nm between adjacent lattices corresponds to the lattice distance of (111) crystal planes of Co_3O_4 phase and the FFT patterns corresponding to the lattice plane of Co_3O_4 (111), (220), (311), (400) are clearly identified in Figure 3e, confirming the cubic phase structure $\text{Fd-}3\text{m}$ of the Co_3O_4 sample prepared with 15 mL of rotten solanum melongena juice.

A study of the surface chemical composition was conducted by XPS and the measured spectra are shown in Figure 4. In Figure 4, Lorentzian-Gaussian functions fitting models were used to obtain high resolution XPS spectra for Co 2p and O 1s. Figure 4a shows the fitted Co 2p spectra for pure Co_3O_4 and 15 mL rotten solanum melongena juice mediated Co_3O_4 , which demonstrate distinctive satellite shake up peaks due to Co (III) and Co (II). The relative % of these variable oxidation states were calculated using the corresponding $\text{Co}^{3+}/\text{Co}^{2+}$ ratio that was 2.8 and 1.4 for pure and solanum melongena samples respectively, which indicates a higher amount of Co (II) species on the surface of solanum melongena plant juice mediated Co_3O_4 . By enriching surface oxygen vacancies, Co (II) species have been shown to be highly active for OER [43-45]. Solanum melongena has been found to produce a wide range of phytochemicals, which have been shown to enhance the presence of Co(II) species on its surface, and the higher the Co(II) content on the surface of cobalt oxide, the greater the oxygen vacancies, thus enhancing the activity of the OER [46]. High resolution O 1s spectra of pure Co_3O_4 and solanum melongena mediated Co_3O_4 were also fitted for the illustration of surface defects contributed by the presence of oxygen vacancies

as shown in Figure 4b. Three main attributions of oxygen were noticed in the O 1s spectra for the metal-oxygen bonds (O1, 529.6 eV), defective positions with oxygen vacancies (O2, 531.3 eV) and adsorbed water or organic substances (O3, 532.9 eV) [43-46]

The relative % of each oxygen contribution was found in the order O1>O2>O3 for pure sample and O1≈O2> O3 for solanum melongena mediated sample and revealing that a greater amount of surface vacancies are present in the case of solanum melongena-based sample. Quantitative information about Co (II) and oxygen defects enabled the solanum melongena mediated Co₃O₄ to behave as an efficient electrode material for the OER half-cell and supercapacitor applications.

Surface area and porosity are important factors that influence the performance of nanostructured materials. We measured the specific surface area and pore-size distribution of the pristine Co₃O₄ and solanum melongena mediated Co₃O₄ (CE-15) nanostructures using a nitrogen gas adsorption experiment. In Figure 5a,b, both nanostructures produced a type-IV isotherm, indicating macro-porosity in both pristine and solanum melongena-mediated Co₃O₄ structures. Using the multi-point BET method, the specific surface area of pristine Co₃O₄ was calculated. An estimated specific surface area of 6.72 m².g⁻¹ was observed, which is only two-fifth of the specific surface area of the solanum melongena mediated Co₃O₄ (CE-15) nanostructure (17.54 m².g⁻¹). The pore volumes of pure Co₃O₄ and solanum melongena mediated Co₃O₄ (CE-15) nanostructures were 1.892 × 10⁻² cc.g⁻¹ and 7.106 × 10⁻² cc.g⁻¹, respectively. The BET analysis has revealed that the solanum melongena mediated Co₃O₄ (CE-15) nanostructures experienced adequate surface area and pore volume which likely enhanced the electrochemical activity [47-49]

3.2 Evaluation of electrochemical performance of as prepared Co₃O₄ nanostructures

The electrochemical activity of Co₃O₄ nanostructures prepared with the use of rotten solanum melongena juice was examined through various electrochemical modes such as cyclic voltammetry (CV), linear sweep voltammetry (LSV), chronopotentiometry (CP) and electrochemical impedance spectroscopy (EIS) in alkaline solution of 1 M KOH. In Figure 6a, LSV polarization curves of pure Co₃O₄ and rotten solanum melongena juice mediated Co₃O₄ nanostructures with iR correction. Compared with pure Co₃O₄ nanostructures, rotten

solanum melongena juice assisted Co_3O_4 nanostructures demonstrated superior OER performance. The improved performance of Co_3O_4 nanostructures could be attributed to rotten solanum melongena juice's influence on shape orientation, size, and surface catalytic properties. As a result of the stabilizing, reducing, and capping properties of natural reductive and oxidative chemical compounds, the rotten solanum melongena juice contributes to the variability of morphology, surface properties, and particle size. Based on the LSV analysis, we calculated the OER overpotential of rotten solanum melongena juice-mediated Co_3O_4 nanostructures of 5 mL, 10 mL, 15 mL and 20 mL at 20 mAcm^{-2} to be 346 mV, 301 mV, 276 mV and 289 mV, respectively. However, the pure Co_3O_4 nanostructures experienced an overpotential of 369 mV at 20 mAcm^{-2} . It has been shown in the literature that surface defects particularly the oxygen vacancies accelerate the OER kinetics and XPS analysis has demonstrated that Co_3O_4 nanostructures prepared with the 15 mL of solanum melongena juice had significantly higher surface oxygen vacancies, which resulted in improved OER activity. In addition, the improved specific surface area of Co_3O_4 nanostructures prepared with 15 mL of solanum melongena juice significantly improved OER performance. It has previously been demonstrated that the OER kinetics of Co_3O_4 nanostructures are highly influenced by the particle size and the specific area of the particles [50-54]. Whereas with the decrease in particle size results in enhanced specific surface area, consequently increased OER performance has been reported [44-46, 51, 52,56]. Interestingly, 15 mL rotten solanum melongena juice assisted Co_3O_4 nanostructures has demonstrated low overpotential of 276 mV at 20 mAcm^{-2} for OER which is several orders lower than many of the recently Co_3O_4 nanostructures based electrocatalysts synthesized by different methods [57]. As shown in Figure 6b, a bar graph representation was made to illustrate the overpotential of as prepared Co_3O_4 nanostructures. Q. Xu *et al.* has designed hydrothermally $\text{Co}_3\text{O}_{4-x}\text{P}_{0.15}$, prepared Co_3O_4 nanostructures by hydrothermal method with overpotential of 338 mV at 10 mAcm^{-2} [58]. J. Y. Xie used oil bath and annealing method for the preparation of $\text{F}_{0.2}\text{-V-Co}_3\text{O}_4\text{-350}$ with overpotential of 320 mV at 10 mAcm^{-2} [59]. L. Li et al has prepared 6 wt% Ni- Co_3O_4 and 8 wt% Ni- Co_3O_4 using hydrothermal method and they has shown overpotential of 330 mV and 335 mV at 10 mAcm^{-2} [60]. It was also noticed from the existing literature that the overpotential possessed by 15 mL rotten solanum melongena juice mediated Co_3O_4 nanostructures is even lower than commercial OER electrocatalyst (IrO_2) with overpotential of 400 mV at 10 mAcm^{-2} , under the same electrolyte conditions. The OER kinetics of Co_3O_4 was examined through Tafel slope equation as given ($\eta = a + b \log j_0$), hereby η

represents overpotential, j_0 : current density, and b :Tafel slope. The estimated Tafel slopes are shown in Figure 6c. The associated Tafel slopes for 5mL, 10 mL, 15 mL 20 mL rotten solanum melongena juice mediated Co_3O_4 nanostructures and pure Co_3O_4 nanostructures were in the order 102 mVdec^{-1} , 83 mVdec^{-1} , 70 mVdec^{-1} , 81 mVdec^{-1} and 107 mVdec^{-1} respectively. The 15 mL solanum melongena mediated Co_3O_4 nanostructures signatures the lowest Tafel slope, thus has shown effective and rapid OER kinetics. Whereas the low Tafel slope of 70 mVdec^{-1} revealed that the adsorbed intermediates are the main rate determining step for the 15 mL rotten solanum melongena juice mediated Co_3O_4 nanostructures. This has been already generalized and described by the Krasil' Shchikov reaction model under the OER half-cell reaction in alkaline electrolytes [61-63].

Furthermore, the electrochemical impedance spectroscopy (EIS) was performed on the 5 mL, 10 mL, 15 mL and 20 mL rotten solanum melongena juice mediated Co_3O_4 nanostructures and pure Co_3O_4 nanostructures using 1.4V versus RHE with sweeping frequency of 100000 kHz to 0.1Hz, and an amplitude of 5 mV as shown in Figure 6d.

The charge transfer resistance (R_{ct}) of 15 mL solanum melongena mediated Co_3O_4 nanostructures was 119.1 Ohms which is lower than many other prepared samples including 5 mL, 10 mL and d 20 mL rotten solanum melongena juice mediated Co_3O_4 nanostructures and pure Co_3O_4 nanostructures including 1498 Ohms, 172.7 Ohms, 131.8 Ohms and 2442 Ohms respectively. Hence, 15 mL solanum melongena mediated Co_3O_4 nanostructures declared that the electrode material exhibited rapid charge transport between the electrode and electrolyte, consequently rapid OER kinetics has been demonstrated by the use of 15 mL rotten solanum melongena juice.

The long-term stability of 15 mL rotten solanum melongena juice mediated Co_3O_4 nanostructures was studied in alkaline solution of 1M KOH for 70 hours using chronopotentiometry measurement at two different overpotentials of 270 mV and 300 mV as shown in Figure 6e. The durability is one of the most important parameters for the nonprecious electrocatalysts in order to verify their practical aspects. The purpose of using two different current densities was to evaluate the durable behavior of rotten solanum melongena juice mediated Co_3O_4 nanostructures in terms of variation in current density, but the observed performance of material remained unaltered. This performance evaluation indicator has confirmed that the electrode material has not brought any significant variation in the change in potential even the oxygen gas bubbling was easily produced without any

effect on the removal or ineffectiveness of catalytic material. Based on these observations, it is safe to say that the proposed 15 mL rotten solanum melongena juice mediated Co_3O_4 nanostructures could be used as an alternative and promising electrocatalyst for long term water splitting. The stability of as synthesized Co_3O_4 nanostructures using 15 mL of rotten solanum melongena juice before and after durability was also investigated through LSV polarization curves as shown in Figure 6f. It was seen obviously from the LSV polarization curves that Co_3O_4 nanostructures exhibited the same onset potential, overpotential and current density, indicating the stability of electrode material and its applicability for the practical applications. The stability of the nanostructure was further analyzed by SEM analysis after the chronopotentiometry analysis for 70 hours as shown in Supplementary Figure (S1). The morphology of the nanostructure was unaffected which confirms that CE-15 nanostructures are highly stable and material can be used for long term applications

To support the LSV and Tafel analysis, the Cdl (electric double layer capacitance) of 5 mL, 10 mL, 15 mL and 20 mL rotten solanum melongena juice mediated Co_3O_4 nanostructures and pure Co_3O_4 nanostructures were estimated. For this purpose, cyclic voltammetry curves were recorded with non-faradic regions at fixed potential range from (1 to 1.22 V) versus RHE as shown in Figure (S2). A linear relationship between difference of anodic and cathode current densities divided by 2 at various sweeping scan rates was built [60-63]. The electrochemical active surface area (ECSA) was estimated using relations ($\text{ECSA} = C_{dl}/C_s$), herein C_s is specific capacitance of material [64, 65]. The 5mL, 10 mL, 15 mL and 20 mL solanum melongena mediated Co_3O_4 nanostructures and pure Co_3O_4 nanostructures exhibited the ECSA values of $3.4 \mu\text{Fcm}^{-2}$, $15.1 \mu\text{Fcm}^{-2}$, $19.4 \mu\text{Fcm}^{-2}$, $17.3 \mu\text{Fcm}^{-2}$ and $1.6 \mu\text{Fcm}^{-2}$ respectively as shown in Figure (S2). The observed ECSA values again supported the obtained results of OER performance via low overpotential and the Tafel slope of 15 mL rotten solanum melongena juice mediated Co_3O_4 nanostructures. The summary of OER performance of different Co_3O_4 nanostructures is given in Supplementary Table (S2). The performance of 15 mL rotten solanum melongena juice mediated Co_3O_4 was compared with the recently reported catalysts in terms of overpotential, electrolyte condition as given in Supplementary Table (S3). From the comparative analysis, it was seen that the presented synthetic method is facile, scale up, ecofriendly and environment friendly and the proposed catalyst has superior OER activity to many of the recently reported catalysts. The rotten solanum melongena is attractive and useful raw material source towards the fabrication of efficient electrocatalytic materials.

3.3 Capacitive evaluation of rotten solanum melongena juice mediated Co_3O_4 nanostructures

The preliminary capacitance properties of solanum melongena mediated Co_3O_4 nanostructures were investigated through cyclic voltammetry (CV). For supercapacitor performance, a three electrodes cell set up built in 3.0 M KOH electrolytic cell solution. Hence, the analysis was performed for the exploration of capacitive properties of bare nickel foam, green mediated Co_3O_4 nanostructures, and Co_3O_4 nanostructures without the Solanum melongena juice. The CV curves of 5 mL, 10 mL and 15 mL rotten solanum melongena juice mediated Co_3O_4 nanostructures and pure Co_3O_4 nanostructures were measured using a potential window of 0.0 to 0.5 V against (Ag/AgCl) under various sweeping scan rates such as 10, 20, 30, 40, 50 and 60 mV/s as shown in Figure (S3)a-e. From the CV curves behavior, it is noticed that the different solanum melongena mediated Co_3O_4 nanostructures and pure Co_3O_4 nanostructures under the influence of various scan rates, indicating the variable CV curve shape with sweeping potential. The CV curves at different scan rates of bare nickel foam are shown in Figure (S3)a. It is obvious for the pure Co_3O_4 nanostructures that the oxidation peak potential was shifted from 0.43 V to 0.45 V, whereas the reduction potential peak was shifted from 0.31 V to 0.27 V towards higher potential in terms of oxidation potential and lower potential in terms of reduction potential as shown in Figure (S3)b. While for the Co_3O_4 nanostructures synthesized with 5 mL of solanum melongena juice has revealed shift in oxidation peak from 0.36 V to 0.39 V at increasing scan rate, whereas the reduction potential was shifted from 0.3V to 0.28 V at increasing scan rate as shown in Figure (S3)c. The CV curves was also recorded for the 10 mL of solanum melongena juice mediated Co_3O_4 nanostructures at various scan rates and the corresponding peak shift in potential for oxidation was notice from 0.39 V to 0.41V, and the reduction peak potential shift was observed from 0.27V to 0.21V with increasing scan rate as shown in Figure (S3)d. The CV curves ate different scan rates were measured for the 15 mL rotten solanum melongena juice mediated Co_3O_4 nanostructures and the shift in oxidation potential from 0.35V to 0.38 V, however for the reduction potential peak shift was found from 0.3V to 0.27 V with increasing scan rates as shown in Figure (S3)e. In all samples, there was an increasing shift in oxidation potential with an increasing scan rate, however there was decrease shift in reduction potential with increasing scan rate. This is because of the increased internal resistance and a polarization effect caused with increasing scan rate [66]. Moreover, the sharp and wide redox pair of peaks have been noticed at the nonlinear region of CV curves, revealing the pseudo-

capacitance characteristics of the different solanum melongena mediated Co_3O_4 nanostructures. Both the anode and cathode peaks were clearly shown. The redox peaks were very sharp and homogenous with increasing scan rate from 10 mV/s to 60 mV/s, suggesting the favorable reversible redox behaviors [67]. The Co_3O_4 nanostructures were describing the electron or charge transfer through CV analysis in 3.0M electrolytic solution of KOH. The redox behavior of CV curves at different scan rates for each material was characterized with the electrochemical double layer capacitance (EDLC). The previous CV results on the Co_3O_4 nanostructures illustrated the reaction mechanisms in various electrolytes are fully justifying the presented CV results. The Dunn method was used to evaluate the diffusion and capacitive presentation through CV curves and the distribution of diffusion and capacitive at 60 mV/s is shown in Figure (S4). It could be seen that the capacitive percentage of was successively increased with increasing amount of solanum melongena used during the synthesis of Co_3O_4 nanostructures. The diffusion and capacitive plots were illustrated using CV curves at different scan rates as shown in Figure S5. It was found that the 15 mL solanum melongena assisted Co_3O_4 nanostructures resulted larger capacitive behavior than the 5 mL and 10 mL solanum melongena mediated Co_3O_4 nanostructures and pure Co_3O_4 nanostructures. The features of CV curves are highly depending on the shape orientation, surface, size and structural properties of as prepared Co_3O_4 nanostructures. Based on these aspects from CV analysis, it is safe to say that the Co_3O_4 nanostructures have high potential and promising activity towards pseudo capacitance applications [68, 69]. The galvanic charge-discharge (GCD) curves were recorded for bare nickel foam, solanum melongena mediated Co_3O_4 nanostructures and pure Co_3O_4 nanostructures using various current densities such as 1.25 A/g, 2.5A/g, 3.75A/g, 5 A/g and 6.25A/g in the potential window 0-0.45 V as enclosed in Figure 7a-e.

The values of specific capacitance, energy density and power density were estimated through the relation:

$$C_s = \frac{I \times \Delta t}{m \times \Delta V} \quad (4)$$

$$E_d = \frac{C_s \times (\Delta V^2)}{2} \quad (5)$$

$$P_d = \frac{E}{\Delta t} \quad (6)$$

Here C_s (F/g) is specific capacitance, I (A) current observed at the time of discharge, Δt discharge time, ΔV voltage range and m (g) is active mass of electrode material.

From the GCD curves, it was noticed that they are associated with the pair of platforms, describing its pseudocapacitive properties and typical redox process took place at the time of charge-discharge phenomenon. Equation (4) was used to estimate the specific capacitance values for each electrode materials and they are given in Table 2. It could be noticed that the 15 mL rotten solanum melongena juice mediated Co_3O_4 nanostructures experienced the highest amount of specific capacitance 1303.13 F/g at 1.25 A/g. Hence, the GCD profiles as synthesized solanum melongena mediated Co_3O_4 nanostructures suggest that migration and diffusions of ions through 3.0 M KOH electrolytic solution has significantly enhanced the electrochemical capacitance as shown in Figure 8a. While the solanum melongena juice mediated Co_3O_4 nanostructures were exhibiting the specific capacitance of 421.95 F/g at 1.25 A/g and the bare nickel foam had specific capacitance of 307.69 F/g at 1.25 A/g. The enhancement in the specific capacitance magnitude is highly dependent on the electrical conductivity, redox properties, and dimension of nanoparticles tailored by the solanum melongena juice via the presence of green reducing, capping and stabilizing agents [70-73]. For other electrode materials such as 5mL and 10 mL solanum melongena mediated Co_3O_4 nanostructures possessed the specific capacitance values of 728.13 F/g at 1.25 A/g and 768.75 F/g at 1.25 A/g respectively. While the estimated values of specific capacitance at different higher current densities are given in Table 2. Moreover, the observable specific capacitance values depend on the surface area of electrode material, shape orientation and variability in electrolyte concentration. Interestingly, it has been found that the synthetic method used for the development of electrode materials is also influencing on the values of specific capacitance [74-76]. The comparative analysis was also performed of presented electrode material with the recently published works on the electrode materials for supercapacitor applications as given in Supplementary Table (S4). The performance evaluation suggested that the proposed electrode material has equal or superior pseudo capacitance performance to many of the recently reported electrode materials in terms of facile synthesis, low cost, high specific capacitance, high power and energy density. The estimated power density, energy density from GCD profiles of different materials and specific capacitance retention % and columbic efficiency % are shown in Figure 8b. The energy density of pure Co_3O_4 nanostructures, bare nickel foam, 5 mL, 10 mL and 15 mL rotten solanum melongena juice mediated Co_3O_4 nanostructures was estimated in the order 9.10, 6.50, 17.08, 16.18 and 28.96

Wh kg^{-1} respectively. While the columbic efficiency and specific capacitance retention % for pure Co_3O_4 nanostructures was observed as 64-72% and 70-77% for 30000 repeatable GCD cycles at 1.25 A/g respectively as shown in Figure 8c. However, the 15 mL solanum melongena mediated Co_3O_4 nanostructures exhibited highly enhanced columbic efficiency and specific capacitance retention % as 91-97% and 94-99% for 30000 repeatable GCD cycles respectively as shown in Figure 8d. These obtained results of cyclic stability are better in cycling stability to many of the recent pseudo capacitance electrode materials [77-80]. Moreover, the rotten solanum melongena juice has enhanced the capacitance of Co_3O_4 nanostructures but the columbic efficiency was slightly deteriorated because of several factors such internal resistance, poor ionic conductivity and IR drop [81]. From the long cyclic stability for the maintenance of specific capacitance revealed that the green reducing, capping and stabilizing agents from rotten solanum melongena juice has drastically played a vital to strengthen the electrochemical capacitance performance of Co_3O_4 nanostructures. Hence, we have seen the formation of Co_3O_4 nanostructures by the use of solanum melongena juice and having relatively smaller size and exhibited high surface area. For designing the efficient electrochemical supercapacitors, the large surface areas of active electrode is required due to high adsorption of hydroxide ions from the electrolytic solution, hence high charge storage capacity is expected. The large surface area of Co_3O_4 nanostructures obtained through the use of 15 mL of solanum melongena juice and offered the frequent interaction with the hydroxide ions and relatively higher adsorption rate was found. Hence, the enhanced electrochemical supercapacitor performance was noticed for the Co_3O_4 nanostructures prepared with the use of 15 mL of solanum melongena juic. The OER and supercapacitor performances of rotten solanum melongena juice assisted Co_3O_4 have been found superior in terms of lower overpotential than aloe vera assisted CuO and Co_3O_4 composite [82] and higher specific capacitance than the milky sap of *Calotropis procera* mediated Co_3O_4 [83]. These favorable aspects of rotten solanum melongena juice towards improving the electrochemical properties of Co_3O_4 are highlighting its importance for the development of next generation for electrode materials. For simplicity, the summary of observed capacitance results is enclosed in Table 2.

Table 2: Supercapacitor results of different prepared Co_3O_4 nanostructures with and without rotten solanum melongena juice.

Samples	Current Density (Ag ⁻¹)	Specific Capacitance (Fg ⁻¹)	Energy Density (Wh kg ⁻¹)	Power Density (W kg ⁻¹)	Columbic Efficiency (%)	Capacitance Retention (%)
CE-05	1.25	728.13	16.18	250.00	-	-
	2.5	718.75	15.97	500.00		
	3.75	703.13	15.63	750.00		
	5	537.50	11.94	1000.00		
	6.25	312.50	6.94	1250.00		
CE-10	1.25	768.75	17.08	250.00	91-97 %	94-99 %
	2.5	737.50	16.39	500.00		
	3.75	693.75	15.42	750.00		
	5	412.50	9.17	1000.00		
	6.25	390.63	8.68	1250.00		
CE-15	1.25	1303.13	28.96	250.00	91-97 %	94-99 %
	2.5	1262.50	28.06	500.00		
	3.75	1134.38	25.21	750.00		
	5	937.50	20.83	1000.00		
	6.25	828.13	18.40	1250.00		
Pure (Co₃O₄)	1.25	421.95	9.10	246.25	64-72%	70-77%
	2.5	375.32	8.05	491.25		
	3.75	361.68	7.80	738.75		
	5	330.79	7.10	982.50		
	6.25	286.99	6.13	1225.00		
Ni-Foam (Bare)	1.25	307.69	6.50	243.75	-	-
	2.5	294.12	6.25	488.75		
	3.75	278.85	5.89	731.25		
	5	269.23	5.69	975.00		
	6.25	160.26	3.39	1218.75		

4 Conclusions

In summary, rotten solanum melongena juice was evaluated for its impact on a number of structural, morphological, and chemical properties of Co_3O_4 nanostructures as well as its ability to enhance electrochemical performance. The Co_3O_4 nanostructures were prepared using 5 mL, 10 mL, 10 mL and 15 mL of rotten solanum melongena juice. In particular, the 15 mL rotten solanum melongena juice mediated Co_3O_4 nanostructures displayed well oriented morphology, excellent crystalline properties, an abundance of surface oxygen vacancies, high specific surface area, a high ECSA, and low charge transfer resistance. It has been demonstrated that these Co_3O_4 nanostructures have enhanced electrochemical performance towards OER with a low overpotential of 276 mV at 20 mA cm^{-2} and a Tafel slope of 70 mVdec^{-1} . The rotten solanum melongena juice mediated Co_3O_4 nanostructures were found highly durable and stable for 70 h. The Co_3O_4 nanostructures prepared with 15 mL of rotten solanum melongena juice exhibited efficient electrode material properties for the development of an electrochemical supercapacitor and had shown a specific capacitance of 1303.13 F/g and energy density of 28.96 Whkg^{-1} at the highest power density of 250 W Kg^{-1} at 1.25 A/g . The electrode material has shown an excellent percentage specific capacitance retention up to 97% for repeatable 30000 GCD cycles at 1.25 A/g . The electrode material based on Co_3O_4 nanostructures synthesized with 15 mL of rotten solanum melongena juice possessed potential cyclic stability. Therefore, it could be used an alternative electrode material for long-term applications. These benefitting aspects of as-prepared Co_3O_4 nanostructures suggest that rotten solanum melongena juice is a highly useful raw material source for reducing, capping and stabilizing agents for the preparation of next generation efficient electrode materials for electrochemical applications.

Acknowledgment

The authors would like to gratefully acknowledge the Higher Education Commission Pakistan for partial support under the project NRP/8350/8330. A.T and E.D would like to acknowledge the partial support of Ajman University, Internal Research Grant No. DRGS ref. 2024-IRG-HBS-1. Brigitte Vigolo and Mélanie Emo would like to thank the platform “Microscopies, Microprobes and Metallography (3 M)” (Institut Jean Lamour, IJL, Nancy, France) for access to TEM and SEM facilities. This publication is part of the R&D project PID2021-126235OB-C32 funded by MCIN/AEI/10.13039/501100011033/ and FEDER funds.

Conflict of Interest

Authors declare no competing interests in the resented research work.

Data Availability Statements

Data sets generated during the current study are available from the corresponding author on reasonable request.

Authors contribution

Abdul Jaleel Laghari, did material synthesis and partial electrochemical tests

Umair Aftab, did supervision

Muhammad Ishaque Abro, did supervision

Aneela Tahira, did XRD analysis

Elmuez Dawi, did visualization and presentation of findings

Muhammad Ali Bhatti, did partial electrochemical tests

Antonia Infantes-Molina, did XPS analysis and wrote the draft

Melanie Emo, did TEM analysis and wrote the draft

Brigitte Vigolo, did SEM and TEM analysis and wrote the draft

Rafat M. Ibrahim, did validate the results and edited the draft

Zafar Hussain Ibupoto, did supervision and wrote the original draft of manuscript

5. References

- [1] A. Vazhayil, L. Vazhayal, J. Thomas, S. Ashok and C. N. Thomas, *Applied Surface Science Advances*, 2021, **6**, 100184.
- [2] S. Anwar, F. Khan, Y. Zhang and A. Djire, *Int J Hydrogen Energy*, 2021, **46**, 32284–32317.
- [3] L.S. Ferreira, T.R. Silva, J.R.D. Santos, V.D. Silva, R.A. Raimundo, M.A. Morales and D.A. Macedo, *Mater Chem Phys*, 2019, **237**, 121847.
- [4] A.A. Lourenço, V.D. Silva, R.B. da Silva, U.C. Silva, C. Chesman, C. Salvador, T.A. Simões, D.A. Macedo and F.F. da Silva, *J Colloid Interface Sci*, 2021, **582**, 124–136.
- [5] M.-I. Jamesh and X. Sun, *J Power Sources*, 2018, **400**, 31–68.
- [6] P. Zhang and H. He, *J Alloys Compd*, 2020, **826**, 153993.
- [7] X.-Y. Zhang, W.-L. Yu, J. Zhao, B. Dong, C.-G. Liu and Y.-M. Chai, *Appl Mater Today*, 2021, **22**, 100913.
- [8] X. Xu, Z. Huang, C. Zhao, X. Ding, X. Liu, D. Wang, Z. Hui, R. Jia and Y. Liu, *Ceram Int*, 2020, **46**, 13125–13132.
- [9] M. Leng, X. Huang, W. Xiao, J. Ding, B. Liu, Y. Du and J. Xue, *Nano Energy*, 2017, **33**, 445–452.
- [10] Z. Zha, Z. Zhang, P. Xiang, H. Zhu, B. Zhou, Z. Sun and S. Zhou, *RSC Adv*, 2021, **11**, 1077–1085.
- [11] X. Hou, T. Peng, J. Cheng, Q. Yu, R. Luo, Y. Lu, X. Liu, J.-K. Kim, J. He and Y. Luo, *Nano Res*, 2017, **10**, 2570–2583.
- [12] Y.-P. Gao, Z.-B. Zhai, Q.-Q. Wang, Z.-Q. Hou and K.-J. Huang, *J Colloid Interface Sci*, 2019, **539**, 38–44.
- [13] H. Sun, Y. Miao, G. Wang, X. Han, Y. Wang, Z. Zhang, C. Luo, X. Liu, C. Xu and H. Chen, *J Energy Storage*, 2024, **76**, 109780.
- [14] J. Sun, X. Tian, C. Xu and H. Chen, *Journal of Materiomics*, 2021, **7**, 1358–1368.
- [15] Y. Wang, X. Ma, S. Li, J. Sun, Y. Zhang, H. Chen and C. Xu, *J Alloys Compd*, 2020, **818**, 152905.
- [16] M. Khalaj, S.Z. Golkhatmi and A. Sedghi, *Diam Relat Mater*, 2021, **114**, 108313.
- [17] H. Jiang, Q. Mu, H. Kimura, R. Liu, W. Yang, L. Liu, W. Du and C. Hou, *Materials International*, 2023, **33**, 743–753.
- [18] C. Hou, W. Yang, H. Kimura, X. Xie, X. Zhang, X. Sun, Z. Yu, X. Yang, Y. Zhang, B. Wang, B. Bin Xu, D. Sridhar, H. Algadi, Z. Guo and W. Du, *J Mater Sci Technol*, 2023, **142**, 185–195.

- [19] J.-Y. Zhang, Y. Yan, B. Mei, R. Qi, T. He, Z. Wang, W. Fang, S. Zaman, Y. Su, S. Ding and B.Y. Xia, *Energy Environ Sci*, 2021, **14**, 365–373.
- [20] Y. Wang, X. Li, M. Zhang, Y. Zhou, D. Rao, C. Zhong, J. Zhang, X. Han, W. Hu, Y. Zhang, K. Zaghib, Y. Wang and Y. Deng, *Advanced Materials*, 2020, **32**, 2000231.
- [21] I. Fareed, M. D. Khan, S. Murtaza, M. U. Hassan Farooq, Z. U. Rehman, M. U. Farooq, F. K. Butt and M. Tahir, *RSC Adv.*, 2024, **14**, 26556–26567.
- [22] S. Ding, Y. Sun, F. Lou, L. Yu, B. Xia, J. Duan, Y. Zhang and S. Chen, *Journal of Power Sources*, 2022, **520**, 230873.
- [23] Q. Huang, B. Xia, M. Li, H. Guan, M. Antonietti and S. Chen, *Nat Commun*, 2024, **15**, 4157.
- [24] F. Ali and N.R. Khalid, *Appl Nanosci*, 2020, **10**, 1481–1488.
- [25] L.-H. Ai and J. Jiang, *Powder Technol*, 2009, **195**, 11–14.
- [26] B. Wang, S. Wang, Y. Tang, Y. Ji, W. Liu and X.-Y. Lu, *Energy Procedia*, 2019, **158**, 5293–5298.
- [27] G. Patrinoiu, J.R. Rodriguez, Y. Wang, R. Birjega, P. Osiceanu, A.M. Musuc, Z. Qi, H. Wang, V.G. Pol, J.M. Calderon-Moreno and O. Carp, *Appl Surf Sci*, 2020, **510**, 145431.
- [28] M. Khalaj, S.Z. Golkhatmi and A. Sedghi, *Diam Relat Mater*, 2021, **114**, 108313.
- [29] S.Z. Mohammadi, B. Lashkari and A. Khosravan, *Surfaces and Interfaces*, 2021, **23**, 100970.
- [30] S.-Y. Jeong, H.-J. Ahn and T.-Y. Seong, *Mater Lett*, 2011, **65**, 471–473.
- [31] A. UmaSudharshini, M. Bououdina, M. Venkateshwarlu, C. Manoharan and P. Dhamodharan, *Surfaces and Interfaces*, 2020, **19**, 100535.
- [32] J.A. Lopes Matias, I. Silva, M. Sousa, J.B. de Oliveira, M. Morales Torres and D. Silva, *Ceram Int*, 2021, 47.
- [33] R.A. Raimundo, J.N. Silva, T.R. Silva, A.J.M. Araújo, J.F.G.A. Oliveira, L.C. de Lima, M.A. Morales, M.M. Soares and D.A. Macedo, *Mater Lett*, 2023, **341**, 134196.
- [34] S. Suresh, S. Vennila, J. Anita Lett, I. Fatimah, F. Mohammad, H.A. Al-Lohedan, S.F. Alshahateet, M.A. Motalib Hossain and M. Rafie Johan, *Inorganic and Nano-Metal Chemistry*, 2022, **52**, 173–180.
- [35] H. Huang, J. Wang, J. Zhang, J. Cai, J. Pi and J.-F. Xu, *Pharmaceutics*, 2021, **13**, 1599.
- [36] P. Chelliah, J.K. Gupta, S. Mohammad Wabaidur, M.R. Siddiqui, S. Foon Lee and W.C. Lai, *Water*, 2023, **15**, 297.
- [37] R.A. Raimundo, C.S. Lourenço, N.T. Câmara, T.R. Silva, J.R.D. Santos, A.J.M. Araújo, M.M.S. Silva, J.F.G. de A. Oliveira, D.A. Macedo, U.U. Gomes, M.A. Morales and M.M. Soares, *Journal of Electroanalytical Chemistry*, 2023, **932**, 117218.

- [38] N. Matinise, N. Mayedwa, X.G. Fuku, N. Mongwaketsi1 and M. Maaza, AIP Conf. Proc, 2018, **1962**, 040005.
- [39] E. T. Bekele, H. C. A. Murthy, D. Muniswamy, Y. A. Lemenh, M. S.Shume, G. T. Ayanie, A. P. Kumar, C. R.Ravikumar, R. Balachandran and A. Roy, Bioinorg Chem Appl. 2022 8440756.
- [40] R. Noor, H. Yasmin, N. Ilyas, A. Nosheen, M.N. Hassan, S. Mumtaz, N. Khan, A. Ahmad and P. Ahmad, Chemosphere, 2022, **292**, 133201.
- [41] A. Karimi, M. Kazemi, S.A. Samani and J. Simal-Gandara, Trends Food Sci Technol, 2021, **112**, 518–531.
- [42] <https://impactful.ninja/what-is-the-carbon-footprint-of-eggplants/>
- [43] T.-Y. Wei, C.-H. Chen, H.-C. Chien, S.-Y. Lu and C.-C. Hu, Adv Mater, 2010, **22**, 347–351.
- [44] T. Liu and G. Liu, J Mater Chem A Mater, 2019, **7**, 23476–23488.
- [45] K.-L. Yan, J.-F. Qin, J.-H. Lin, B. Dong, J.-Q. Chi, Z.-Z. Liu, F.-N. Dai, Y.-M. Chai and C.-G. Liu, J Mater Chem A Mater, 2018, **6**, 5678–5686.
- [46] Z. Xiao, Y.-C. Huang, C.-L. Dong, C. Xie, Z. Liu, S. Du, W. Chen, D. Yan, L. Tao, Z. Shu, G. Zhang, H. Duan, Y. Wang, Y. Zou, R. Chen and S. Wang, J Am Chem Soc, 2020, **142**, 12087–12095.
- [47] J. Jirkovský, M. Makarova and P. Krtíl, Electrochem Commun, 2006, 1417–1422.
- [48] C. Hou, F. Li, H. Kimura, Q. Li, L. Liu, Q. Chu, J. Wu, G. Fan and W. Du, Journal of Materials Research and Technology, 2023, **25**, 5148–5158.
- [49] F. Li, N. Wu, H. Kimura, Y. Wang, B. Bin Xu, D. Wang, Y. Li, H. Algadi, Z. Guo, W. Du and C. Hou, Nanomicro Lett, 2023, **15**, 220.
- [50] Q. Li, L. Liu, H. Kimura, X. Zhang, X. Liu, X. Xie, X. Sun, C. Xu, W. Du and C. Hou, J Colloid Interface Sci, 2024 , **655**, 634–642.
- [51] A. Saad, D. Liu, Y. Wu, Z. Song, Y. Li, T. Najam, K. Zong, P. Tsiakaras and X. Cai, Appl Catal B, 2021, **298**, 120529.
- [52] K. Chakrapani, G. Bendt, H. Hajiyani, I. Schwarzrock, T. Lunkenbein, S. Salamon, J. Landers, H. Wende, R. Schlögl, R. Pentcheva, M. Behrens and S. Schulz, ChemCatChem, 2017, **9**, 2988–2995.
- [53] C. Broicher, M. Klingenhof, M. Frisch, S. Dresch, N.M. Kubo, J. Artz, J. Radnik, S. Palkovits, A.K. Beine, P. Strasser and R. Palkovits, Catal Sci Technol, 2021, **11**, 7278–7286.
- [54] C. Roy, B. Sebok, S.B. Scott, E.M. Fiordaliso, J.E. Sørensen, A. Bodin, D.B. Trimarco, C.D. Damsgaard, P.C.K. Vesborg, O. Hansen, I.E.L. Stephens, J. Kibsgaard and I. Chorkendorff, Nat Catal, 2018, **1**, 820–829.
- [55] A. Muthurasu, V. Maruthapandian and H.Y. Kim, Appl Catal B, 2019, **248**, 202–210.

- [56] Q. Xu, H. Jiang, H. Zhang, H. Jiang and C. Li, *Electrochim Acta*, 2018, **259**, 962–967.
- [57] J.-Y. Xie, R.-Y. Fan, J.-Y. Fu, Y.-N. Zhen, M.-X. Li, H.-J. Liu, Y. Ma, F. Wang, Y.-M. Chai and B. Dong, *Int J Hydrogen Energy*, 2021, **46**, 19962–19970
- [58] L. Li, Q. Xu, Y. Zhang, J. Li, J. Fang, Y. Dai, X. Cheng, Y. You and X. Li, *J Alloys Compd*, 2020, **823**, 153750.
- [59] H. Jiang, H. Zhang, Q. Kang, H. Ma, Y. Tong, F. Gao and Q. Lu, *Sci Rep*, 2019, **9**, 15681.
- [60] J. Lian, Y. Wu, H. Zhang, S. Gu, Z. Zeng and X. Ye, *Int J Hydrogen Energy*, 2018, **43**, 12929–12938.
- [61] G. Li, L. Anderson, Y. Chen, M. Pan and P.-Y. Abel Chuang, *Sustain Energy Fuels*, 2018, **2**, 237–251.
- [62] C.S. Lim, C.K. Chua, Z. Sofer, O. Jankovský and M. Pumera, *Chemistry of Materials*, 2014, **26**, 4130–4136.
- [63] R.A. Raimundo, V.D. Silva, E.S. Medeiros, D.A. Macedo, T.A. Simões, U.U. Gomes, M.A. Morales and R.M. Gomes, *Journal of Physics and Chemistry of Solids*, 2020, **139**, 109325.
- [64] V.D. Silva, R.A. Raimundo, T.A. Simões, F.J.A. Loureiro, D.P. Fagg, M.A. Morales, D.A. Macedo and E.S. Medeiros, *Int J Hydrogen Energy*, 2021, **46**, 3798–3810.
- [65] S. Liu, K.S. Hui and K.N. Hui, *ACS Appl Mater Interfaces*, 2016, **8**, 3258–3267.
- [66] L. Cheng, M. Xu, Q. Zhang, G. Li, J. Chen and Y. Lou, *J Alloys Compd*, 2019, **781**, 245–254.
- [67] G.-S. Jang, S. Ameen, M.S. Akhtar and H.-S. Shin, *Ceram Int*, 2018, **44**, 588–595.
- [68] X.-H. Xia, J.-P. Tu, X.-L. Wang, C.-D. Gu and X.-B. Zhao, *Chemical Communications*, 2011, **47**, 5786–5788.
- [69] C. Liu, A. Gao, F. Yi, D. Shu, H. Yi, X. Zhou, J. Hao, C. He and Z. Zhu, *Electrochim Acta*, 2019, **326**, 134965.
- [70] J. Chen, B. Yao, C. Li and G. Shi, *Carbon*, 2013, **64**, 225–229.
- [71] M. Li, S.K. Cushing, X. Zhou, S. Guo and N. Wu, *J Mater Chem*, 2012, **22**, 23374–23379.
- [72] Y. Liu, Z. Cheng, H. Sun, H. Arandiyana, J. Li and M. Ahmad, *J Power Sources*, 2015, **273**, 878–884.
- [73] R. Kumar, R.K. Singh, P.K. Dubey, D.P. Singh and R.M. Yadav, *ACS Appl Mater Interfaces*, 2015, **7**, 15042–15051.
- [74] M. Mirzaeian, N. Akhanova, M. Gabdullin, Z. Kalkozova, A. Tulegenova, S. Nurbolat and K. Abdullin, *Energies (Basel)*, 2020, **13**, 5228.
- [75] C. V Niveditha, R. Aswini, M.J. Jabeen Fatima, R. Ramanarayan, N. Pullanjiyot and S. Swaminathan, *Mater Res Express*, 2018, **5**, 065501.

- [76] L. Li, P. Wang, Q. Shao and X. Huang, *Chem Soc Rev*, 2020, **49**, 3072–3106.
- [77] S. Kumari, B.P. Ajayi, B. Kumar, J.B. Jasinski, M.K. Sunkara and J.M. Spurgeon, *Energy Environ Sci*, 2017, **10**, 2432–2440.
- [78] Z. Wang, Q.-K. Li, C. Zhang, Z. Cheng, W. Chen, E.A. McHugh, R.A. Carter, B.I. Yakobson and J.M. Tour, *ACS Catal*, 2021, **11**, 2454–2459.
- [79] K. Guo, Z. Zou, J. Du, Y. Zhao, B. Zhou and C. Xu, *Chemical Communications*, 2018, **54**, 11140–11143.
- [80] L. Li, K. Chao, X. Liu and S. Zhou, *J Alloys Compd*, 2023, **941**, 168952
- [81] H. Razmi and E. Habibi, *Electrochim Acta*, 2010, **55**, 8731–8737.
- [82] D.K. Sarkar, V. Selvanathan, M. Mottakin, M.A. Islam, H. Almohamadi, N.H. Alharthi and M. Akhtaruzzaman, *International Journal of Hydrogen Energy*, 2024, **51**, 700-712.
- [83] A.L. Bhatti, A. Tahira, S. Kumar, Z. A. Ujjan, M. A. Bhatti, S.Kumar, U.Aftab, A. Karsy, A. Nafady, A. Infantes-Molina and Z. H. Ibupoto, *RSC Adv*, 2023, **26**, 17710–17726. doi: 10.1039/d3ra02555a

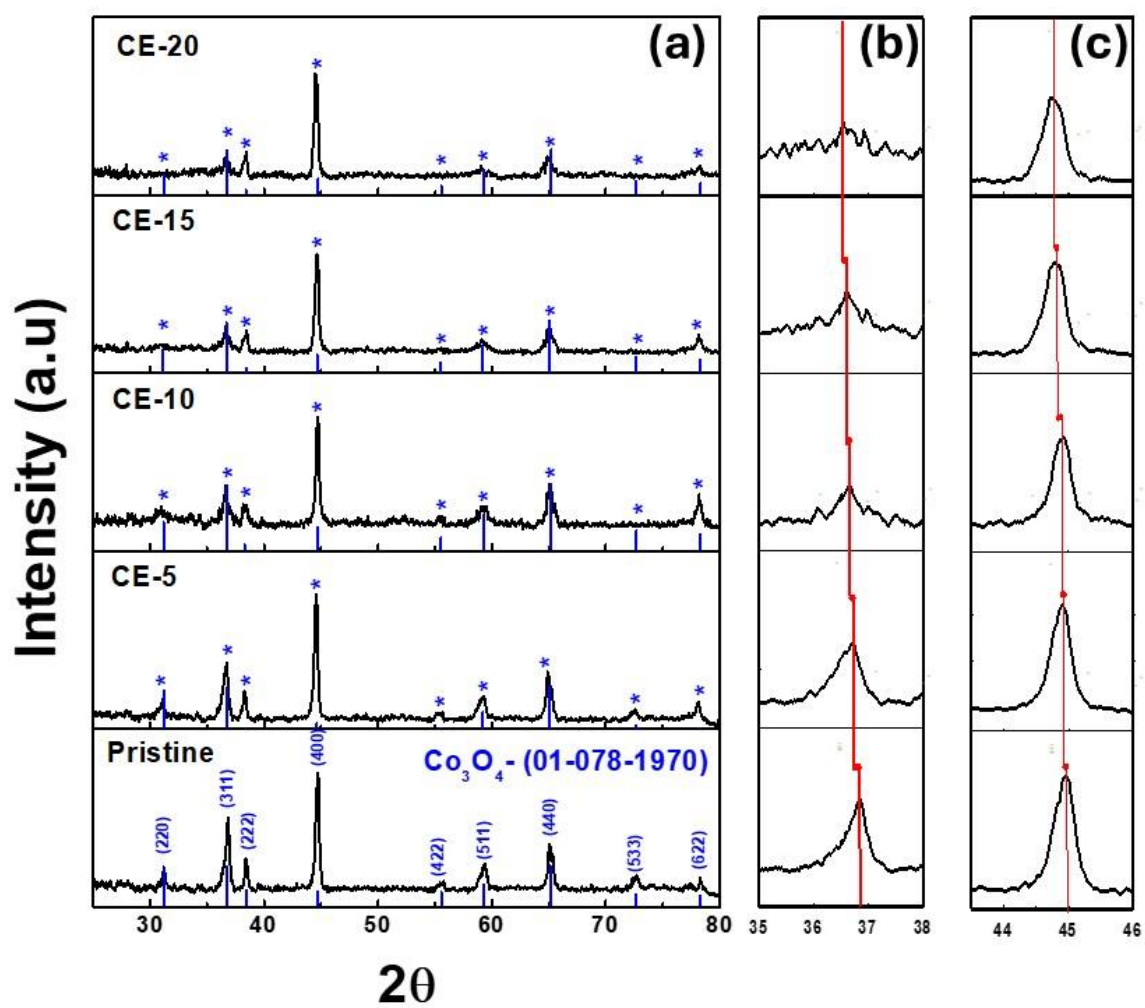


Figure 1: (a) XRD patterns of Co₃O₄ synthesized without rotten solanum melongena juice (pristine) and with 5 mL (CE-5), 10 mL (CE-10), 15 mL (CE-15) and 20 mL (CE-20) of rotten solanum melongenas juice. (b) (311) plane peak shift of corresponding XRD patterns, (c) (400) plane main peak shift of corresponding XRD patterns.

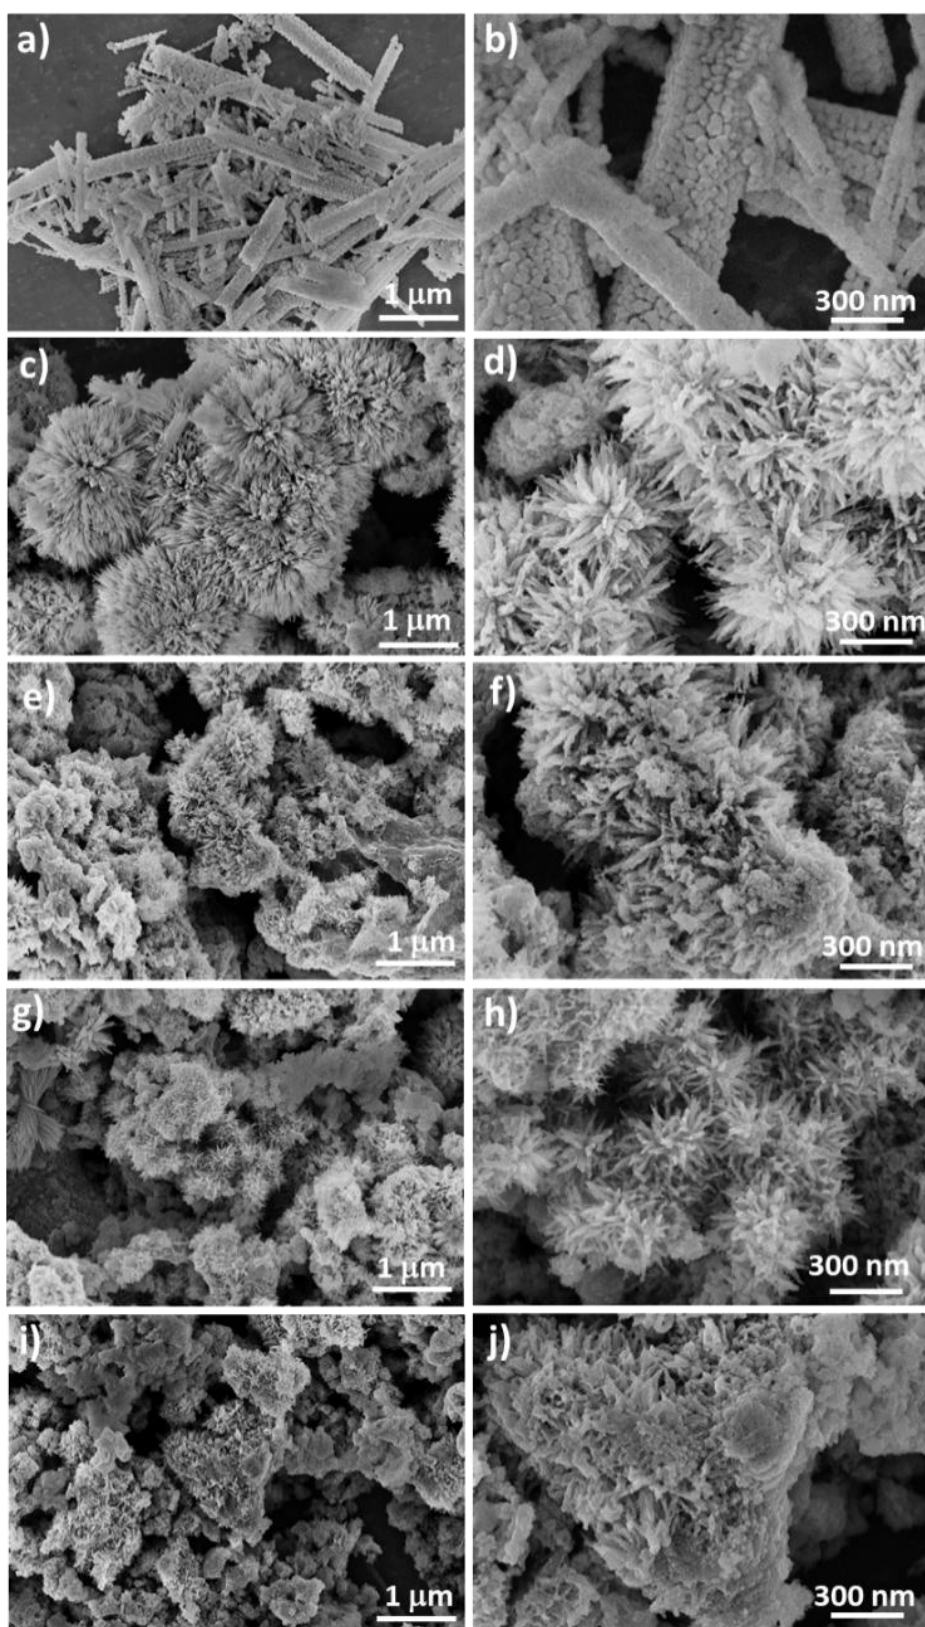


Figure 2: SEM images at different magnifications of Co_3O_4 synthesized (a and b) without rotten solanum melongena juice and (c and d) with 5 mL, (e and f) 10 mL, (g and h) 15 mL and (i and j) 20 mL of rotten solanum melongena juice.

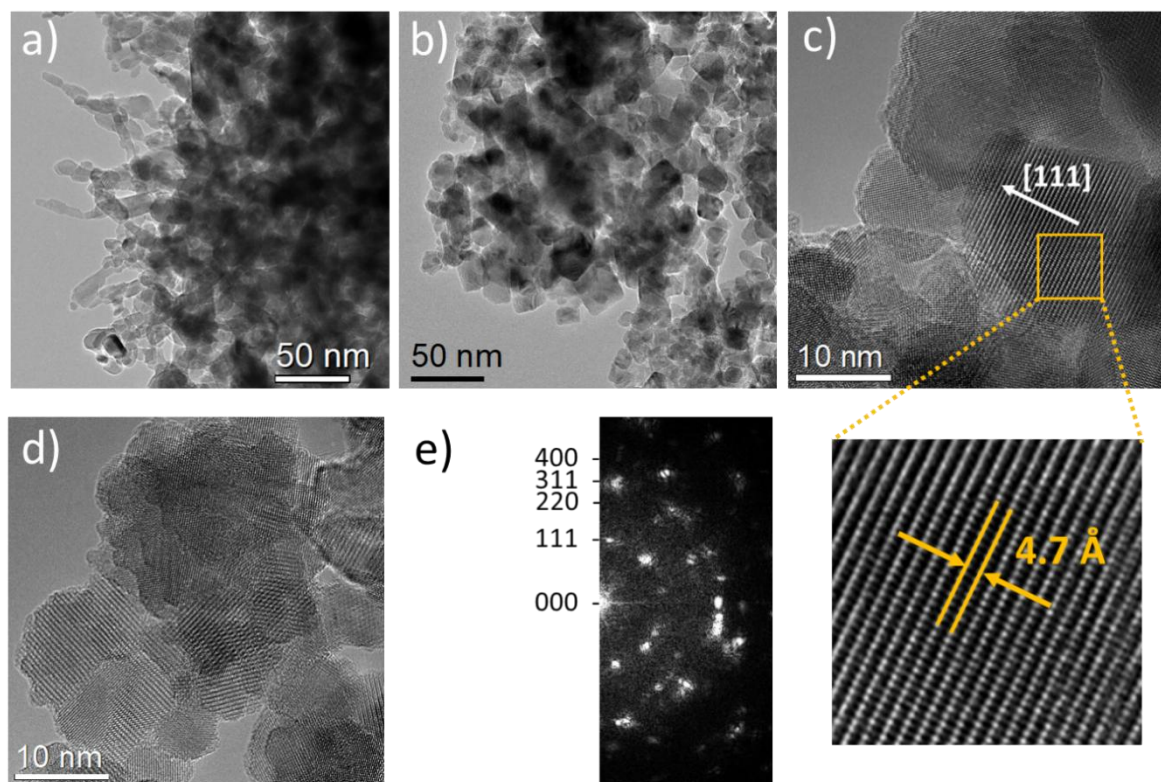


Figure 3: (a-b) TEM and (c-d) HRTEM micrographs at different magnifications of Co_3O_4 sample prepared with 15 mL of rotten solanum melongena juice and (e) corresponding Fast Fourier Transform of (d).

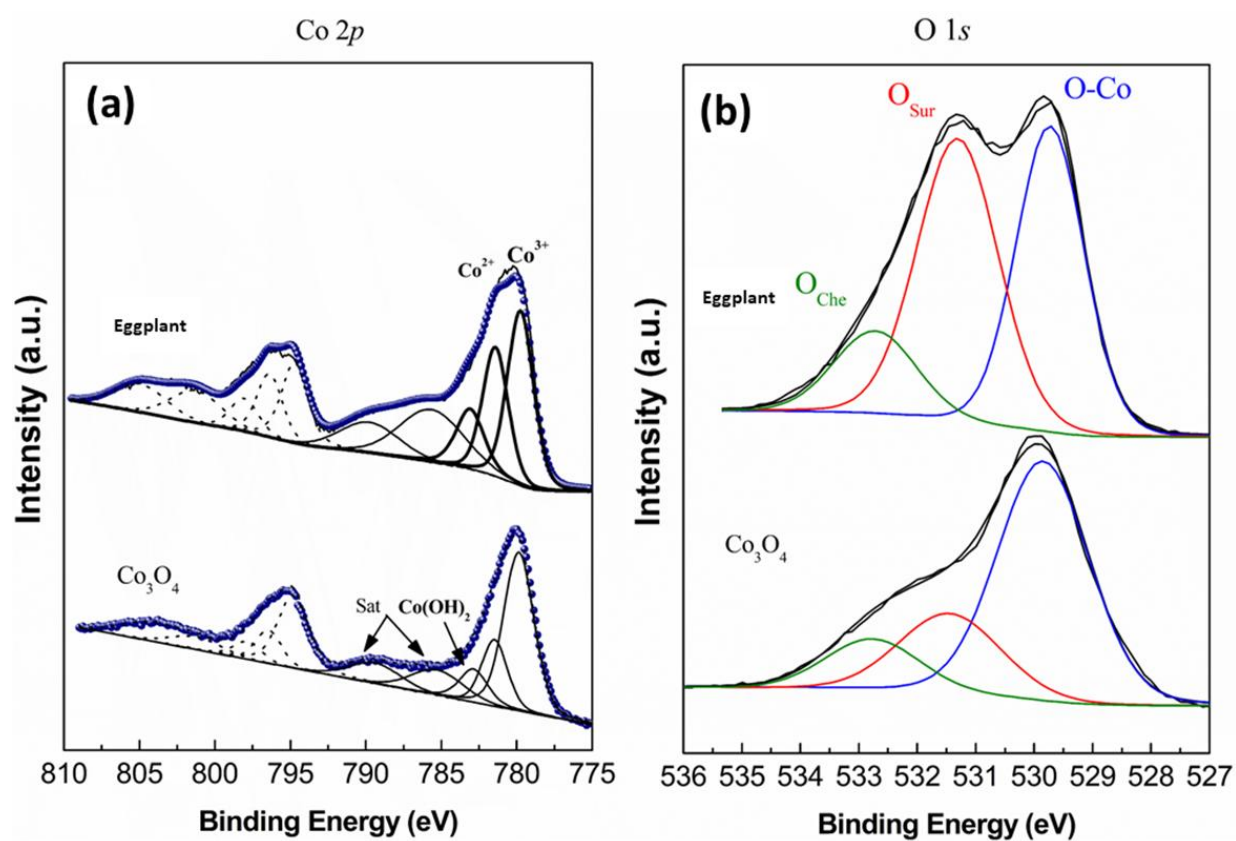


Figure 4: X-ray core level spectra of pure Co_3O_4 nanostructures and 15 mL rotten solanum melongena juice mediated Co_3O_4 nanostructures (a) Co $2p_{3/2}$, (b) O 1s.

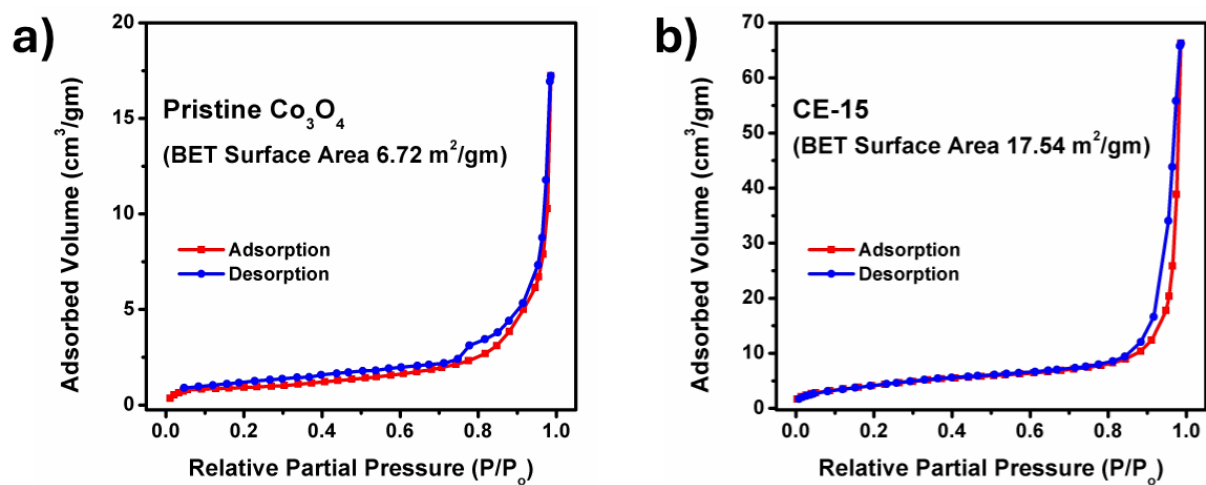


Figure 5: BET surface area analysis of pure Co_3O_4 nanostructures and 15 mL rotten solanum melongena juice mediated Co_3O_4 nanostructures.

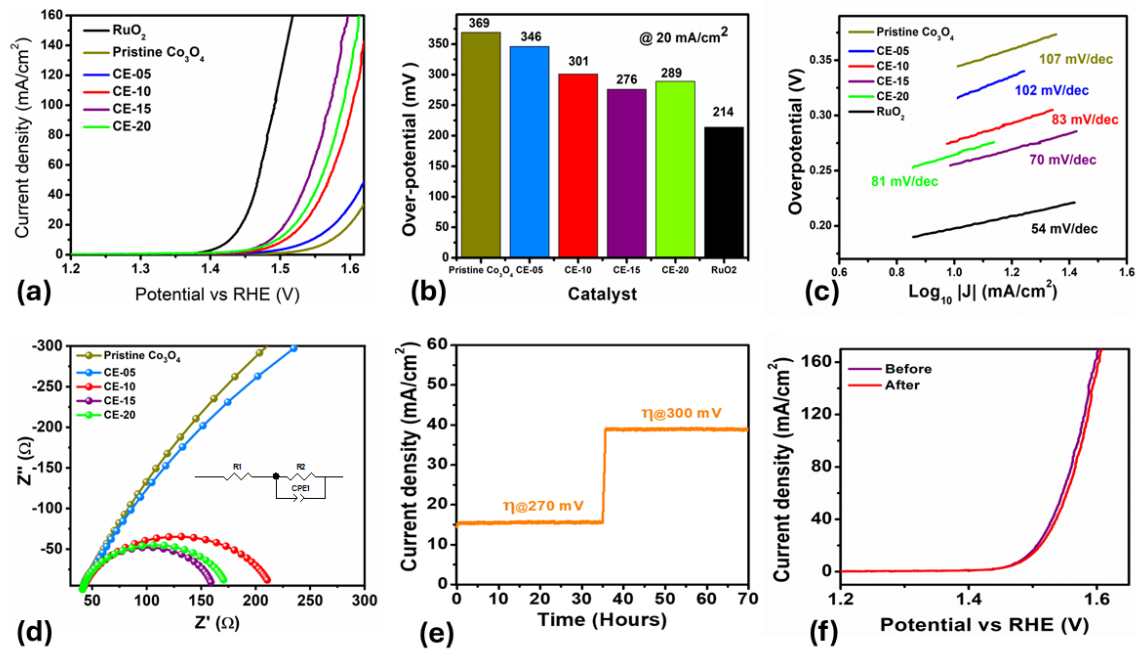


Figure 6: (a) OER polarization curves of pristine Co_3O_4 nanostructures, RuO_2 , and CE-05, CE-10, CE-15, CE-20, measured by LSV at 2 mV/s with iR corrected data, (b) Bar graph presentation of overpotential of each material at 20 mA cm^{-2} , (c) Corresponding Tafel slopes of each nanomaterial, (d) Charge transfer analysis using EIS Nyquist plots of various Co_3O_4 nanostructures with different volumes and without rotten solanum melongena juice using frequency range of 100 kHz to 0.1 Hz at an amplitude of 10 mV and OER onset potential of 1.4 vs RHE, inset shows the fitted equivalent circuit in 1.0M KOH aqueous solution, (e) Durability of Co_3O_4 nanostructures prepared with 15 mL of rotten solanum melongena for 15 hours at two different overpotentials of 270 mV and 300 mV for 70 h, (f) Stability of Co_3O_4 nanostructures prepared with 15 mL of rotten solanum melongena juice using LSV curves at 5 mV/s before and after durability test.

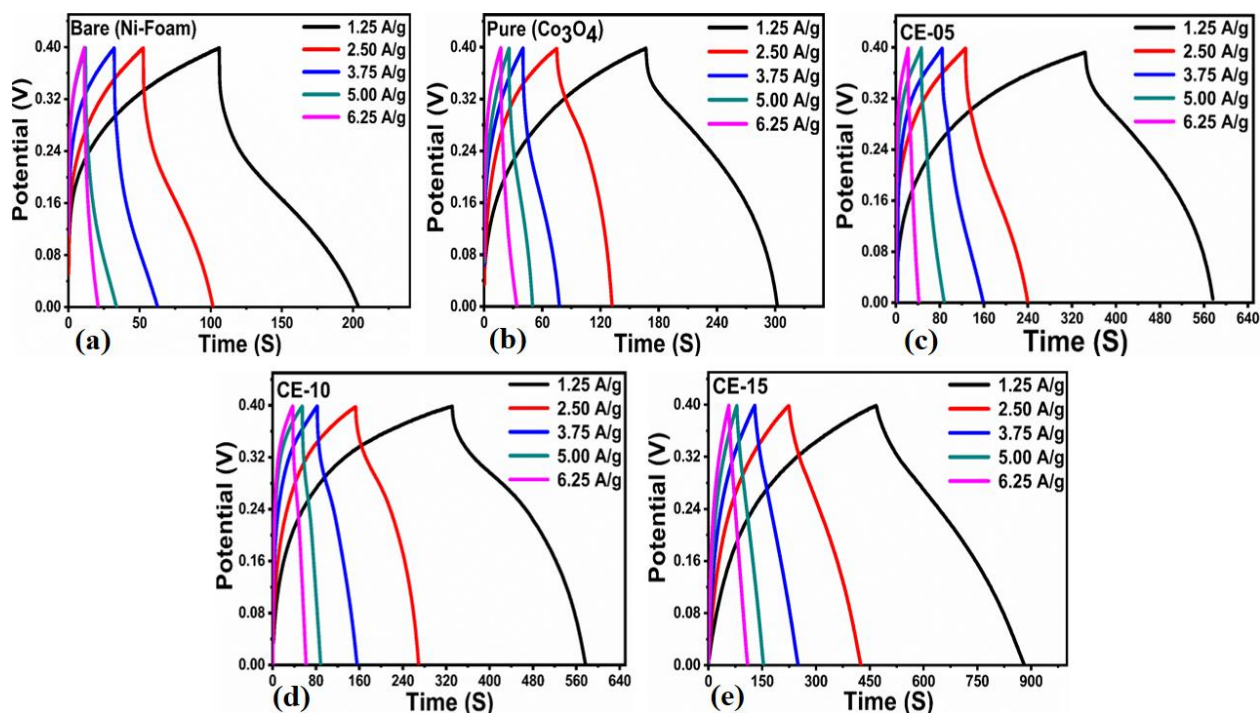


Figure. 7: (a-e) Co_3O_4 nanostructures with different volumes and without rotten solanum melongena juice like (CE-05, CE-10, CE-15, CE-20, CE stands for cobalt oxide-solanum melongena juice for the illustration of redox aspects using GCD curves at various current densities in 3.0 M KOH aqueous solution.

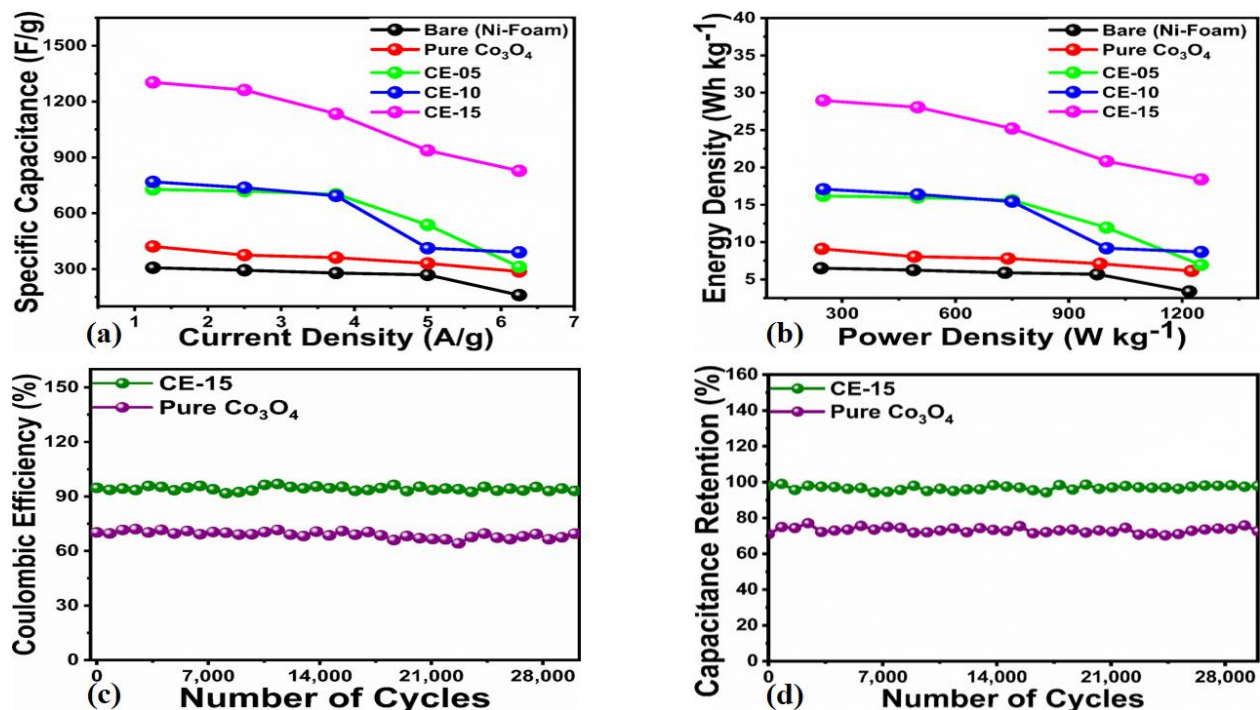


Figure. 8: (a) Estimated specific capacitance of Co_3O_4 nanostructures with different volumes and without rotten solanum melongena juice like (CE-05, CE-10, CE-15, CE-20, CE stands for cobalt oxide-solanum melongena from GCD curves in 3.0 M KOH aqueous solution, (b) Related energy density of Co_3O_4 nanostructures with different volumes and without solanum melongena for the illustration of redox aspects (c) columbic efficiency of Co_3O_4 nanostructures with different volumes and without rotten solanum melongena juice for the columbic efficiency (d) Corresponding percentage retention specific capacitance of Co_3O_4 nanostructures with different volumes and without rotten solanum melongena juice from 30000 GCD repeatable cycles in 3.0 M KOH for the demonstration of cycling stability.

Supplementary Information

Facile preparation of cobalt-oxide nanostructures with enrich Cobalt(II) ion surface using solanum-melongena for energy application

Abdul Jaleel Laghari^a, Umair Aftab^a, Muhammad Ishaque Abro^a, Aneela Tahira^f, Elmuez Dawi^g, Muhammad Ali Bhatti^e, Antonia Infantes-Molina^d, Melanie Emo^c, Brigitte Vigolo^c, Rafat M. Ibrahim^h, Zafar Hussain Ibupoto^b

^a*Department of Metallurgy and Materials, Mehran University of Engineering and Technology, 7680 Jamshoro, Sindh, Pakistan.*

^b*Institute of Chemistry, University of Sindh Jamshoro, 76080, Sindh, Pakistan.*

^c*Université de Lorraine, CNRS, IJL, F-54000 Nancy, France.*

^d*Department of Inorganic Chemistry, Crystallography and Mineralogy, Unidad Asociada al ICP-CSIC, Faculty of Sciences, University of Malaga, Campus de Teatinos, 29071, Malaga, Spain.*

^e*Centre for Environmental Sciences, University of Sindh Jamshoro, 76080, Sindh, Pakistan.*

^f*Institute of Chemistry, Shah Abdul Latif University Khairpur Mirs, Sindh, Pakistan.*

^g*College of Humanities and Sciences, department of Mathematics and Sciences, Ajman University, P.O.Box 346, Ajman, United Arab Emirates.*

^h*Physics Department, Faculty of Science, Taibah University, Al-Madaina Al Munawarah 42353, Saudi Arabia.*

**Corresponding author(s):*

Zafar Hussain Ibupoto, PhD, Email : zaffar.ibhupoto@usindh.edu.pk;

Muhammad Ishaque Abro, PhD, Email: ishaque.abro@faculty.muet.edu.pk

Table (S1): Crystallinity index, d-Spacing and lattice parameters calculated from XRD patterns.

S. No:	Sample IDs	Crystallinity index %	d-space	% Variance in d-space	Lattice parameter	% Variance in lattice parameter
1	Pristine	80.41	2.44	---	8.09	---
2	CE-05	79.42	2.444	0.164	8.108	0.222
3	CE-10	76.88	2.449	0.369	8.14	0.618
4	CE-15	75.38	2.455	0.615	8.184	1.162
5	CE-20	75.03	2.457	0.697	8.254	2.027

Phytochemical analysis methods

The phytochemical analysis methods was performed in following manner.

1. CARBOHYDRATES

. (General Test)

Molish's test

Add a few drops of concentrated H_2SO_4 (from the walls of the test tube) to the 2-3 ml aqueous extraction solution (a few drops of alcoholic α -naphthol). Shake well. A violet ring forms at the intersection of the two liquids.

. For reducing sugar)

Fehling's test

To the 2-3 ml aqueous extraction solution, add a few drops of concentrated H_2SO_4 (from the test tube walls) (a few drops of alcoholic α -naphthol). Give it a good shake. At the point where the two liquids meet, a violet ring appears.

Benedict's test: Add a few drops of concentrated H_2SO_4 (from the test tube walls) (a few drops of alcoholic α -naphthol) to the 2-3 ml aqueous extraction solution. Shake it thoroughly. At the spot where the two liquids contact, a violet ring develops.

. Monosaccharides

Barfoed's test

Equal volumes of Barfoed's reagent and test solution should be combined. Boil the mixture for one to two minutes, then let it cool. Precipitations turn red.

2. ALKALOIDS

. (Wagner's)

Wagner's reagent and 1 ml of HCl were added to the 2-3 ml filtrate, and everything was well shaken. A reddish-brown precipitate's formation indicated the presence of alkaloids.

3. FLAVONOIDS

. (Lead acetate Test)

Lead acetate solution was added to the little extract. The presence of flavonoids was indicated by the formation of a yellow precipitate.

4. PHENOLS /TANNINS


. (Ferric Chloride Test)

The extract will turn deep blue-black when 5% FeCl_3 solution is added.

5. TEST FOR NON-REDUCING POLY SACCHARIDES:

. Iodine test:

Mix 3ml test solution and few drops of weak iodine solution. The color turns blue; it vanishes when it boils and returns when it cools.

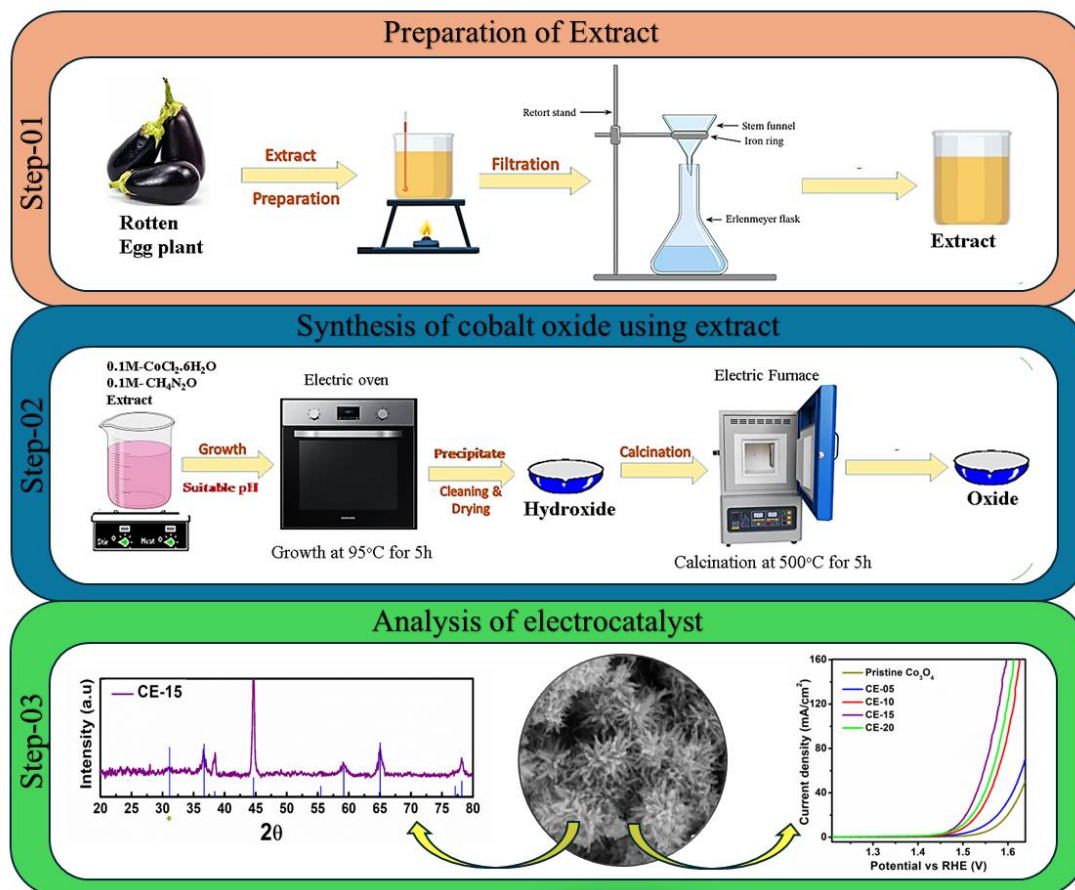

Supplementary (Scheme 1): Illustration of synthesis scheme and its interaction with heterostructure.

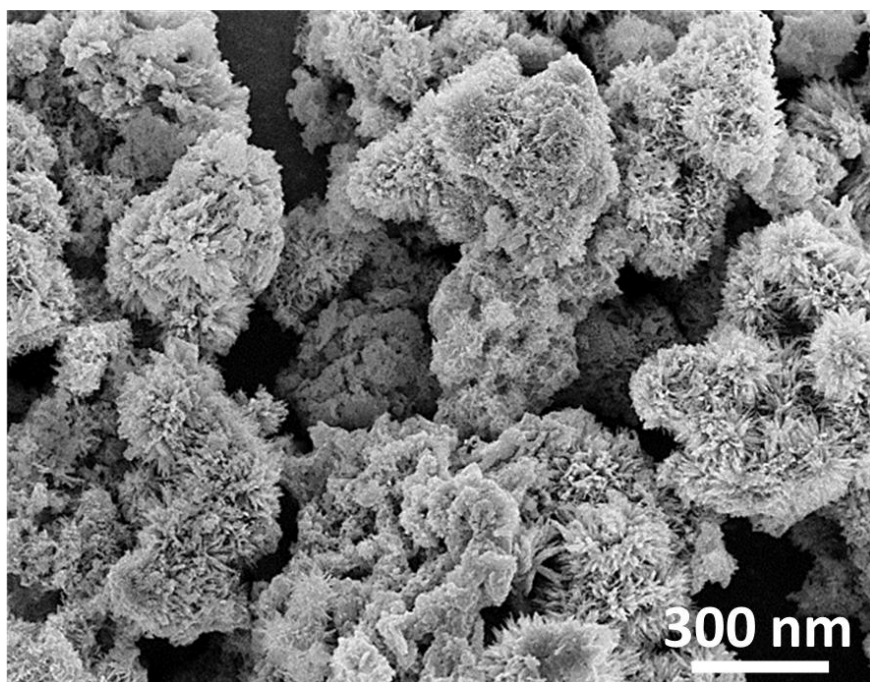


Figure (S1): Morphology after stability and durability test.

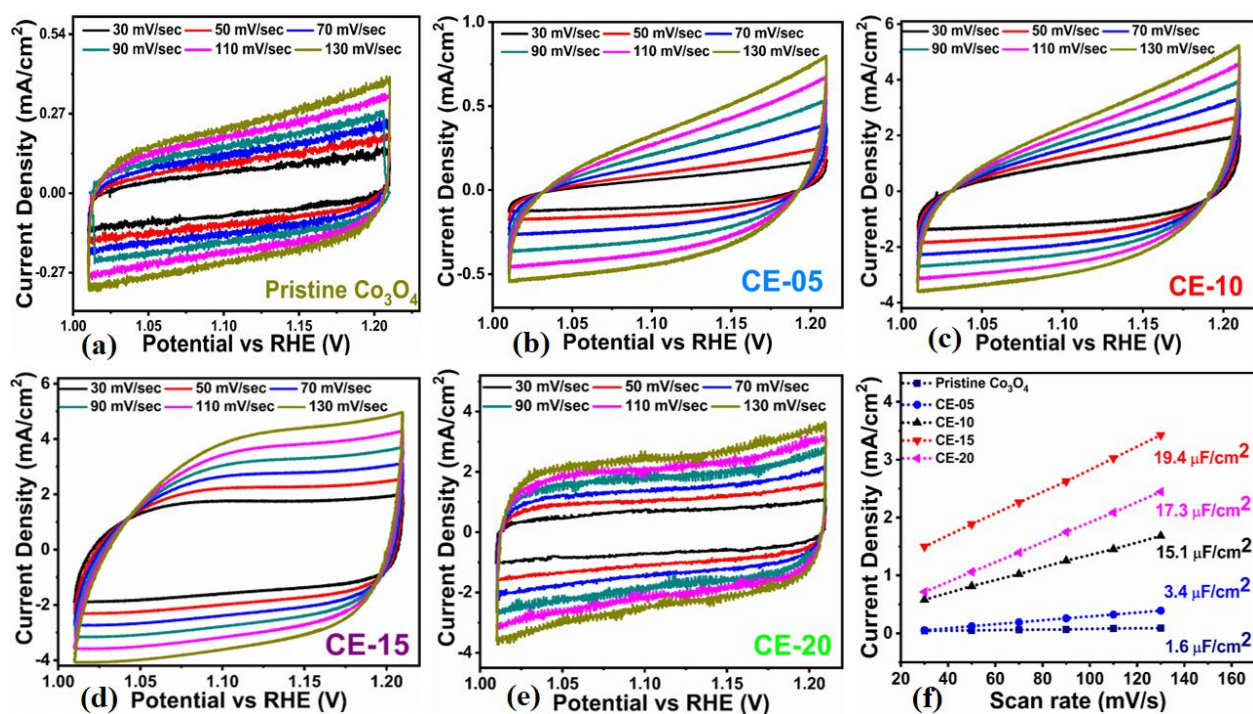


Figure (S2). (a-e) CV curves of Co_3O_4 nanostructures with different volumes and without rotten solanum melongenas juice like (CE-05, CE-10, CE-15, CE-20, CE stands for cobalt oxide) at various scan rates, (f) Related linear plot for the calculation of ECSA from the non-Faradic region of CV curves of Co_3O_4 nanostructures with different volumes and without rotten solanum melongenas juice.

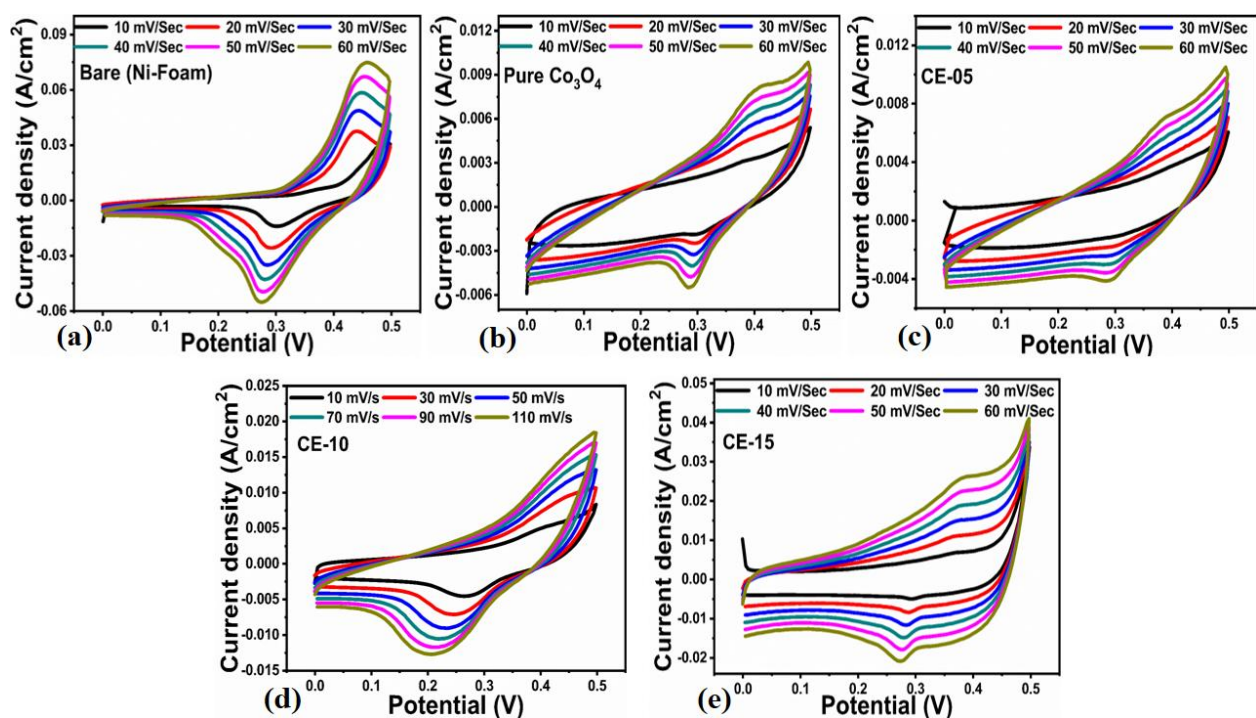


Figure. (S3): (a-e) bare nickel foam and Co_3O_4 nanostructures with different volumes and without rotten solanum melongena like (CE-05, CE-10, CE-15, CE-20, CE stands for cobalt oxide rotten solanum melongena juice) for the illustration of redox aspects using CV curves at different scan rates in 3.0M KOH aqueous solution.

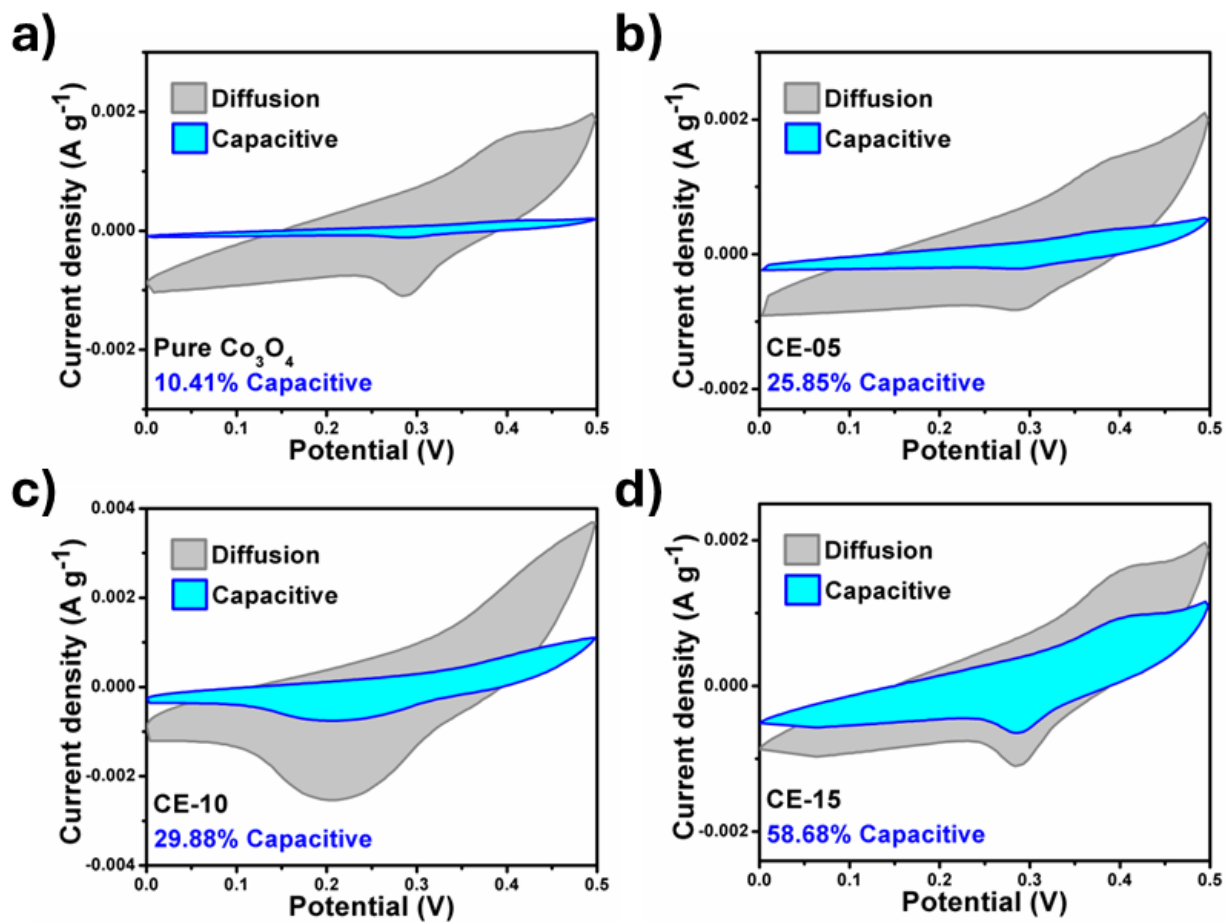


Figure (S4): (a-d) The illustration of diffusion and capacitive distribution of pure Co_3O_4 nanostructures and different (CE-05, CE-10, and CE-15) at 60 mV/s in 3M KOH solution.

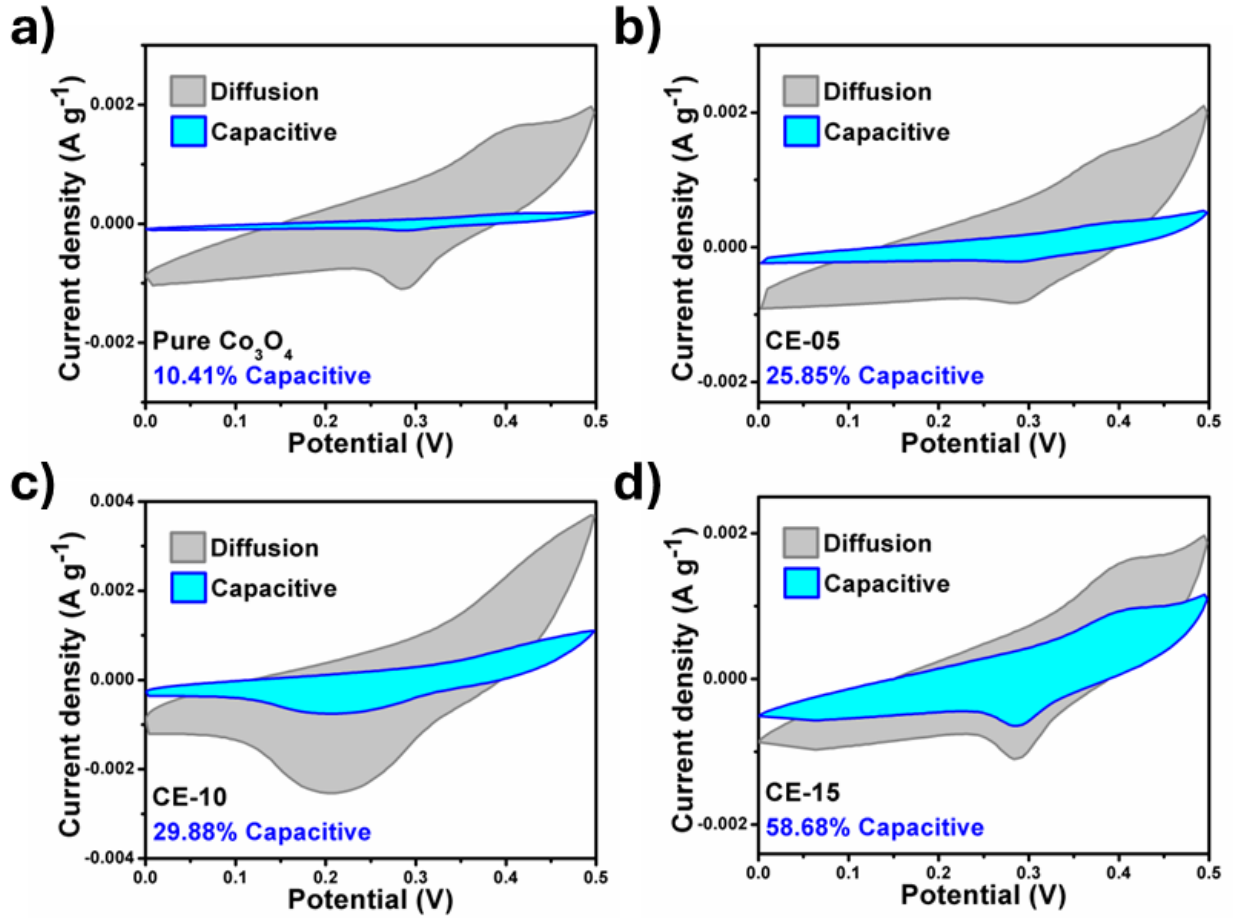


Figure (S5). (a-d) The diffusion and capacitive plots of pure Co₃O₄ nanostructures and different (CE-05, CE-10, and CE-15, CE stands for cobalt oxide rotten solanum melongenas juice) at various scan rates in 3M KOH solution .

The specific capacitance retention (%) is used to evaluate how much capacitance remains after repeated charge-discharge cycles, often in supercapacitor or battery testing. It is calculated using the following formula [1]:

$$\text{Specific Capacitance Retention (\%)} = C_n / C_0 \times 100 (\text{eq. S1})$$

Where ,

C₀ = initial specific capacitance (1st cycle)

C_n = specific capacitance after n cycles

The Coulombic Efficiency (CE) is a measure of how efficiently charge is transferred in a battery or supercapacitor during charge/discharge cycles. It is calculated using the following formula[2]:

$$\text{Coulombic Efficiency (\%)} = (\Delta t_{\text{discharge}}) / (\Delta t_{\text{charge}}) \times 100 \quad (\text{eq. S2})$$

Where:

$$\Delta t_{\text{discharge}} = \text{Discharging time (sec)}$$

$$\Delta t_{\text{charge}} = \text{Charging time (sec)}$$

Table (S2): Calculated values from LSV and CV curve of various Co_3O_4 nanostructures.

Catalyst	Calculated from LSV		Calculated from EIS		
	Over-potential @ 20 mA cm^{-2}	Tafel Slope mV dec^{-1}	Charge Transfer Resistance	Double Layer Capacitance	Double Layer Capacitance
	B	B	R_{ct}	CPE_{cdl}	C_{dl}
	mV	mV/dec	Ω	mF	$(\mu F \text{ cm}^{-2})$
<i>Pristine Co_3O_4</i>	369	107	1924	0.21	1.6
<i>CE-05</i>	346	102	1860	0.343	3.4
<i>CE-10</i>	301	83	599	0.40	7.2
<i>CE-15</i>	276	70	65	2.62	23
<i>CE-20</i>	289	81	122	1.67	14

Table (S3): Comparison of 15 mL rotten solanum melongenas juice mediated Co_3O_4 nanostructures OER performance with recently reported OER electrocatalysts.

Electrode material	Extract	Electrolyte KOH	Overpotential (mV)	Tafel (mV/dec)	References
Co₃O₄ (CE-15)	solanum melongenas	1 M	276	70	Present work
Co₃O₄	Plantago Ovata	1 M	328	71	[3]
CuO/ Co₃O₄	Aloe vera extract	1 M	453	49	[4]
Cobalt-Based Mixed Oxide	Tea Leaf	1 M	390	-	[5]
Carbon doped Cobalt-oxide	Tea leaf	1 M	380	-	[6]
CoS/ Co₃O₄	L-Lysine	1 M	304	-	[7]
Co₃O₄	Phyllanthus emblica	1 M	405	121	[8]
Co₃O₄-CoO	Gelialgas- Argagel	1 M	337	65	[9]

Table (S4): Provides comparative result of CE-15 mL rotten solanum melongenas juice mediated Co_3O_4 nanostructures with recently reported electrode materials for supercapacitor applications performance.

Material	Specific Capacitance (F/g)	Current Density (A/g)	Potential Window (V)	Energy Density (Wh/kg)	Power Density (W/kg)	Reference
NC6	1294 F/g	10 A/g	0.4 V	-	-	[10]
Ni-Co-O-1	568 F/g	20 A/g	0 to 0.5 V	19.72	5000	[11]
NiCoF	50 F/g	1 A/g	0 to 1 V	-	-	[12]
NCO@MWCNT/ /MWCNT	242 F/g	0.6 A/g	-0.5 to 2.2 V	61	2837	[13]
NiCo ₂ O ₄ (Lemon juice)	358 F/g	0.8 A/g	0 to 0.4 V	7.96	160	[14]
NiCo ₂ O ₄ (Grapefruit)	434 F/g	0.8 A/g	0 to 0.4 V	9.64	160	[15]
(Co ₃ O ₄) (MilkySap)	699 F/g	0.8 A/g	0 to 0.4 V	30	236	[16]
CE-15 (solanum melongenas)	1303 F/g	1.25 A/g	0 to 0.4 V	28.96	250	Present work

References

- [1] M. Sethi, U. S. Shenoy and D. K. Bhat, *Nanoscale Adv.*, 2020, 2, 4229–4241.
- [2] S. Sharma and P. Chand, *Results in Chemistry*, 2023, 5, 100885.
- [3] R. A. Raimundo, C. S. Lourenço, N. T. Câmara, T. R. Silva, J. R. D. Santos, A. J. M. Araújo, M. M. S. Silva, J. F. G. de A. Oliveira, D. A. Macedo, U. U. Gomes, M. A. Morales and M. M. Soares, *J. Electroanal. Chem.*, 2023, 932, 117218.
- [4] D. K. Sarkar, V. Selvanathan, M. Mottakin, M. A. Islam, H. Almohamadi, N. H. Alharthi and M. Akhtaruzzaman, *Int. J. Hydrogen Energy*, 2024, 51, 700–712.
- [5] X. Deng, C. K. Chan and H. Tüysüz, *ACS Appl. Mater. Interfaces*, 2016, 8, 32488–32495.
- [6] A. Bähr, H. Petersen and H. Tüysüz, *ChemCatChem*, 2021, 13, 3824–3835.
- [7] J. Hu, Z. Li, D. Zhao, Z. Han, X. Wu, J. Zhai, Z. Liu, Y. Tang and G. Fu, *Green Chem.*, 2023, 25, 7309–7317.
- [8] I. Ahmed, R. Raj, V. Burman, G. P. Singh and K. K. Haldar, *Waste Biomass Valorization*, 2024, DOI: 10.1007/s12649-024-02672-4.
- [9] R. A. Raimundo, J. N. Silva, T. R. Silva, A. J. M. Araújo, J. F. G. A. Oliveira, L. C. de Lima, M. A. Morales, M. M. Soares and D. A. Macedo, *Mater. Lett.*, 2023, 341, 134196.
- [10] M. Kaur, P. Chand and H. Anand, *J. Energy Storage*, 2022, 52, 104941.
- [11] H. Wang, Q. Gao and L. Jiang, *Small*, 2011, 7, 2454–2459.
- [12] B. Bhujun, M. T. T. Tan and A. S. Shanmugam, *Results Phys.*, 2017, 7, 345–353.
- [13] M. Pathak, J. R. Jose, B. Chakraborty and C. S. Rout, *J. Chem. Phys.*, 2020, 152.
- [14] S. Kumar, A. Tahira, A. L. Bhatti, M. A. Bhatti, R. H. Mari, N. M. Shaikh, M. Y. Solangi, A. Nafady, M. Emo, B. Vigolo, A. Infantes-Molina, A. Vomiero and Z. H. Ibupoto, *RSC Adv.*, 2023, 13, 18614–18626.
- [15] S. Kumar, A. Tahira, M. Emo, B. Vigolo, A. Infantes-Molina, A. M. Alotaibi, S. F. Shaikh, A. Nafady and Z. H. Ibupoto, *J. Energy Storage*, 2023, 68, 107708.
- [16] A. L. Bhatti, A. Tahira, S. Kumar, Z. A. Ujjan, M. A. Bhatti, S. Kumar, U. Aftab, A. Karsy, A. Nafady, A. Infantes-Molina and Z. H. Ibupoto, *RSC Adv.*, 2023, 13, 17710–17726.